



**HAL**  
open science

## **Kinetics of hematite chlorination with Cl<sub>2</sub> and Cl<sub>2</sub> + O<sub>2</sub>: Part I. Chlorination with Cl<sub>2</sub>**

Ndue Kanari, Devabrata Mishra, Lev Filippov, Frédéric Diot, Javier Mochón,  
Eric Allain

► **To cite this version:**

Ndue Kanari, Devabrata Mishra, Lev Filippov, Frédéric Diot, Javier Mochón, et al.. Kinetics of hematite chlorination with Cl<sub>2</sub> and Cl<sub>2</sub> + O<sub>2</sub>: Part I. Chlorination with Cl<sub>2</sub>. *Thermochimica Acta*, 2010, 497, pp.52-59. 10.1016/j.tca.2009.08.007 . hal-01506543

**HAL Id: hal-01506543**

**<https://hal.univ-lorraine.fr/hal-01506543>**

Submitted on 6 May 2017

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

## **Kinetics of Hematite Chlorination with $\text{Cl}_2$ and $\text{Cl}_2+\text{O}_2$**

### **Part I. Chlorination with $\text{Cl}_2$**

**N. Kanari<sup>a</sup>✉, D. Mishra<sup>a</sup>, L. Filippov<sup>a</sup>, F. Diot<sup>a</sup>, J. Mochón<sup>b</sup> and E. Allain<sup>a</sup>**

<sup>a</sup> Laboratoire Environnement et Minéralurgie, UMR 7569 CNRS, Nancy-University, ENSG, BP 40, 54501 Vandoeuvre-lès-Nancy Cedex, France

<sup>b</sup> CENIM - CSIC, Av. Gregorio del Amo 8, Madrid 28040, Spain

✉: Corresponding author, e - mail: ndue.kanari@ensg.inpl-nancy.fr

#### **Abstract**

Preliminary tests of the chlorination of two iron oxides (wüstite and hematite) in various chlorinating gas mixtures were performed by thermogravimetric analysis (TGA) under non isothermal conditions. Wüstite started to react with chlorine from about 200 °C generating ferric chloride and hematite as the final reaction products. The presence of a reducing and oxidation agent in the chlorinating gas mixtures influenced the chlorination reactions of both iron oxides, during non isothermal treatment, only at temperatures higher than 500 °C.

The chlorination kinetics of hematite with  $\text{Cl}_2$  have been studied in details between 600 and 1025 °C under isothermal chlorination. The values of the apparent activation energy ( $E_a$ ) were about 180 and 75 kJ/mol in the temperature ranges of 600 to 875 °C and 875 to 1025 °C, respectively. The apparent reaction order with respect to  $\text{Cl}_2$  was found to be 0.67 at 750 °C. Mathematical model fitting of the kinetics data was carried out to determine the most probable reaction mechanisms.

*Keywords:* Hematite, Thermogravimetric analysis, Chlorination, Kinetics.

## 1. Introduction

Chlorine technology is proved to be an efficient method for the extraction of several non - common metals such as Zr, Hf, Nb, Ta, Ti, rare-earth elements, the treatment of solid wastes, the upgrading of lean ores and minerals, etc. The attractiveness of chlorine metallurgy is essentially based on:

- (i) high reactivity of chlorine towards almost all metals, many metal oxides and sulphides etc.,
- (ii) appreciable differences in the boiling points of metal chlorides and / or oxychlorides for a good number of metals,
- (iii) low boiling points of metal chlorides and /or oxychlorides, etc.

An overview concerning several chlorination methods developed by our laboratory in the past two decades was presented recently [1]. Besides, various industrial practices of chlorine metallurgy for several non - common metals, can be found from the review work of Korshunov [2].

Iron is the fourth most abundant element, constituting about 5.0 % by weight of the earth crust [3]. It is found naturally in the form of oxides or sulphides and it also constitutes an important part of the primary ores of several valuable metals such as Cu, Zn, Cr, Pb, Ti, Nb, Ta etc. and of metallurgical wastes containing some of these metals. The extraction of these metals and / or upgrading of their ores by chlorination process depends on the amount and nature of the iron compounds content. In some cases, such as from laterites [4], jarosites [5], steel making waste dusts [6], slags from tin metallurgy [7], etc., selective separation of nonferrous metals are desirable, while in other cases, for example in the upgrading of chromite [8], bauxite [9], ilmenite [10], etc., removal of Fe as volatile chlorides has been proved to be highly beneficial. Selectivity in the processes, as mentioned above, is greatly dependent on the nature of interaction between iron oxides and different chlorinating agents.

The thermodynamic of Fe - O - Cl system are well known. Furthermore, this item becomes easily available thanks to thermochemical databases such as 'HSC Chemistry' [11] designed for many

different kinds of chemical reactions and equilibria calculations. Whilst, the kinetics parameters are derived from experimental studies. A literature survey on the chlorination of iron oxides (wüstite, magnetite and hematite) in various chlorination mediums was given in an early work [12]. Thus, only a summary of the chlorination kinetics of hematite using the most usual chlorination agents found in the literature is shown in Table 1.

The literature survey indicated that several reports are available for the chlorination kinetics of hematite with  $\text{Cl}_2$ , but little information is available for the oxychlorination behavior of hematite. The values of the apparent activation energy of hematite chlorination varied from about 6 kJ/mol to 200 kJ/mol depending on the chlorinating agent used and on the temperature range explored. Moreover, the kinetics parameters obtained are generally dependent on the investigation methodology. For instance, research works regarding the use of nominal flow rate of gases in order to minimize the starvation phenomena and mass transfers through the boundary layer around the sample were seldom performed.

The objective of the present study is to explore the chlorination and oxychlorination kinetics of hematite and to understand the reaction mechanisms occurring between chlorine and iron oxides. In this part, results of non isothermal chlorination of wüstite and hematite obtained under different atmospheres followed by the isothermal kinetics of hematite chlorination between 600 - 1025 °C are revealed and discussed.

## **2. Materials and experimental procedures**

The hematite sample of 99 pct purity used in this study was obtained from Merck Chemicals (Eurolab, France). A sample of wüstite was also used for some experimental tests. It was prepared by hematite reduction using a controlled  $\text{H}_2$ - $\text{H}_2\text{O}$  atmosphere. The elemental composition and structure of both samples were checked by scanning electron microscopy 'SEM' and x-ray diffraction 'XRD' analyses, respectively. The chlorination of iron oxides was measured by a thermogravimetric analysis (TGA) technique described previously [22]. Its main unit is a CAHN

1000 microbalance having a sensitivity of 10  $\mu\text{g}$ . A sample of about 40 mg was uniformly distributed in a quartz crucible having a section of about 0.5  $\text{cm}^2$ . This crucible is suspended to the balance by a quartz chain. During the non isothermal treatment, the sample was directly heated in the chlorinating gas mixture by an electrical furnace. Data obtained was plotted as evolution of % weight change as a function of temperature. One may emphasize that all negative values represent % weight losses (% WL), whilst positive ones express % weight gains.

For the isothermal runs, the sample was first heated in nitrogen atmosphere up to a given temperature before introducing the reactive gases ( $\text{Cl}_2$ , or  $\text{Cl}_2+\text{N}_2$ ). The sample chlorination extent is deduced from the percent weight change of the sample as a function of time.

### **3. Results**

#### ***3.1. Non isothermal chlorination tests of iron oxides***


Three experimental tests of wüstite sample chlorination were performed under isothermal condition from 25  $^{\circ}\text{C}$  to 1000  $^{\circ}\text{C}$  in  $\text{Cl}_2+\text{CO}$ ,  $\text{Cl}_2+\text{N}_2$  and  $\text{Cl}_2+\text{air}$  gas mixtures having an equimolar proportion of their constituents. The heating rate of the furnace was about 25  $^{\circ}\text{C}/\text{minute}$ . The experimental results are grouped in Figure 1 as weight change (%) as function of temperature.

A rough analysis of these plots suggests that the reaction of wüstite with the three chlorinating gas mixtures started at temperatures as low than below 250  $^{\circ}\text{C}$  and a maximum weight gain is reached at about 325  $^{\circ}\text{C}$ . Since then, only losses of sample weight were observed up to temperatures approaching 500  $^{\circ}\text{C}$ . The effect of oxygen on the reaction of wüstite with chlorine seems to be limited as the three curves almost overlap at temperatures lower than 500  $^{\circ}\text{C}$ . During the chlorination with  $\text{Cl}_2+\text{CO}$ , an additional continuous weight loss was observed from 550  $^{\circ}\text{C}$  and the full sample had reacted at  $T < 1000$   $^{\circ}\text{C}$ . Whilst, a plateau in weight change was observed up to about 750  $^{\circ}\text{C}$  during chlorination with  $\text{Cl}_2+\text{N}_2$  and  $\text{Cl}_2+\text{air}$ , and about 50 % WL and 42 % WL of samples were observed at 1000  $^{\circ}\text{C}$ , respectively.

Tests of the chlorinating of wüstite for all chlorinating gas mixtures were stopped at 550  $^{\circ}\text{C}$  and

the partially reacted samples were subjected to XRD analysis. Only hematite (Fe<sub>2</sub>O<sub>3</sub>) was identified as crystallized phase whichever was the chlorinating gas mixture indicating the oxidation of Fe<sup>2+</sup> into Fe<sup>3+</sup> during chlorination.

The reactions of ferrous oxide with Cl<sub>2</sub> and Cl<sub>2</sub>+CO to be considered are shown by Eqs. 1 to 4 and 5 to 8, respectively. From a thermodynamic point of view, all these envisaged reactions are favorable up to 1000 °C [11].



The phase stability diagram of the system Fe-O-Cl[11] is given in Figure 2. It suggests that at high chlorine partial pressure and low partial pressure of oxygen the predominant stable phase is ferric chloride. The ferrous chloride becomes a predominant specie only at low partial pressure of chlorine. The evolution of vapor pressure of ferrous and ferric chloride as a function of the temperature is shown in Figure 3 [23]. It is clear from this Figure that FeCl<sub>3</sub> possesses a high vapor pressure at temperatures close to 300 °C. One may mention that ferric chloride is volatilized as a dimer (Fe<sub>2</sub>Cl<sub>6</sub>) at low temperature and as a monomer (FeCl<sub>3</sub>) at high temperature. Ferrous chloride is in solid state up to about 700 °C and it has a vapor pressure nearing 1 atm only at 726 °C.

These thermodynamic considerations seem to be in good agreement with the results of Figure 1. In other words, wustite reacted with chlorine resulting to hematite and volatile ferric chloride as final reaction products. The weight loss observed in Figure 1 was shifted towards higher temperatures due to the heating rate (25 °C/minute) of the furnace which was somewhat higher. If ferrous chloride is formed (Eq. 1 and 5), it is probably transformed to ferric chloride because of the

high partial pressure of chlorine. Few boat experimental tests performed earlier [12] about the chlorination of wüstite in  $\text{Cl}_2+\text{CO}$  at 2 hours showed that full reaction and volatilization of the reaction products were achieved at 550 °C indicating that  $\text{FeCl}_3$  is the final chlorinated compound.

This study shows that the overall reaction of wüstite with chlorine can be described by Eqs. [4] and [8]. It seems that carbon monoxide has little effect on the chlorination of wüstite at low temperatures during non isothermal treatment. Similar results were reported in other investigations [14], [15]

An hematite sample was also subjected to non isothermal treatments under conditions identical to those described above for wüstite. Results obtained for the chlorination of wüstite allow to assume Eqs. [9] and [10] for the reaction of  $\text{Fe}_2\text{O}_3$  with  $\text{Cl}_2$  and  $\text{Cl}_2+\text{CO}$ , respectively. Data obtained for the non isothermal chlorination of hematite is charted in Figure 4. Hematite seems to be inert in chlorinating atmospheres up to about 550 °C in spite of the presence of carbon monoxide. However, full carbochlorination ( $\text{Cl}_2+\text{CO}$ ) of the sample was achieved at about 1000 °C.



Hematite starts to react with  $\text{Cl}_2+\text{N}_2$  from 700 °C and only 30 % of sample had reacted at 1000 °C. Similarly, the reaction of  $\text{Fe}_2\text{O}_3$  with  $\text{Cl}_2+\text{air}$  is obvious at high temperature and the reaction extent at 1000 °C is somewhat lower than with  $\text{Cl}_2+\text{N}_2$ . This result may be explained by the presence of oxygen shifting the reaction of hematite chlorination [Eq. 9] from the right to the left side of the equation.

An examination of Figure 1 and Figure 4 indicates that the curves of the chlorination of wüstite and hematite have same trend and shape for a selected chlorinating gas mixture at temperatures higher than 550 °C. This is an indirect confirmation of  $\text{Fe}_2\text{O}_3$  formation during the treatment of wüstite at low temperatures. Another information from these non isothermal tests is the formation of volatile ferric chloride during the chlorination of iron oxides. With this assumption, the isothermal chlorination of hematite at temperatures equal to and higher than 600 °C leads to a complete gasification of the reaction product. Consequently, the % WL of sample is directly related

to the reaction extent of hematite with chlorine.

### 3.2. Effect of chlorine flow rate

In order to determine the intrinsic parameters of the gas - solid reactions, it is suitable to minimize the effect of the external mass transfer phenomena. This could be achieved by using a sufficient flow rate of reactive gases. The effect of Cl<sub>2</sub> gas flow rate on the chlorination reaction rate of hematite is studied at 750 and 950 °C. The gas flow rate of chlorine was varied from 5 to 70 liter per hour (L/h).

Figure 5 gives a typical example of evolution of weight change (right ordinate) of the sample as a function of time during hematite chlorination at 750 °C at 5 and 70 L/h of chlorine. This Figure contains also the reaction rate evolution (left ordinate) versus time for the two chosen flow rates of chlorine. The reaction rate is calculated as  $-dWL/dt$  and expressed as  $-\%WL/minute$ . More than 80 % of sample has reacted for a reaction time of 80 minutes when a Cl<sub>2</sub> flow rate of 70 L/h was used, whilst less than 48 % of the reaction were observed for the same time at 5 L/h of chlorine. As also shown by Figure 5, the reaction rate remains almost constant versus time when a low flow rate was used, as illustrated by the linear aspect of the weight change curve. This is a typical example of a reaction governed by external mass transfer.

Chlorine flow rates data were converted into chlorine linear velocity ones ' $V_g$ ' taking into account the cross section area of the reactor and the obtained values are expressed as  $cm\ min^{-1}$ . An average reaction rate is calculated for a reaction extent ' $X$ ':  $0.05 \leq X \leq 0.40$  for all isothermal data obtained at 750 °C and 950 °C.

Figure 6 summarizes the results of reaction rate evolution as a function of chlorine velocity for both temperatures. As shown by Figure 6 (a), the reaction rate at 750 °C is almost independent from the chlorine linear velocity at values higher than about 30 cm/min. As it could be expected, at 950 °C, the chlorination rate of hematite is more dependent on the chlorine velocity (Figure (6b)). A chlorine velocity higher than 50 cm/min will be required to minimize the effect of mass transfer phenomena in the reaction. However, chlorine with a  $V_g$  of 50 cm/min is used to investigate the



effect of other parameters on the chlorination of hematite.

### 3.3. Effect of temperature

Series of isothermal tests were carried out at different temperatures ranging from 600 to 1025 °C using Cl<sub>2</sub> at a constant chlorine velocity of 50 cm/min. Figures 7(a) and 7(b) show the % weight change versus time curves obtained by the chlorination of Fe<sub>2</sub>O<sub>3</sub>. At 600 °C and a reaction time of 10 hours, the weight loss is less than 25 %. The reaction rate increases steadily as the temperature rises between 600 °C and 1025 °C and about 90 pct of sample are chlorinated at 950 °C for a reaction time of about 6 min.

The average reaction rate of the obtained isotherms is calculated using the initial almost linear stage for a reaction extent 'X' (0.05 < X < 0.40). The Arrhenius plot is given in Figure 8. The apparent activation energy 'E<sub>a</sub>' is 180±4 kJ/mol for the temperature range of 600 to 875 °C. Such a high value suggests that the chlorination mechanism of Fe<sub>2</sub>O<sub>3</sub> is controlled by the chemical reaction in this temperature range. As indicated by Figure 8, the chlorination of Fe<sub>2</sub>O<sub>3</sub> beyond 875 °C proceeds with an E<sub>a</sub> value of about 74 kJ/mol. Similar values of E<sub>a</sub>, although in different temperature intervals, are also reported in the literature. Bertoti et al. [15] found an apparent activation energy of about 188 kJ/mol and 100 kJ/mol in the temperature ranges of 597-777° C and 777-807 °C during the chlorination of hematite by chlorine.

To correlate these activation energy values with a change of reaction mechanism, a mathematical formulation of the experimental data is attempted using the following equations [24].

$$1 - (1 - X)^{1/Fp} = kt \quad [11]$$

$$X = kt \quad (\text{for } Fp = 1) \quad [12]$$

$$1 - (1 - X)^{1/2} = kt \quad (\text{for } Fp = 2) \quad [13]$$

$$1 - (1 - X)^{1/3} = kt \quad (\text{for } Fp = 3) \quad [14]$$

where  $k$  = constant,  $t$  = chlorination time,

$X$  = extent of reaction (ratio of weight of the reacted fraction to initial weight),

$F_p$  = particle shape factor (1 for infinite slabs, 2 for long cylinders and 3 for spheres).

Equation [11] is considered to describe a reaction controlled by the chemical reaction in the case of shrinking nonporous particles (with or without a solid porous product) and porous particles with unchanged overall sizes. It also applies for a mechanism affected by pore diffusion in the case of complete gasification of porous solids. One may underline that the chlorination of hematite at the explored temperature range belongs to the reactions of complete gasification of solids. As mentioned in section 3.1, iron tri-oxide ( $\text{Fe}_2\text{O}_3$ ) is converted to iron tri-chloride ( $\text{FeCl}_3$ ) which is volatile at temperatures higher than 300 °C.

Figure 9 (a) and (b) shows the mathematical fitting of the experimental data obtained during the chlorination of hematite between 600 and 875 °C by using Eq. [14]. The correlation coefficient of the data linearization is close to unity. This supports the hypothesis that the chlorination reaction of  $\text{Fe}_2\text{O}_3$  particles is controlled by the chemical reaction according to the shrinking sphere model described by Eq. [14]. While, the best fitting data for temperatures higher than or equal to 900 °C (Figure 9 (c)) is obtained by using Eq. [12]. This result combined with the value of  $E_a \approx 74$  kJ/mol suggests that the chlorination of hematite is probably diffusion controlled in this temperature range. As mentioned in section 3.2, the chlorine velocity maintained at this temperature is lower than the optimum one required for minimizing the mass transfer phenomena (see Figure 6 (b)).

Typical examples of isotherms in two distinguished temperature regions are shown in Figure 10 displaying the evolution of the weight changes (right ordinate) and reaction rates (left ordinate) as a function of the reaction time. Figure 10 (a) shows that the weight change curve versus time follows mostly a one-third-power law function for the chlorination of hematite at 700 °C. The deduced reaction rate decreased rapidly with time, at least, for a weight loss up to 75 pct. As a contrast, plots of data obtained at 1000 °C show a linear dependency of weight change versus time with an almost constant reaction rate during the first three minutes of chlorination. Again, these parameters' variation at 1000 °C must be indicative trends only for a reaction controlled by a diffusion step.

### 3.4. Effect of partial pressure of chlorine

To determine this effect, a series of experimental tests was carried out at 750 °C. Nitrogen was used as diluting gas and a total gas velocity was kept at 50 cm/min. The chlorine partial pressure was varied from 0.20 to 1.00 atm. Figure 11 (a) gives the evolution of % weight change as a function of time for different chlorine partial pressures. As it could be expected, the chlorination extent, for a given reaction time, increased with partial pressure of chlorine in the Cl<sub>2</sub>+N<sub>2</sub> gaseous mixtures. The evolution of reaction rate as a function of Cl<sub>2</sub> partial pressure is shown in Figure 11 (b) in natural logarithm scale. The apparent reaction order with respect to chlorine '<sup>n</sup>Cl<sub>2</sub>' derived from this figure is about 0.67. It appears difficult to hypothesis about the paths of the hematite chlorination by chlorine. However, such value of '<sup>n</sup>Cl<sub>2</sub>' seems to indicate that the molecular chlorine could be dissociated before reacting with hematite. Mathematical formulation of the experimental data for different partial pressure of chlorine was established using equations [11] to [14]. This data, shown by Figure 12, matches Eq. [14] well with an average correlation coefficient of 0.999 confirming that the rate of the chemical reaction remains the rate controlling step of the overall process of chlorination for partial pressures of chlorine ranging from 0.20 to 1.00 atm.

## 4. Conclusions

1. Wüstite reacted with chlorine at low temperatures generating hematite and ferric chloride as final reaction products. The presence of carbon monoxide affected the chlorination rate for hematite chlorination especially at high temperatures during non isothermal conditions.
2. Under isothermal conditions, hematite started to react with chlorine from at least 600 °C and the reaction becomes very fast at temperatures approaching 1025 °C.
3. Two temperature regions have been distinguished for the chlorination of hematite. The first one is comprised between 600 and 875 °C and is characterized by an apparent activation energy of about 180 kJ/mol. Mathematical fitting of experimental data indicates that the

shrinking sphere model is the most adequate to describe the reaction of hematite chlorination in this temperature range. Beyond this temperature, there is a second temperature dependency for which the overall reaction is mostly controlled by diffusion phenomena with a value of  $E_a$  of about 74 kJ/mol.

4. Chlorination of hematite at 750 °C depended slightly on the partial pressure of chlorine resulting to an apparent reaction order of 0.67. Decreasing the  $Cl_2$  partial pressure in the chlorinating gas mixture from 1.00 to 0.20 atm does not affect the rate controlling step of hematite chlorination.

### **Acknowledgments**

This work was performed in the frame of contract N° BRE2 - CT92 - 0173. Thanks to the financial support of the European Union (DG - XII).

### **References**

- [1] N. Kanari E. Allain, R. Joussemet, J. Mochón, I. Ruiz-Bustanza, I. Gaballah, “An overview study of chlorination reactions applied to the primary extraction and recycling of metals and to the synthesis of new reagents”, *Paper in press, Thermochemica Acta*.
- [2] B.G. Korshunov, “Applications and potential use of chlorination methods in metallurgy of non - common metals”, *Metallurgical Review*, 8(2), (1992), pp. 1 - 33.
- [3] F.W. Clarke, “The relative abundance of the chemical elements”, *Bull. Phil. Soc. Washington*, 1889, Vol 11, pp. 131.
- [4] S.B. Kanungo, S.K. Mishra, “Kinetics of chloridization of nickel bearing lateritic iron ore by hydrogen chloride gas”, *Metallurgical and Materials Transactions B*, 28B, (1997), pp. 389 - 399.
- [5] N. Kanari, A. Bonazezi, E. Allain, I. Gaballah, “Decontamination of jarosite through thermal treatment” *Proceeding of the international conference: Recycling and waste treatment in*

mineral and metal processing: Technical and economic aspects, Luleå, June 2002, Sweden, Vol. 1, pp. 909 - 918.

- [6] L. Komorova, I. Imris, I. Novak, "Chlorinating roasting of steel making waste dusts", Zbornik Vedeckych Prac (Vysokej Skoly Technickej V. Kosiciach), 110, (1979), pp. 97 - 109.
- [7] I. Gaballah, E. Allain, M. Djona, "Extraction of tantalum and niobium compounds from tin slags by chlorination and carbochlorination of pure oxides and concentrates", Metallurgical and Materials Transactions B, (1997), V 28B, pp. 359 - 369
- [8] N. Kanari, I. Gaballah, E. Allain, "Use of chlorination for chromite upgrading", Thermochemica Acta, 351(1 - 2), (2000), pp. 109 - 117.
- [9] I. Szabo, A. Ujhidy, R. Jelinko, I. Vassanyi, "Decrease of iron content of bauxite through high temperature chlorination", Hung. J. Ind. Chem., 17(4), (1989), pp. 465 - 475.
- [10] F.C. Gennari, A.E. Bohe, D.M. Pasquevich, "Effect of reaction temperature on the chlorination of a  $\text{Fe}_2\text{O}_3$  -  $\text{TiO}_2$  - C mixture", Thermochemica Acta, 302, (1997), pp. 53 - 61.
- [11] A. Roine: Outokumpu HSC Chemistry for windows, version 3.0, Outokumpu Research, Pori, Finland, April 1997.
- [12] N. Kanari, Extraction des métaux de valeur des concentrés de chalcopirite et de chromite par chloruration, Ph.D. Thesis, Institut National Polytechnique de Lorraine, Laboratoire Environnement et Mineralurgie, Nancy, France, November 1995, 209 pages.
- [13] Y. Okahara, I. Iwasaki, "Chlorination of manganiferous iron ores", Trans. Soc. Mining Eng. AIME, 247, (1970), pp. 73-80.
- [14] I.S. Pap, I. Bertoti, T. Szekely, I.Z. Babievskaya, L. Bottyan, "TG studies on the reactions of hematite, magnetite and wüstite with  $\text{COCl}_2$  and  $\text{CO}+\text{Cl}_2$ ", Thermochemica Acta, 92, (1985), pp. 587-590.
- [15] I. Bertoti, I.S. Pap, T. Szekely, I.Z. Babievskaya, "Comparative thermogravimetric study of chlorinations of hematite and wüstite", J. Therm. Anal., 32 (1), (1987), pp. 281-292.
- [16] I. Bertoti, I.S. Pap, T. Szekely, I.Z. Babievskaya, L. Bottyan, "TG studies on the reactions of hematite, magnetite and wüstite with  $\text{CCl}_4$ ", Thermochemica Acta, 85, (1985), pp. 87-90.

- [17] G. Daradimos, U. Kuxmann, "Chlorination of SnO<sub>2</sub> and Fe<sub>2</sub>O<sub>3</sub> with chlorine gas in the temperature range from 700 to 1050 °C", *Erzmetall*, 24 (4), (1971), pp. 163-172.
- [18] R. Titi-Manyaka, I. Iwasaki, "Thermogravimetric investigation of the chlorination behaviors of some common metals and their oxides", *Trans. Soc. Mining Eng. AIME*, 252, (1972), pp. 307-313.
- [19] V.I. Evdokimov, I.Z. Babievskaya, N.F. Drobot, I. Bertoti, I. Pap, T. Szekely, "The reaction of iron oxides with chlorine", *Zh. Neorg. Khim.*, 30 (6), (1985), pp. 1507-1512.
- [20] R.J. Fruehan, L.J. Martonik, "Rate of chlorination of metals and oxides: Part III. Rate of chlorination of Fe<sub>2</sub>O<sub>3</sub> and NiO in Cl<sub>2</sub> and HCl", *Met. Trans.*, 4 (12), (1973), pp. 2793-2797.
- [21] F.C. Gennari, D.M. Pasquevich, "Kinetics of chlorination of hematite", *Thermochimica Acta*, 284, (1996), pp. 325 - 339.
- [22] N. Kanari, I. Gaballah, "Reactivity of Magnesium Oxide in Different Chlorination Gas Mixtures" (Paper presented at the 127<sup>th</sup> TMS Annual Meeting 'EPD Congress 1998', San Antonio, TX, Edited by B. Mishra, Pub. by TMS, 1998), pp. 595 – 609.
- [23] D.R. Lide, Ed., *Handbook of Chemistry and Physics*, 74<sup>th</sup> edition, Boca Raton, New York, London, Tokyo, 1993-94, 6-68 to 6-70.
- [24] J. Szekely, J. W. Evans, H. Y. Sohn, "*Gas - Solid Reactions*" (Academic Press, New York, NY, 1976) 68 - 70, 73 - 88, 109 - 131 and 232 - 235.

Table 1. Works devoted to the chlorination of hematite by different chlorinating agents.

Chlorinating Agent	Temperature Range <sup>a</sup> , °C	Observations	Reference
C+Cl <sub>2</sub>	25-800	Formation of FeCl <sub>2</sub> which volatilized as FeCl <sub>3</sub> .	[13]
CO+Cl <sub>2</sub>	27-727	Reaction started at T > 577 °C with formation of Fe <sub>2</sub> Cl <sub>6</sub> .	[14]
CO+Cl <sub>2</sub>	27-927	E <sub>a</sub> <sup>b</sup> = 84 kJ/mol between 327 °C and 527 °C.	[15]
COCl <sub>2</sub>	27-727	Reaction started at T > 427 °C with formation of Fe <sub>2</sub> Cl <sub>6</sub> .	[14]
COCl <sub>2</sub>	27-927	E <sub>a</sub> = 88 kJ/mol between 237 °C and 297 °C. E <sub>a</sub> = 60 kJ/mol between 297 °C and 447 °C.	[15]
CCl <sub>4</sub>	27-927	E <sub>a</sub> = 125 kJ/mol between 397 °C and 597 °C, n <sup>c</sup> CCl <sub>4</sub> = 0.5 at 527 °C.	[16]
CCl <sub>4</sub>	27-927	E <sub>a</sub> = 130 kJ/mol between 452 °C and 552 °C.	[15]
Cl <sub>2</sub>	25-800	Reaction started at 700 °C generating FeCl <sub>3</sub> and O <sub>2</sub> .	[13]
Cl <sub>2</sub>	700-900	E <sub>a</sub> = 136.8 kJ/mol, nCl <sub>2</sub> = 0.85.	[17]
Cl <sub>2</sub>	25-900	E <sub>a</sub> ≈ 96 kJ/mol between 700 °C and 900 °C.	[18]
Cl <sub>2</sub>	597 to > 777	E <sub>a</sub> = 188 - 191 kJ/mol between 597 °C and 777 °C, E <sub>a</sub> = 100 kJ/mol at T > 777 °C.	[19]
Cl <sub>2</sub>	27-927	E <sub>a</sub> = 188 kJ/mol between 597 °C and 777 °C, E <sub>a</sub> = 100 kJ/mol between 777 °C and 807 °C.	[15]
Cl <sub>2</sub>	800-1200	E <sub>a</sub> = 167 kJ/mol, nCl <sub>2</sub> = 1.	[20]
Cl <sub>2</sub>	600-950	E <sub>a</sub> = 200 kJ/mol between 600 °C and 750 °C. E <sub>a</sub> = 125 kJ/mol between 750 °C and 950 °C.	[21]
Cl <sub>2</sub> +O <sub>2</sub>	700-900	nCl <sub>2</sub> = 2.75.	[17]
Cl <sub>2</sub> +O <sub>2</sub>	25-900	Oxygen had little effect from 0 to 40 %.	[18]
HCl	25-900	Formation of FeOCl decomposing from 300 °C to 400 °C.	[18]
HCl	800-1000	E <sub>a</sub> = 34 kJ/mol, nHCl = 1.	[17]
HCl	25-750	Formation of FeOCl, E <sub>a</sub> = 5.9 kJ/mol.	[20]

<sup>a</sup> When treatment starts from room temperature, non isothermal conditions were also used.

<sup>b</sup> Apparent activation energy.

<sup>c</sup> Apparent reaction order.

# Kinetics of Hematite Chlorination with $\text{Cl}_2$ and $\text{Cl}_2+\text{O}_2$

## Part I. Chlorination with $\text{Cl}_2$

N. Kanari<sup>a</sup>✉, D. Mishra<sup>a</sup>, L. Filippov<sup>a</sup>, F. Diot<sup>a</sup>, J. Mochón<sup>b</sup> and E. Allain<sup>a</sup>

<sup>a</sup> Laboratoire Environnement et Minéralurgie, UMR 7569 CNRS, Nancy-University, ENSG, BP 40, 54501 Vandoeuvre-lès-Nancy Cedex, France

<sup>b</sup> CENIM - CSIC, Av. Gregorio del Amo 8, Madrid 28040, Spain

✉: Corresponding author, e - mail: ndue.kanari@ensg.inpl-nancy.fr

### FIGURE CAPTIONS

- Figure 1** : Non isothermal treatment of wüstite in different chlorinating gas mixtures.
- Figure 2** : Phase stability diagram of the Fe-O-Cl system at 800 °C.
- Figure 3** : Vapor pressure evolution as a function of the temperature for ferrous and ferric chlorides.
- Figure 4** : Non isothermal treatment of hematite in different chlorinating gas mixtures.
- Figure 5** : Isothermal treatment of hematite at 750 °C for two chosen flow rates and evolution of the reaction rate as a function of the reaction time.
- Figure 6** : Effect of chlorine velocity on the reaction rate of  $\text{Fe}_2\text{O}_3$  chlorination at 750 and 950 °C.
- Figure 7** : Isotherms of  $\text{Fe}_2\text{O}_3$  chlorination between 600 and 1025 °C.
- Figure 8** : Arrhenius diagram of  $\text{Fe}_2\text{O}_3$  chlorination between 600 and 1025 °C.
- Figure 9** : Mathematical fitting of data for the chlorination at: (a) & (b):  $T \leq 875$  °C using Eq. [14] (c):  $T \geq 900$  °C using Eq. [12].
- Figure 10** : Reaction rate evolution versus time during hematite chlorination at 700 and 1000 °C.
- Figure 11** : Effect of chlorine partial pressure on the  $\text{Fe}_2\text{O}_3$  chlorination at 750 °C.
- Figure 12** : Mathematical fitting of experimental data of Figure 11 (a).



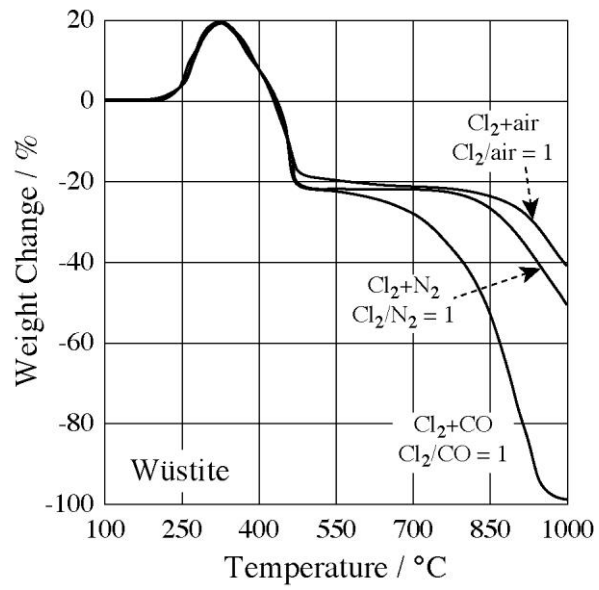


Figure 1: Non isothermal treatment of wüstite in different chlorinating gas mixtures.

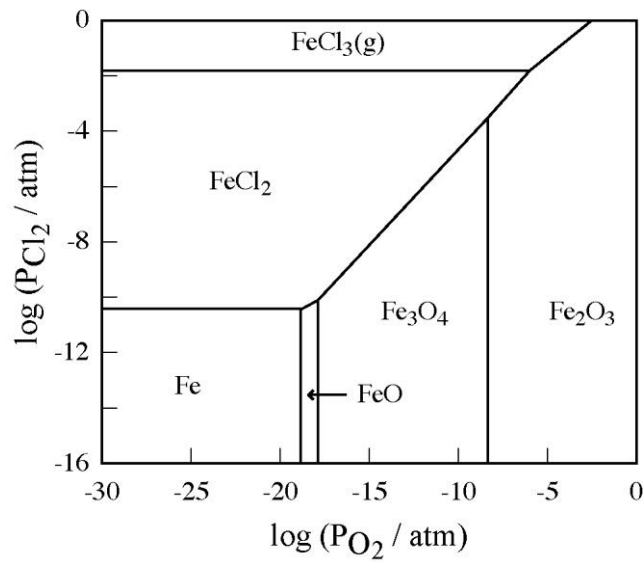


Figure 2: Phase stability diagram of the Fe-O-Cl system at 800 °C.

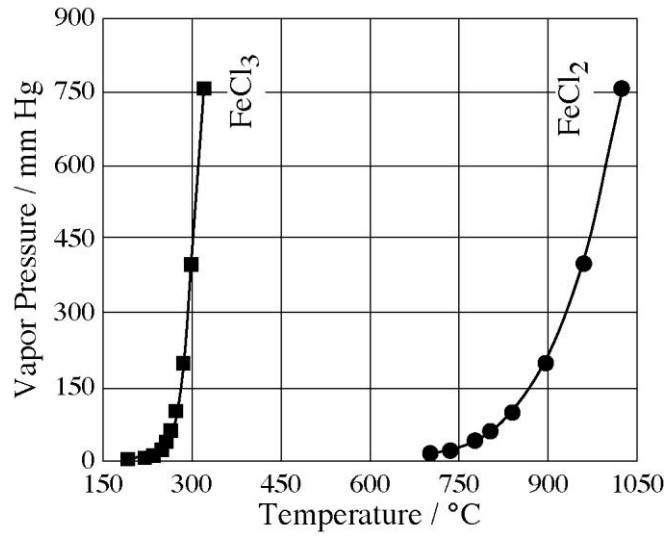


Figure 3: Vapor pressure evolution as a function of the temperature for ferric and ferrous chlorides.

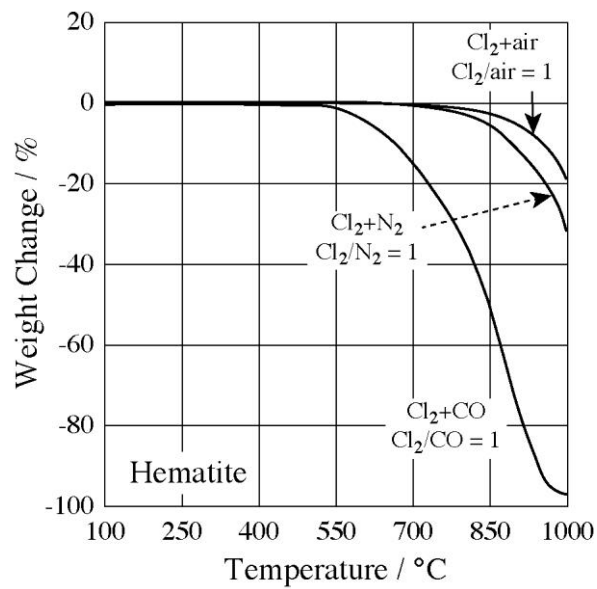


Figure 4: Non isothermal treatment of hematite in different chlorinating gas mixtures.

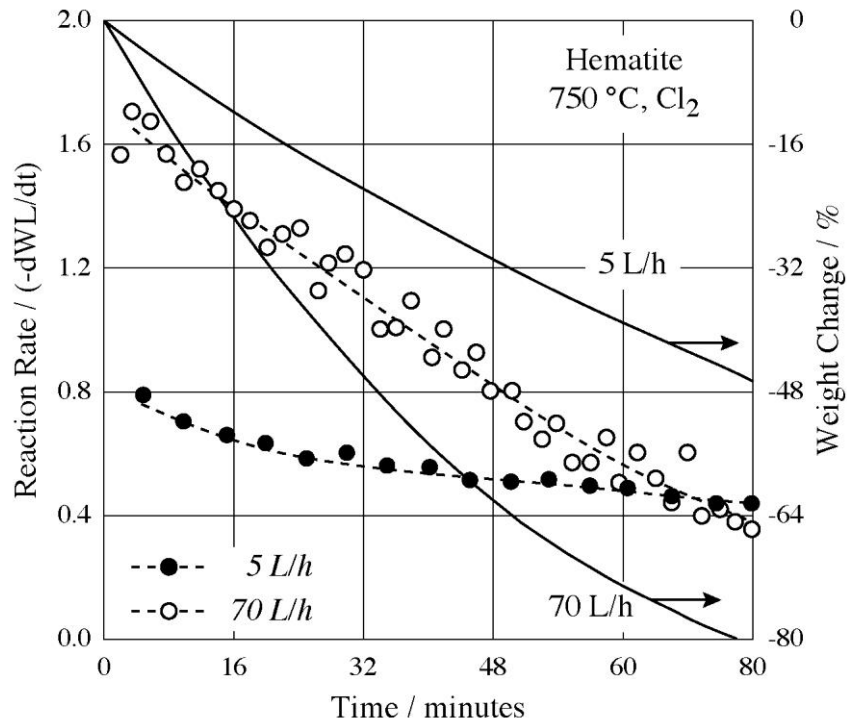


Figure 5: Isothermal treatment of hematite at 750 °C for two chosen flow rates and evolution of the reaction rate as a function of the reaction time.

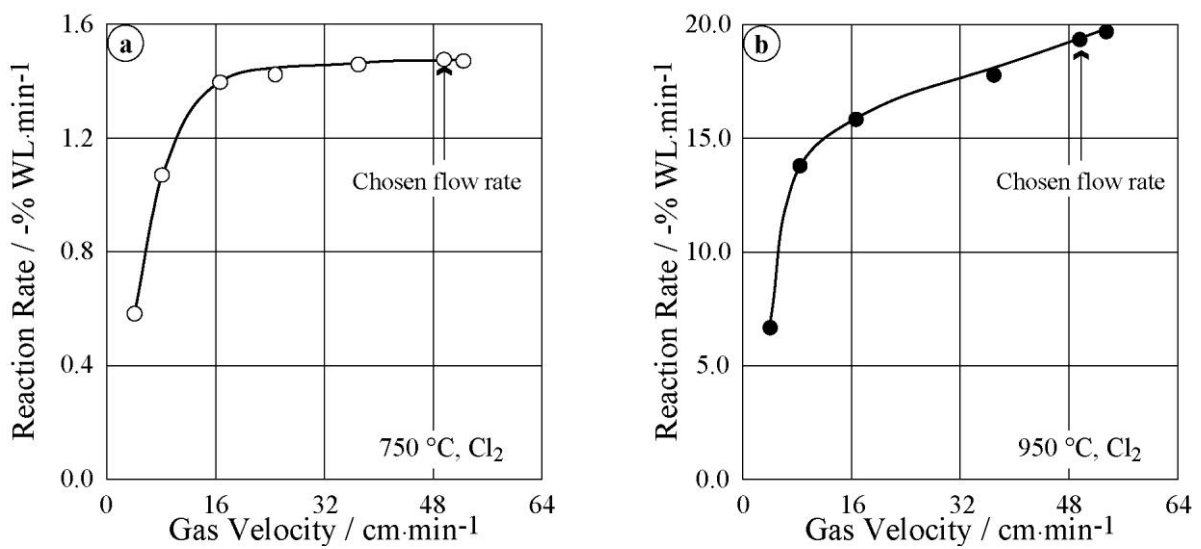


Figure 6: Effect of chlorine velocity on the reaction rate of Fe<sub>2</sub>O<sub>3</sub> chlorination at 750 and 950 °C.

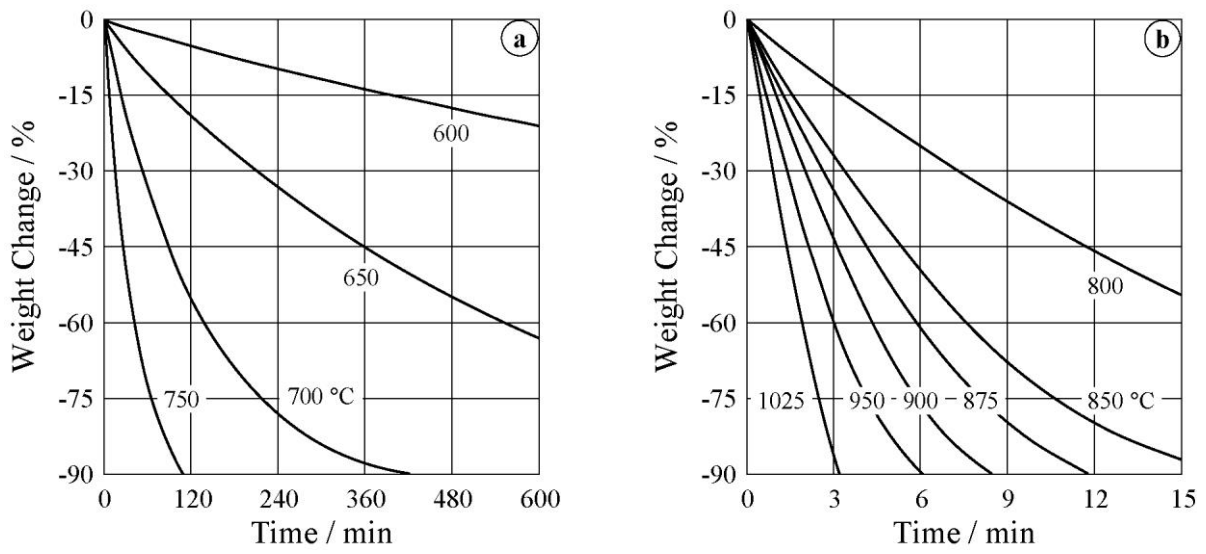


Figure 7: Isotherms of Fe<sub>2</sub>O<sub>3</sub> chlorination between 600 and 1025 °C.

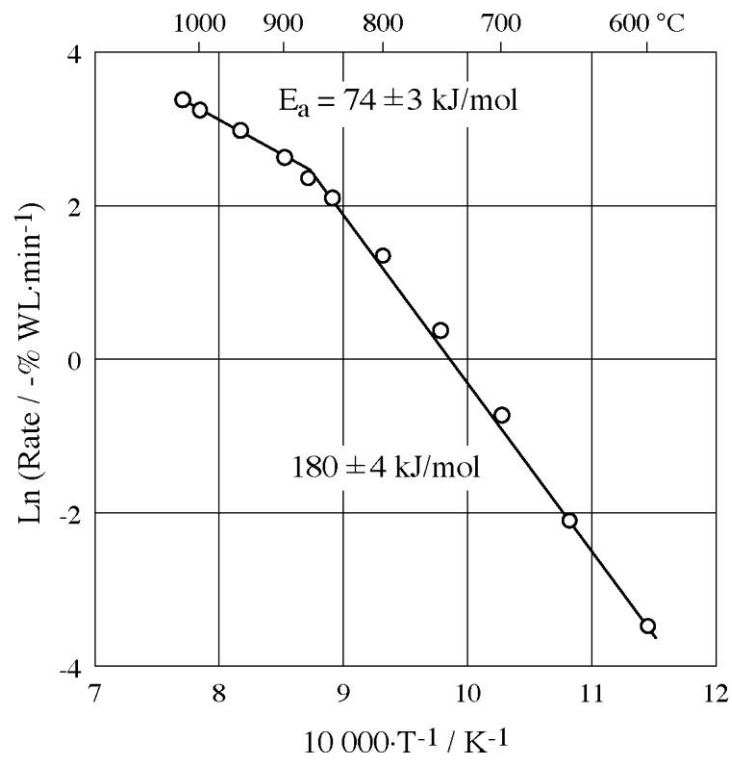


Figure 8: Arrhenius diagram of Fe<sub>2</sub>O<sub>3</sub> chlorination between 600 and 1025 °C.

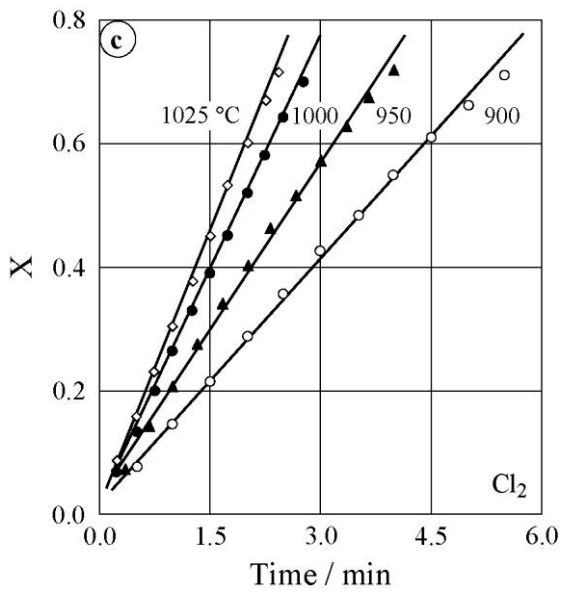
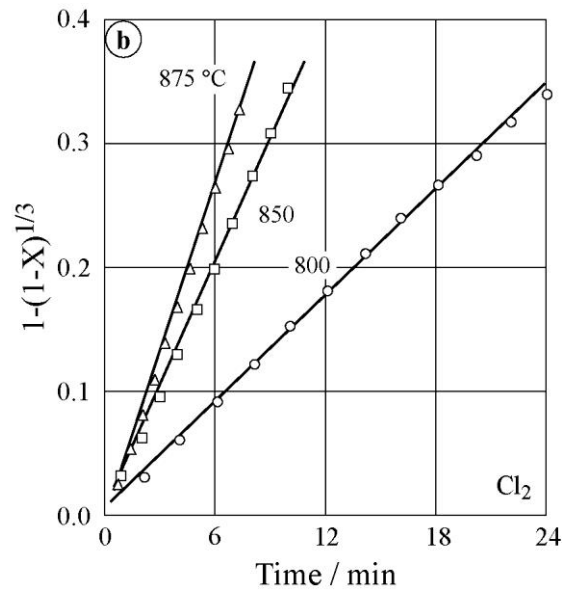
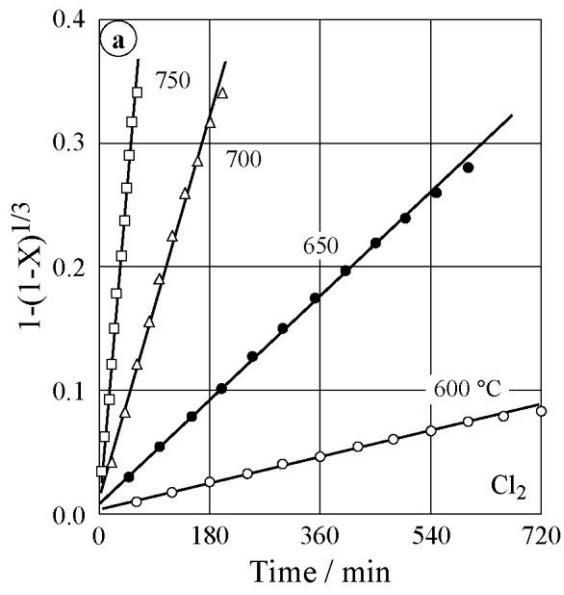


Figure 9: Mathematical fitting of data for the chlorination at:

(a) & (b):  $T \leq 875$  °C using Eq. [14]

(c):  $T \geq 900$  °C using Eq. [12].

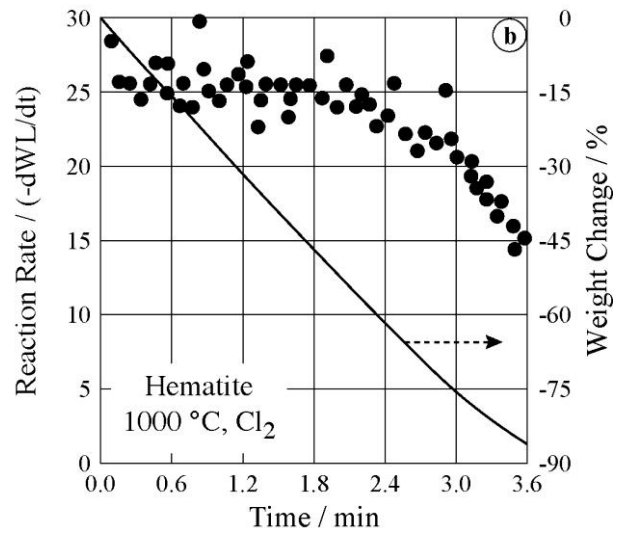
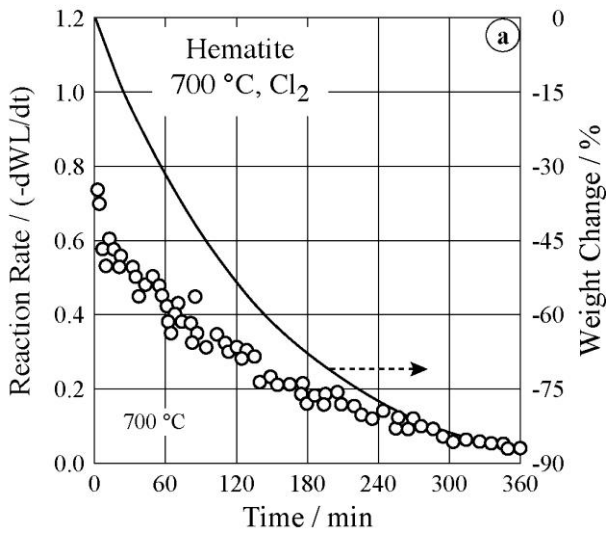


Figure 10: Reaction rate evolution versus time during hematite chlorination at 700 and 1000 °C.

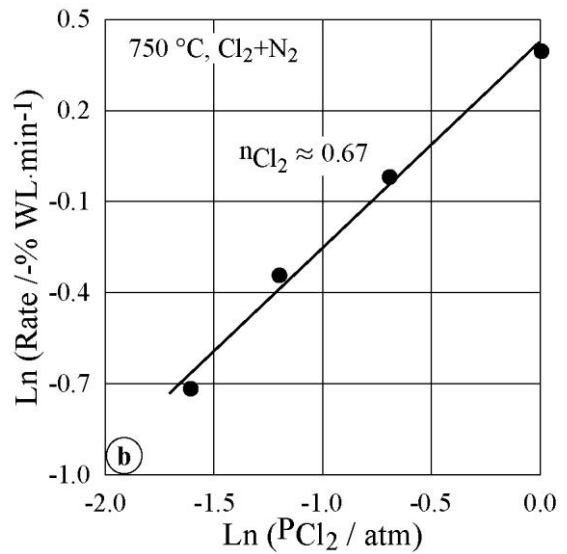
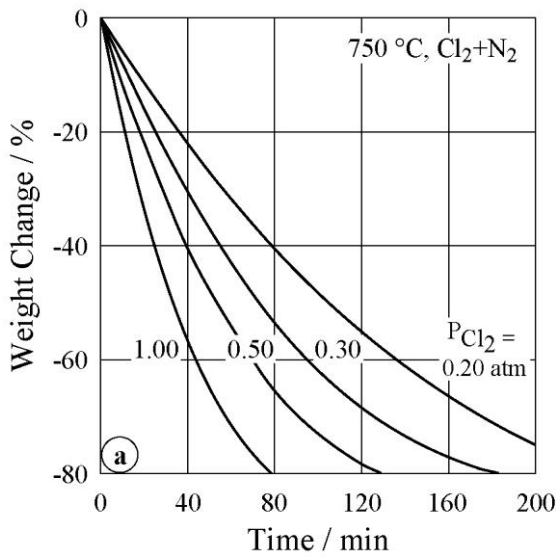


Figure 11: Effect of chlorine partial pressure on the  $\text{Fe}_2\text{O}_3$  chlorination at 750 °C.

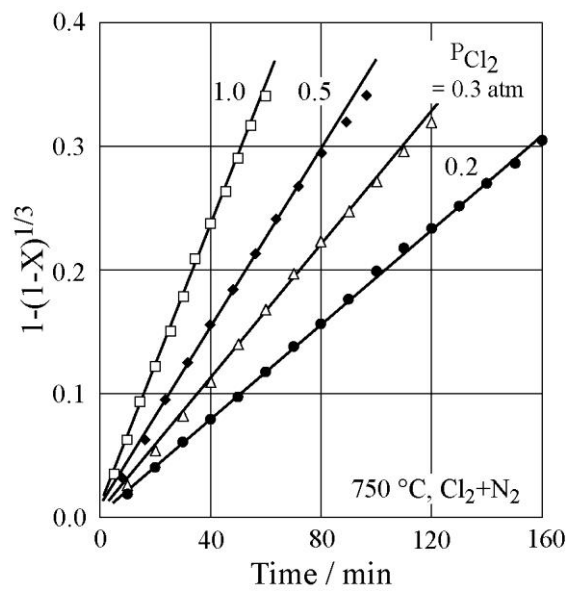


Figure 12: Mathematical fitting of experimental data of Figure 11 (a).