



**HAL**  
open science

## Reduction of chlordecone environmental availability by soil amendment of biochars and activated carbons from lignocellulosic biomass

Ronald Ranguin, Corine Jean-Marius, Christelle Yacou, Sarra Gaspard, Cyril Feidt, Guido Rychen, Matthieu Delannoy

### ► To cite this version:

Ronald Ranguin, Corine Jean-Marius, Christelle Yacou, Sarra Gaspard, Cyril Feidt, et al.. Reduction of chlordecone environmental availability by soil amendment of biochars and activated carbons from lignocellulosic biomass. *Environmental Science and Pollution Research*, 2020, 27 (33), pp.41093-41104. 10.1007/s11356-019-07366-2 . hal-02510064

**HAL Id: hal-02510064**

**<https://hal.univ-lorraine.fr/hal-02510064>**

Submitted on 8 Mar 2022

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Reduction of chlordecone environmental availability by soil amendment of biochars and activated carbons from lignocellulosic biomass

Ronald Ranguin<sup>a</sup> ; Corine Jean-Marius<sup>a</sup> ; Christelle Yacou<sup>a</sup> ; Sarra Gaspard<sup>a</sup> ; Cyril Feidt<sup>b</sup> ; Guido Rychen<sup>b</sup> ; Matthieu Delannoy<sup>b</sup>

**a : Laboratoire COVACHIMM, EA 3592, Université des Antilles et de la Guyane, BP 250, 97157 Pointe-à-Pitre Cedex, Guadeloupe, France**

**b : Université de Lorraine-INRA (USC340), URAFPA, 54500 Vandœuvre-lès-Nancy, France**

Published in *Environmental Science and Pollution Research*. Available online: 23/01/2020 <https://doi.org/10.1007/s11356-019-07366-2>

## Keywords

Chlordecone . Environmental availability . Activated carbon . Biochar . Soil

## Abstract

Chlordecone (kepone or CLD) was formerly used in French West Indies as an insecticide. Despite its formal ban in 1993, high levels of this pesticide are still found in soils. As such, sequestering matrices like biochars or activated carbons (ACs) may successfully decrease the bioavailability of halogenated compounds like CLD when added to contaminated soils. The present study intends (i) to produce contrasted sequestering matrices in order to (ii) assess their respective efficiency to reduce CLD environmental availability. Hence, the work was designed following two experimental steps. The first one consisted at producing different sequestering media (biochars and ACs) via pyrolysis and distinct activation processes, using two lignocellulosic precursors (raw biomass): oak wood (*Quercus ilex*) and coconut shell (*Cocos nucifera*). The chemical activation was carried out with phosphoric acid while physical activation was done with carbon dioxide and steam. In the second step, the CLD environmental availability was assessed either in an OECD artificial soil or in an Antillean contaminated nitisol (i.e. 2.1 µg CLD per g of soil Dry Matter, DM), both amended with 5wt% of biochar or 5wt% of AC.

These both steps aim to determine CLD environmental availability reduction efficiency of these media when added (i) to a standard soil material or (ii) to a soil representative of the Antillean CLD contamination context. Textural characteristics of the derived coconut and oak biochars and ACs were determined by nitrogen adsorption at 77K. Mixed microporous and mesoporous textures consisting of high pore volume (ranging from 0.38 cm<sup>3</sup>.g<sup>-1</sup> to 2.00 cm<sup>3</sup>.g<sup>-1</sup>) and specific (BET) surface areas from 299.9 m<sup>2</sup>.g<sup>-1</sup> to 1285.1 m<sup>2</sup>.g<sup>-1</sup>, were obtained. Overall, soil amendment with biochars did not limit CLD environmental availability (environmental availability assay ISO/DIS 16751 Part B). When soil amended with ACs, a significant reduction of the environmental availability in both artificial and natural soils was observed. AC soil amendment resulted in a reduced CLD transfer by at least 65% (P<0.001) for all lignocellulosic matrices (excepted for coconut sample activated with steam, which displayed a 47% reduction). These features confirm that both pore structure and extent of porosity are of particular importance in the retention process of CLD in aged soil. Owing to its adsorptive properties, AC amendment of CLD contaminated soils appears as a promising approach to reduce the pollutant transfer to fauna and biota.

## Introduction

Chlordecone (CLD) is a chlorinated persistent organic pollutant (POP) particularly recalcitrant to biochemical degradation due to its very stable bishomocubane structure (composed by two methylene groups on a cubane skeleton, a cubic cage of carbon atoms as described by Marchand

1989) (Cabidoche et al. 2009; Matolcsy et al. 1988). Its broad application as an insecticide from 1972 to 1993, especially in the French West Indies to control the proliferation of a banana pest (i.e. *Cosmopolites sordidus*), resulted in high levels of CLD contamination in plantation soils (>1 mg/kg for CLD in numerous areas) (Cabidoche et al. 2009; Le Déaut and Procaccia 2009; Levillain et al. 2012). Despite CLD formal ban in 1993, soil contamination is expected to last several centuries due to its low water solubility and its high affinity for organic matter (with  $K_{OC}$  in the range of 2.5 - 20 m<sup>3</sup>.kg<sup>-1</sup>) (Cabidoche et al. 2009), if no remediation process is applied. In this context, CLD soil contamination constitutes a major transfer risk of CLD transfer to fauna and biota (Bouveret et al. 2013; Delannoy et al. 2018; Jurjanz et al. 2014, 2016, 2017).

A promising way to reduce soil-bound CLD transfer to biota and fauna is to sequester the pollutant within the soil matrix. Activated Carbons (ACs) have shown efficient long-term sequestration for halogenated compounds (Choi, et al. 2014; Hilber et Bucheli 2010; Jakob et al. 2012; Perelo 2010), little evidence is available regarding the effects of ACs on CLD environmental availability (as the soil pollutant fraction susceptible to be mobilized and accessible for biological uptake) in contaminated soils (Delannoy et al. 2018). Although successful AC amendment application trials for polychlorinated biphenyls' (PCBs) sequestration in soils were performed (Denyes et al. 2012; Denyes et al. 2013, 2016), so far, no attempt has been made concerning the immobilization of CLD in an Antillean soil.

Biochars, which can be defined as pyrolyzed biomass or organic waste materials under very low oxygen conditions (without any activation

process), may also be of interest in this perspective (Ahmad et al. 2014). Biochars are usually characterized by lower specific surface area and microporosity volume than ACs, which could significantly limit the sequestration and subsequent bioavailability reduction factor of organic contaminants (Ahmad et al. 2014). In view of CLD-contaminated potential land management, *in-situ* soil pollutant sequestration methods based on the use of ACs or biochars, could be a valuable strategy to limit the contaminant transfer from soil to biota and fauna. The proposed strategy could further involve locally produced biochars and ACs. Indeed, the latter represents an eco-friendly solution seeking to solve the serious environmental problem of contamination by chlorinated pesticides while improving the value of residues. The production of ACs using locally available waste such as coconut coir (coconut fiber) via chemical and physical activation methods offers the great opportunity for future economic utilization of this cheap and abundant agriculture biomass.

This study intends (i) to produce contrasted sequestering matrices in order (ii) to assess their respective efficiency to reduce CLD environmental availability in both an OECD artificial soil and an Antillean contaminated nitisol. These both steps aim to determine CLD environmental availability reduction efficiency of these media when added (i) to a standard soil material (ii) or to a soil representative of the Antillean CLD contamination context. For this purpose, normalized a standardized ISO *in vitro* test (environmental availability assay ISO/DIS 16751) was used (ISO 2015).

## Material and Methods

The work was set in two experimental steps. The first one consisted of the production of contrasted sequestering media (biochar and ACs) using different activation processes on two lignocellulosic precursors (raw biomass): oak wood (*Quercus ilex*) and coconut shell (*Cocos nucifera*). Then, their physico-chemical properties were characterized by N<sub>2</sub> sorption, scanning electron microscopy and thermogravimetric (TG) analysis. In the second step, the CLD environmental availability was assessed either in an OECD artificial soil or in an Antillean contaminated nitisol (2.1 µg CLD per g of soil Dry Matter), amended with 5wt% of biochar or 5 wt% of AC.

### 2.1. Production and characterization of experimental matrices

#### 2.1.1.AC and biochar synthesis from raw materials

Coconut shells of the dwarf variety (*Cocos nucifera*), were harvested in Saint-Claude, Guadeloupe (French West Indies), then peeled and crushed. Oak wood/bark was obtained from Nancy, France. All samples were firstly cut and then dried in an oven at 105°C for 48 h to remove the moisture content until reaching a content around 10% as recommended in the literature for

the pyrolysis of biomasses (Daltro et al. 2018). They were then grounded using the Retsch SM 100 to pass through a 4-mm screen and sieved with the Retsch AS 200 sieve shaker (amplitude 2.00, 60-s interval time, and 30-min total running time) into particle size ranging from 0.4 to 1 mm (Altenor et al. 2009), and subsequently stored in the same oven. In this work, three types of matrices were obtained from coconut and oak including biochars, chemically activated carbons, and physically activated carbons.

Biochars were produced by pyrolysing the precursors at 700 °C for 1 h in a tubular furnace (Carbolite Gero® CTF 12/75/700) under a nitrogen flow of 80 mL.min<sup>-1</sup>, and a heating rate of 10 C.min<sup>-1</sup> and maintained at the final temperature for 1 h.. The resultant samples will be later labeled oak biochar or coconut biochar.

Chemically activated carbons were obtained following a procedure published in previous work (Altenor et al. 2009). Briefly, an appropriated amount of precursor was soaked during 24 h in phosphoric acid (H<sub>3</sub>PO<sub>4</sub>, 85 wt%), resulting in a impregnation ratio of 1.5:1 (g H<sub>3</sub>PO<sub>4</sub>:g precursor). Samples were subsequently dried in an oven at 110 °C during 4 h, followed by their pyrolysis using the same conditions as the above-mentioned biochars. This resulted in samples herein referred to as Oak P1.5 and Coco P1.5 for Oak and Coconut respectively.

For physical activation, the oak and coconut biochars were heat treated under three gasses, either steam alone, CO<sub>2</sub> alone, or with CO<sub>2</sub>/H<sub>2</sub>O mixture, carried by a nitrogen flow (80 mL.min<sup>-1</sup>), until a burn-off of approximately 50% was achieved. The burn-off (%) or degree of carbon loss refers to the percentage of mass loss, which indicates efficient activation (Chang, Chang, et Tsai 2000; Gaspard et al. 2007). The burn-off refers to the weight difference between the original char and the activated carbon divided by the weight of original char with both weights on a dry basis: this is calculated according to the following equation:

$$\text{« burn - off »\%} = 1 - \frac{W_{\text{final}}}{W_{\text{initial}}} * 100 \quad (1)$$

with  $W_{\text{initial}}$ : weight of biochar

$W_{\text{final}}$ : mass of carbon after activation

Samples obtained from oak wood were labeled Oak CO<sub>2</sub>, Oak CO<sub>2</sub>/H<sub>2</sub>O, Oak H<sub>2</sub>O and from Coconut shell were labeled Coco CO<sub>2</sub>,

Coco CO<sub>2</sub>/H<sub>2</sub>O, Coco H<sub>2</sub>O, depending of their physical activation conditions.

### 2.1.2.ACs and biochars characterization

Generally, thermal treatment in an inert atmosphere of lignocel-lulosic matters consists on the progressive degradation of their embedded biopolymers leading to the reorganization of the carbon phase. As such, thermogravimetric analysis (TG) represents a convenient semiquantitative technique for anticipating the preparation of the ACs and biochars. Thermogravimetric analysis of the two precursors (coconut *shell* and oak wood) were carried out using a LABSYS Evo-Setaram instrument under a nitrogen flow of 80 mL.min<sup>-1</sup> and heating rate of 10 °C.min<sup>-1</sup>.

Microstructural characteristics of the samples were evaluated via scanning electron microscopy, operating at 20 KV (SEM, Hitachi S 2500).

The textural structure of the carbonaceous materials was analyzed N<sub>2</sub> sorption at 77K in a Micromeritics ASAP 2020 apparatus. Prior to analysis, samples were degassed 24 h under vacuum at 300 °C (heating rate of 8 °C.min<sup>-1</sup>). Specific surface area was determined according to the Brunauer, Emmett and Teller model (Brunauer, Emmett, et Teller 1938). Dubinin–Radushkevich (D-R) equation was used to evaluate the micropore volume whilst the mesopore volume was estimated using the Barrett–Joiner–Halenda (BJH) theory, calculated from the desorption branch (Barrett, Joyner, et Halenda 1951). Total pore volume was calculated by summing the micropores and mesopores volume. The mean pore diameter (Dp) was calculated according to the following equation  $4 \times V_T/S_{\text{BET}}$  (Durimel et al. 2013).

### 2.2. Artificial soils preparation

Artificial soils were prepared as described in Table 1 accordingly to the OECD guideline 207 (OECD 1984). Briefly, the common fraction present in each artificial soil contains sand and kaolin (78:22, m:m dry basis) (Sigma-Aldrich, St Louis, USA) as well as 10% (dry mass basis of whole soil) of sphagnum peat (Tourbe de Sphaigne, Florentaise, Truffaut, Paris). An additional portion constituted by biochar or AC was then added (5% dry mass basis of whole soil) as described in Table 1. All artificial soils were spiked with 100 µg of CLD (Kepone, Supelco, Sigma Aldrich, Saint-Louis) per g of dry matter.

Briefly, a CLD mix was spread over artificial soils using an aqueous mixture of CLD (20:80; methanol:water vol:vol). After spiking, solvent traces were evaporated under an extractor hood overnight. At last, ultrapure water was added to reach 18% of mass of the wet soil. Then, all artificial soils were aged during 80 days at room temperature ( $20 \pm 2^\circ\text{C}$ ) prior the following experimental parts.

### 2.3. Nitisol amendment

Contaminated nitisol soil (2.1  $\mu\text{g}$  CLD per g of soil Dry Matter) was sampled in French West Indies in the previous “croissant bananier” as described elsewhere (Jurjanz et al. 2014) and dried at room temperature until mass stabilization. Then, 5% of the condensed materials (dry mass basis) was added to 2g subsamples of this soil ( $n=3$ ). Six not amended subsamples were used as control. Finally, ultrapure water was added to reach 18% of mass of the wet soil. All soils were aged during 80 days at room temperature ( $20 \pm 2^\circ\text{C}$ ) prior the following experimental parts.

### 2.4. Environmental availability assays

Environmental availability assays were performed on each subsamples of artificial and natural soils. These tests were performed on the Bioavailability-Bioactivity (Bio-DA) platform of Université de Lorraine (Vandoeuvre-lès-Nancy, France). The protocol was adapted from the XP ISO/TS 16 751 Part B to fit a 2g soil-sample instead of 5g (ISO 2015). Thus,  $600 \pm 25$  mg of Tenax (60-80 mesh, Sigma-Aldrich, Saint-Louis) were added in an amber collection vial and 28 mL of ultrapure water were spread to preserve the soil:water ratio of the ISO standard. After a 20h-agitation period at 150

rpm in a horizontal shaker, the tubes were centrifuged (2000 g during 15min) and tenax was recovered using Glass Pasteur pipettes and washed with ultrapure water. As CLD is poorly soluble in petroleum ether the ISO protocol was adapted as follow: tenax was dried during 1h in a  $40 \pm 0.5^\circ\text{C}$  ventilated oven. Then, tenax was extracted three times with 10mL acetone using a 10-minutes ultrasonic bath. All extracts were combined and concentrated until 3mL prior GC-MS analyze (7 890A, Agilent Technologies, Santa Clara, USA). Briefly, the mass spectrometer was set at a resolution of 10 000, in electron ionization mode (70 eV electron energy) (5975C, Agilent Technologies, Santa Clara, USA). Single Ion Monitoring (SIM) was used to record the two most abundant signals. A DB5MS (25 m  $\times$  0.25 mm  $\times$  0.25  $\mu\text{m}$ ) capillary column from Agilent J&W (Agilent Technologies) was used in splitless mode. The GC temperature program for PCBs analysis was the following:  $120^\circ\text{C}$  (1 min),  $40^\circ\text{C min}^{-1}$  to  $220^\circ\text{C}$  (10 min) and  $2^\circ\text{C min}^{-1}$  to  $250^\circ\text{C}$  and  $10^\circ\text{C min}^{-1}$  to  $300^\circ\text{C}$  (5 min). Signals were integrated using Chemstation (Chemstation E.02.00, Agilent Technologies, Santa Clara, USA). Quantitation was realized using isotopic dilution by adding  $^{13}\text{C}$  CLD (Azur Isotope, 98% grade, Marseille, France) in each sample before analysis.

### 2.5. Statistical analysis

In order to assess the impact of biochars and ACs on CLD availability and bioavailability, an ANOVA was performed. The ANOVA procedure and the Tukey–Kramer post-hoc test of R version 3.2.3 (R Foundation for Statistical Computing, Vienna, Austria) running the package “car” (Fox and Sanford 2011). Differences were considered significant at  $P < 0.05$ .

## Results

### 3.1. ACs and biochar characterization

#### 3.1.1. Thermogravimetric behaviour of the precursors

Figure 1 shows the TG and the differential TG (DTG) curves obtained for both coconut and oak precursors. The TG curves highlight the mechanism of conversion of cellulose to carbon which comprises four successive steps. It starts with the desorption of moisture in the samples corresponding to a mass loss of 12.8wt% and 4.4wt% for the oak and coconut, respectively. This implies that a significant peak at around  $120^\circ\text{C}$  is

observed in both DTG curves. The subsequent mass loss can be assigned to the decomposition of hemicelluloses and glycosidic linkage of cellulose (25.6wt% at around  $290^\circ\text{C}$  for oak and 18.0 wt% at around  $275^\circ\text{C}$  for coconut). Likewise, the next region occurring at around  $350^\circ\text{C}$ , is usually attributed to the degradation of cellulose (weight loss up to 50%). Finally, above  $400^\circ\text{C}$ , depolymerization and rupture of C-O and C-C bonds leads to the aromatization and the formation of graphitic layers. Such behaviors are in good agreement with previous studies (Alvarez et Vázquez 2004), (Kim et al. 2006; Ncibi et al. 2014). In addition, it can be observed that thermal stability of the samples was reached from  $700^\circ\text{C}$ . As such, the temperature of pyrolysis was chosen

to be set at 700°C during the preparation of the biochars and activated carbon.

### 3.1.2. Microstructure analysis by scanning electron microscopy

Scanning electron microscopy (SEM) analysis was conducted to examine the microstructure of the samples. SEM images of the oak precursor shown in Figure 2 indicate a relatively homogeneous surface with the presence of spherical or elliptical macropores of various sizes (10 - 50 µm) homogeneously distributed in the cell wall of the precursor. The transverse section highlights the oak vessels oriented parallel to the axis of the wood. These observations are in agreement with the expected microstructure of hard woods which are characterized by the presence of these channels dedicated to the conduction of the sap. SEM micrographs of the resulting biochar suggest that high temperature pyrolysis led to a slight alteration of the sample morphology (some macropores are narrowed and the surface appears slightly damaged). However, no additional porosity could be observed at this stage, as pyrolysis is simply associated with loss of mass followed by clogged pore formation.

The coconut precursor (coir), for its part, exhibits a fibrous microstructure associated with a relatively rough surface (Figure 3). This cell wall is generally made of cellulose embedded in a non-crystalline matrix of lignin. The diameter of these fibers varies from 10 to 100 µm. After pyrolysis at 700 ° C, observations are similar to those of oak, namely no significant change in the porosity of the samples was detected.

### 3.1.3. Textural properties of ACs and biochars by N<sub>2</sub> sorption

Liquid nitrogen adsorption/desorption at 77 K was measured for ACs and biochars. As shown in Figs. 4 and 5, the volume of N<sub>2</sub> adsorbed increases suddenly at low relative pressure, which clearly indicates the existence of micropores until a P/P<sub>0</sub> value of 1. The International Union of Pure and Applied Chemistry (IUPAC) classification of adsorption isotherms consists of two adsorption and desorption pathways. Samples Oak H<sub>2</sub>O and Oak H<sub>2</sub>O/CO<sub>2</sub>, Coco CO<sub>2</sub> and Coco P1.5 shows a classical Type IV isotherm shape, associated with capillary condensation that occurs in mesopores. This suggests the coexistence of high microporosity and the presence of mesopores. The values of measured specific surface area are presented in the Table 2. Coco biochar exhibits the lower BET surface area of

299 m<sup>2</sup>.g<sup>-1</sup>, and the highest one is obtained for the physically activated samples, and especially Coco CO<sub>2</sub>, with a BET surface area of 998 m<sup>2</sup>.g<sup>-1</sup>.

Samples Oak H<sub>2</sub>O, Oak CO<sub>2</sub>/H<sub>2</sub>O, CocoP1.5, Coco H<sub>2</sub>O and Coco CO<sub>2</sub> sample show mesoporous-type porosity. The adsorption-desorption isotherms overlap completely at very low relative pressures and then become rapidly distinct and two different hysteresis loops appear at high relative pressures (P/P<sub>0</sub> > 0.45). Similarly Oak biochar presents the lower surface area among the Oak carbon samples, with a value of 424 m<sup>2</sup>.g<sup>-1</sup>. The BET surface area of the carbon samples obtained by physical activation is around 1000 m<sup>2</sup>.g<sup>-1</sup>, and Oak P1.5 has a much higher value of surface area of 1506 m<sup>2</sup>.g<sup>-1</sup>.

### 3.2. CLD environmental availability in artificial soils

The first set of assays involved 13 samples of OECD soils amended by either one of ACs or biochars in order to apprehend the potentialities of sequestration offered by condensed media on CLD availability. The results are presented in Figure 6. CLD environmental availability of the OECD standard soil was 75.7±1.8% indicating that the main part of soil CLD was available. No significant reduction of CLD availability (P>0.05) with both biochars in comparison to non-amended OECD standard soil was obtained (oak biochar: 65.2±5.6%; coconut biochar: 67.7±6.8%). A significant reduction (by a factor 2) of CLD-environmental availability was seen when the OECD soil was amended by activated matrices with the exception of Coco H<sub>2</sub>O sample.

### 3.3. CLD environmental availability in Antillean nitisol

The second set of experiments involved one Antillean nitisol sample amended by either one of ACs or one of biochars. The results are presented in Figure 7. CLD environmental availability of the nitisol soil was set to 100%. No reduction of CLD availability from amended soils with biochar in comparison to nitisol soil was observed (oak biochar: 105±11%; coco biochar: 103±8%). In contrast, CLD environmental availability for 6 out of 7 activated carbons was in the range of 20 to 40% showing a major reduction compared to the control (P<0.05). Steam-activated coconut exhibited higher CLD-environmental availability than the 6 other ACs (P<0.05). ORBO activated carbon appeared to be the most effective sorbent reducing CLD-environmental availability to 16±11%.

## Discussion

### 4.1. AC vs biochar characteristics and effectiveness to reduce environmental availability

As thoroughly described in the literature, ACs displayed higher porosity than biochars (Table 2) (Chai et al. 2012; Delannoy et al. 2018). Indeed, the activation process is known (i) to eliminate incomplete combustion materials and (ii) to increase the porosity. As a result, no reduction of environmental availability was obtained when soils were amended with biochars, whereas a significant reduction was obtained with activated carbons (Figs. 6 and 7). This result is in accordance with previous data obtained within OECD soil and for different organic pollutants (Delannoy et al. 2014a; Delannoy et al. 2014b) and CLD (Yehya et al. 2017). It indicates that the pyrolysis process on its own is not sufficient to reach an adequate basal porosity quality and a total surface area which would be needed to bound CLD and consequently to reduce its environmental availability.

Considering the results obtained after amendment of OECD soil (Fig. 8) and nitisol (Fig. 9), a similar pattern of CLD environmental availability reduction was observed for the different studied ACs. Indeed, except for the coconut activated by steam, reduction of environmental availability was in the same range for the OECD soils amended with the different ACs (reduction factor between 13 and 37%). The same trends were observed with AC-amended nitisol. The reduced distinctive sequestration efficiency of the steam-activated coconut could be explained by the low surface area in pore ( $706 \text{ m}^2\cdot\text{g}^{-1}$ ) compared to the majority of the activated carbons prepared exhibiting a specific surface values higher than  $900 \text{ m}^2\cdot\text{g}^{-1}$ . In contrast coco P1.5 prepared by phosphoric activation of coconut exhibiting a specific surface area of  $642 \text{ m}^2\cdot\text{g}^{-1}$  was able to reduce CLD environmental availability to a value of 19%. These results may be linked to the higher amount of mesoporous volume than the other ACs. Overall it appears that the textural characteristics like specific BET surface area, total pore volume, and micro- and mesopore volume and mean pore diameter are positively correlated to the CLD environmental availability reduction (Figs. 9 and 10). Considering the total pore volume, a high reduction level of environmental availability was reached for values above  $0.5 \text{ cm}^3\cdot\text{g}^{-1}$  for both OECD soil and nitisol. Textural properties like micro- and mesopore volumes

appear to play a role in this reduction. Indeed, these parameters were much lower for biochars than for ACs (Table 1, Figs. 2, 3, and 4b). As an illustration, the micropore volume appears to be significantly and negatively correlated to the CLD environmental availability (Fig. 8c). This trend was also previously noticed in another set of biochars and ACs (Delannoy et al. 2018).

### 4.2. Comparison of strategies applied to limit CLD transfer to flora and fauna

The in vitro “environmental availability” studies described and discussed above give interesting insight and perspective in order to limit the CLD transfer from soil to biota and fauna. Indeed, in the French West Indies, no sustainable solution has been found to tackle CLD transfer to flora or fauna. Such transfers pose a major threat for local production of vegetables and food producing animals.

It has to be noted that different research programs are still in place to investigate CLD sequestration by the use of organic amendments like compost (decayed organic material from plants) (Woignier et al. 2016). Regarding the use of compost, one major problem is related to its durability. Indeed, composts are mainly labile carbon sources which are degraded after a few decades (Schmidt et al. 2011), in contrast to ACs that have a time residence of several hundred years (Wang et al. 2016).

Some other studies investigated the in situ reduction of CLD using zero-valent iron compounds for CLD degradation (Mouvet et al. 2011). This approach consists in the addition of large amount of zero-valent iron in anoxic condition in order to modify CLD in less halogenated compounds. Such strategy was efficient to decrease CLD concentration in soil (Mouvet et al. 2011). However, no long-term studies assessed the toxicological and environmental impact of such extensive treatment on soil property and biota.

Several studies have proven that AC and biochar application to soils was able to significantly limit organic pollutants transfer to biota (Ghosh et al. 2011). As an example, reduction levels up to 94% of pollutant transfer were reported on earthworms when using ACs (Denyes et al. 2012, 2013; Langlois et al. 2011; Paul and Ghosh 2011; Wang

et al. 2012). The results of the present study confirm the adequacy of this sequestration strategy for CLD-contaminated soils (Delannoy et al. 2018). In the present study, the minimum environmental availability observed was of about 20% representing 80% reduction of CLD availability after AC amendment. Such reduction transfer implies a significant improvement in terms of CLD contamination of biota. These promising results could even be improved by the optimization of (i) the duration of the maturation and (ii) the rate of application of ACs or biochars.

The effectiveness of carbon amendments in the form of biochars has also been reported in several studies for PCBs, PAHs, and several pesticides (Chai et al. 2012; Denyes et al. 2013, 2016; Gu et al. 2016; Jakob et al. 2012; Kołtowski et al. 2016, 2017; Wang et al. 2012). In these studies, authors reported positive sequestration effects after biochar amendments. In the present study, such reduction was not observed when the soils were amended by biochars. It could be suggested that the bishomocubane structure or chemical characteristic of the CLD impeded the sequestration for such matrices.

Another critical point to consider toward in further field application is to ensure the innocuity of soil-amendment by biochars or ACs. Literature

assessed thoroughly the environmental toxicological aspect of AC and biochar amendment. Such amendment of soil is known to increase soil water holding capacity as well as microbial activities (Lehmann et al. 2011; Tammeorg et al. 2014). These elements are of benefit for agricultural practices and improve soil water retention (Karhu et al. 2011), as well as for specific fauna like earthworms (Zhang et al., 2019; Liesch et al. 2010). If no comprehensive ecological review is available to apprehend globally the impact of such strategy on ecosystems, the rate of application was proven to be correlated to the toxicity for the soil fauna (Zhang et al., 2019; Gomez-Eyles et al., 2011). Thus, levels equal or above to 10% biochar or ACs show adverse effects on earthworms (Zhang et al., 2019) as well as in plants (Lehmann et al. 2011). Another noteworthy observation is related to the precursor of the ACs or biochars: as an illustration, plant-derived biochars or ACs present lower toxicity than other precursors like manure, hence droppings by immobilization heavy metals and organic pollutants by induction of microbial pollutant degraders (Liu et al. 2018). Although reported toxicity of such strategy only appears at high application rates (higher than 10%), this suggests a wide range of safe application rates to avoid toxicity while ensuring a reduction of POPs transfer.


## **Conclusion**

---

Soil amendment with 5% of ACs derived from lignocellulosic sources resulted in major reductions of CLD environmental availability (up to 80%). Biochars from the same lignocellulosic precursors were not effective to reduce environmental availability of CLD as a minimal porosity was obtained. According to these results, the activation process appears to

strategy would consist in soil amendment by ACs like coconut or oak. In order to valorize local green wastes, the production of coconut-based ACs and its amendment to Antillean CLD-contaminated soils will contribute to sustainably limit CLD transfer to ecosystems. For such purpose, the collection, the storage, and the AC production processes have to be locally organized.

be crucial to sequester CLD in soils. In terms of practical application in situ, the only valuable

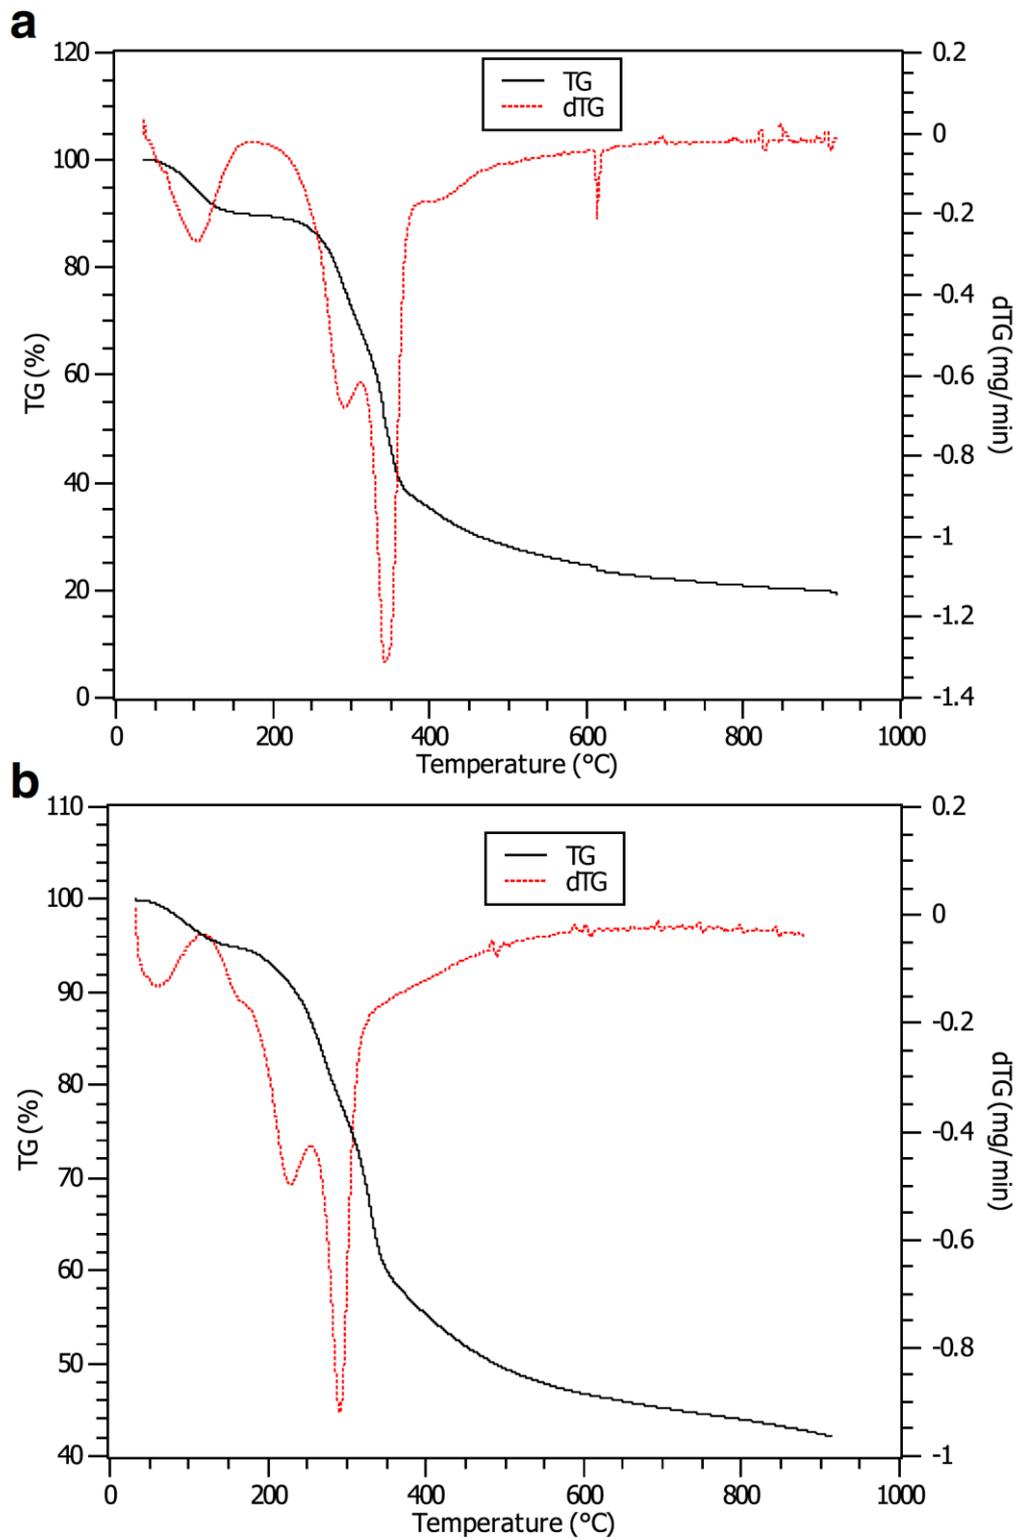

**Figure 1** : TGA of (a) oak wood and (b) Coconut nucifera.

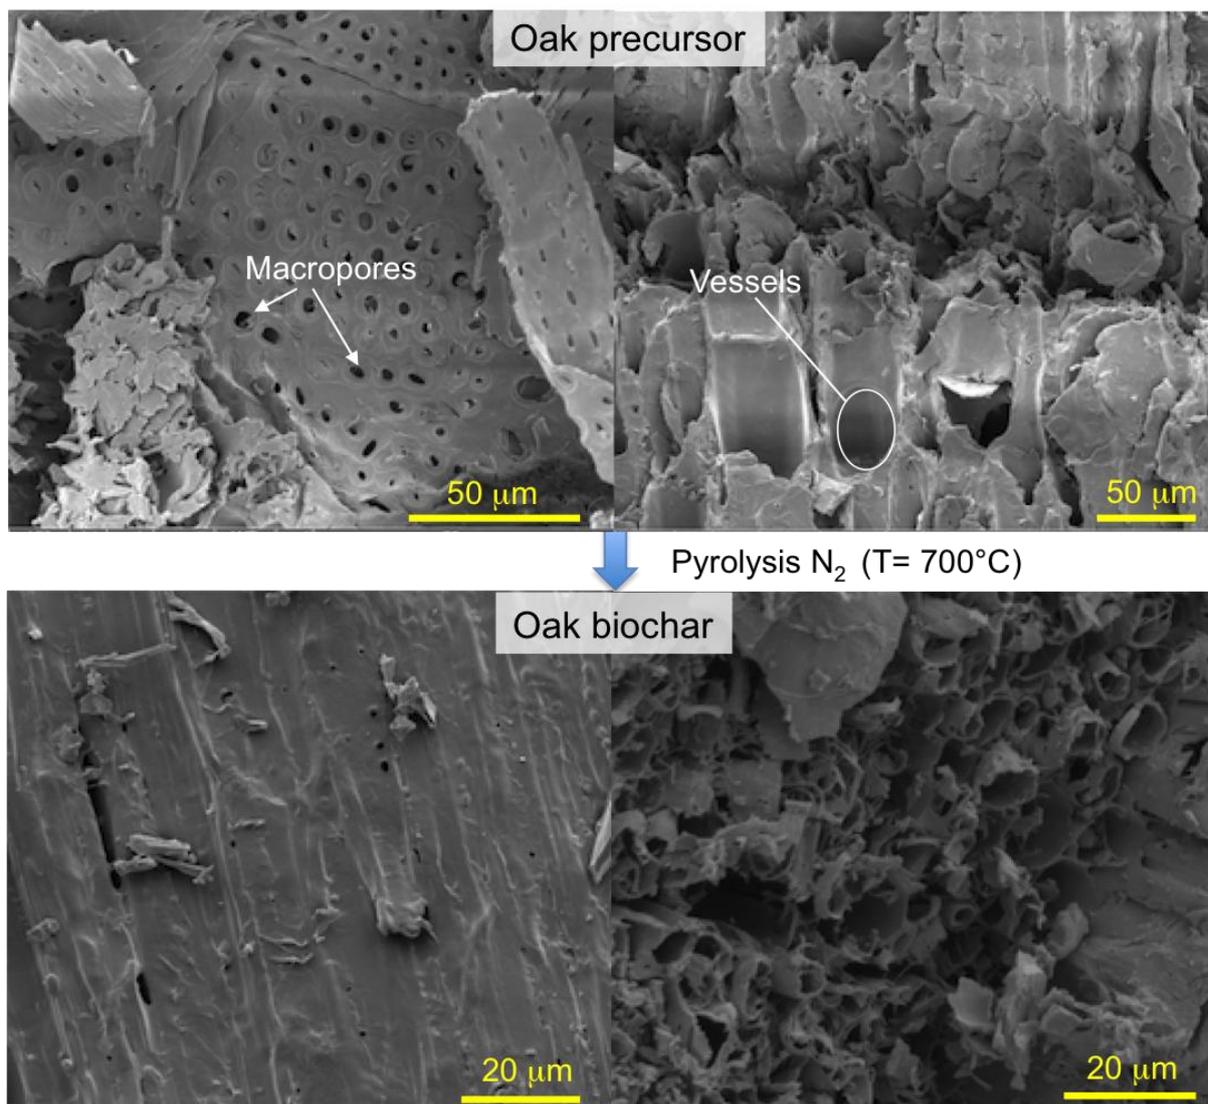


Figure 2 : SEM images of oak wood before and after pyrolysis.

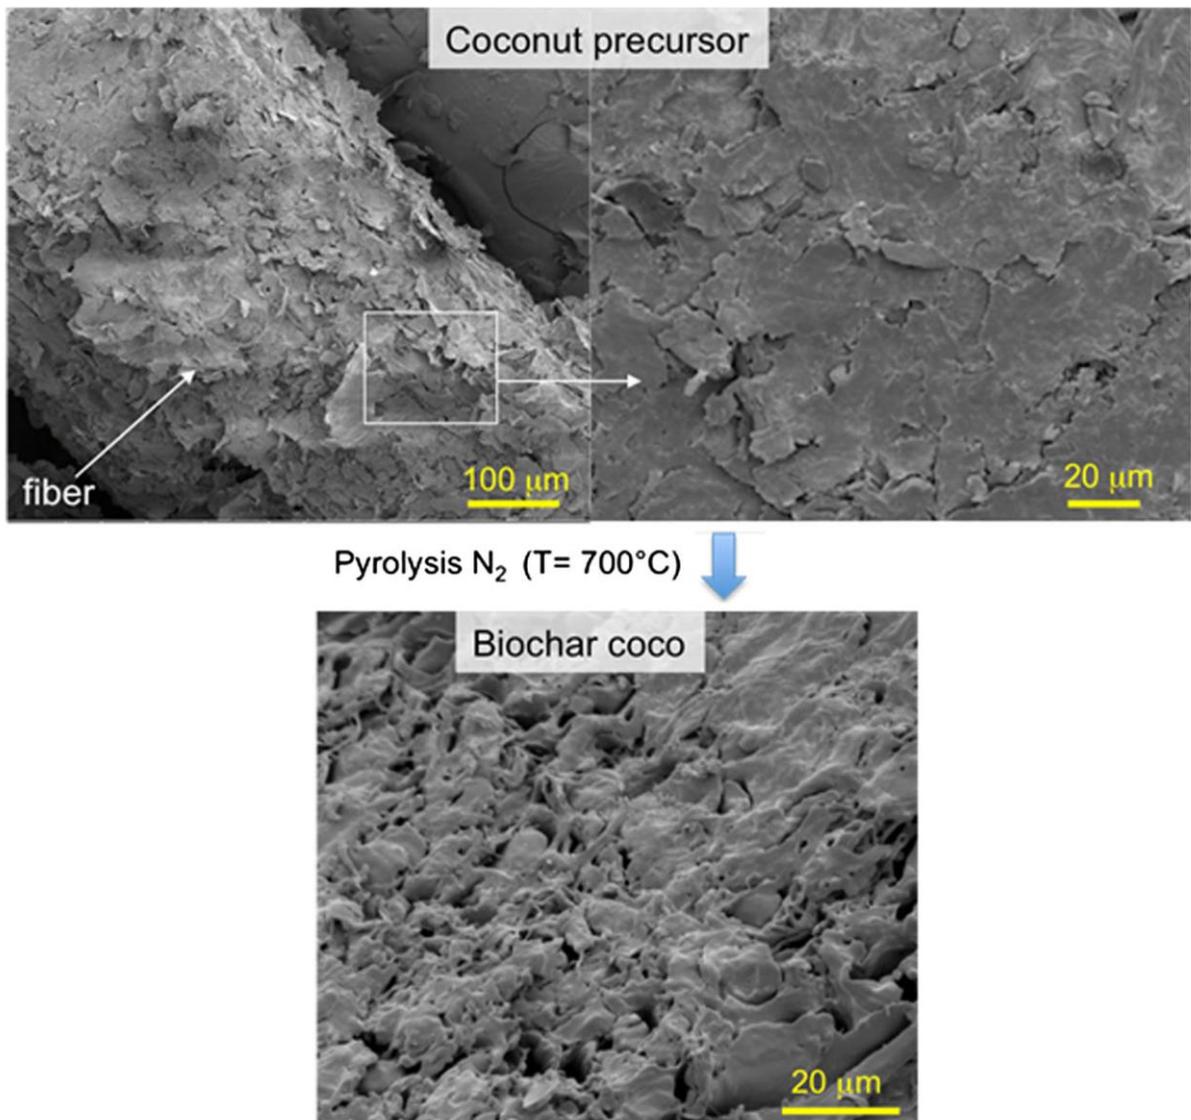


Figure 3 : SEM images of coconut shell precursor before and after pyrolysis.

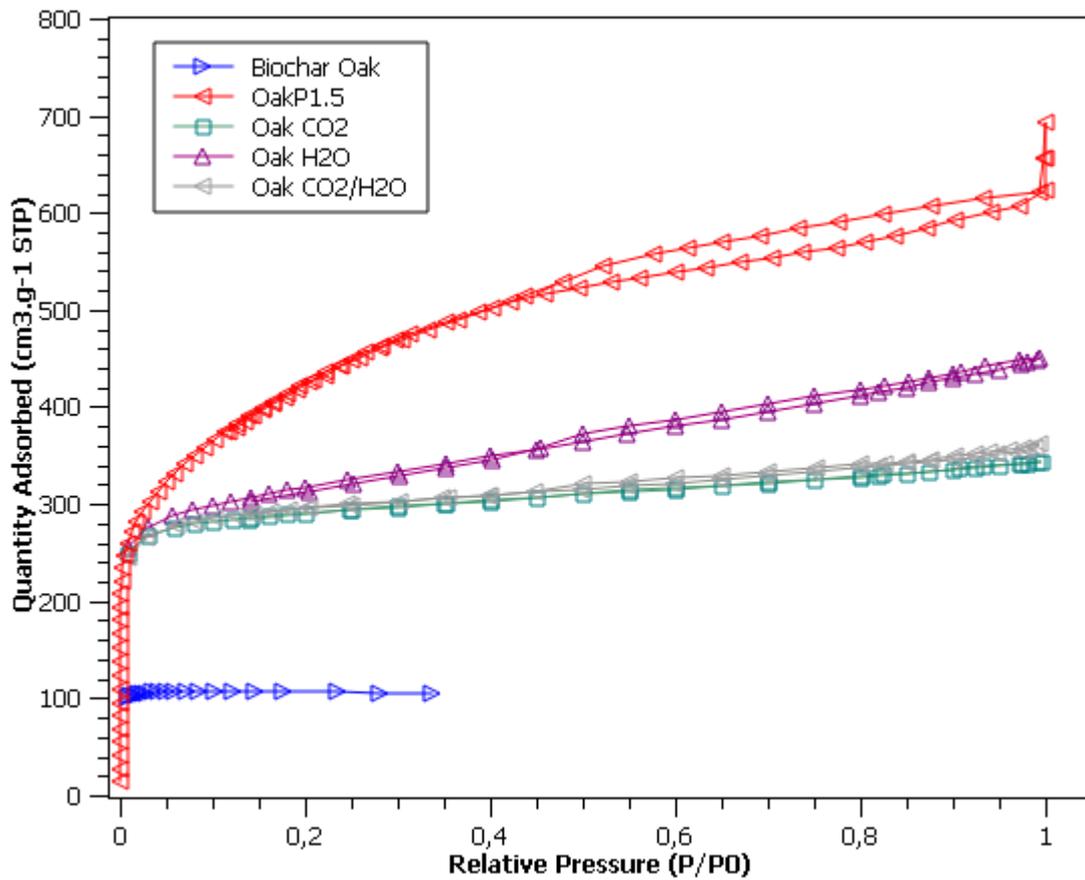


Figure 4: Adsorption isotherm of nitrogen at 77 K by AC of *Quercus ilex* pyrolyzed at 700 °C during 1 h.



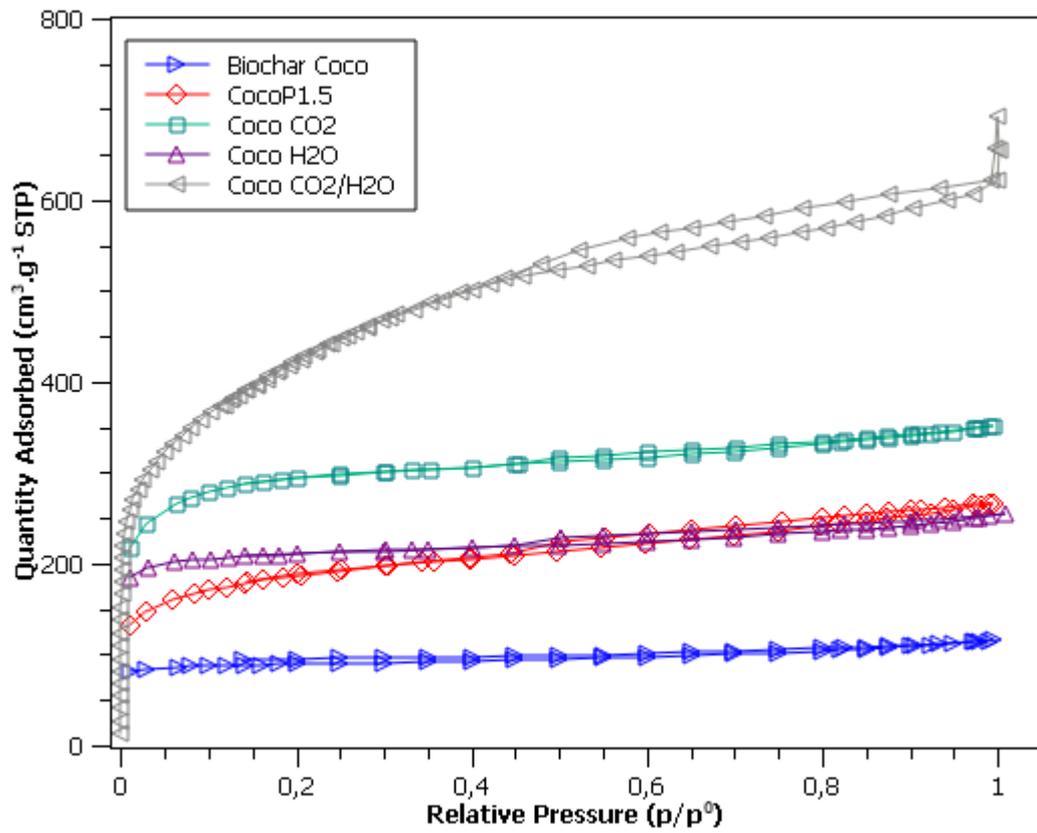


Figure 5: Adsorption isotherm of nitrogen at 77 K by AC of Coconut *nucifera* pyrolyzed at 700°C during 1 h.

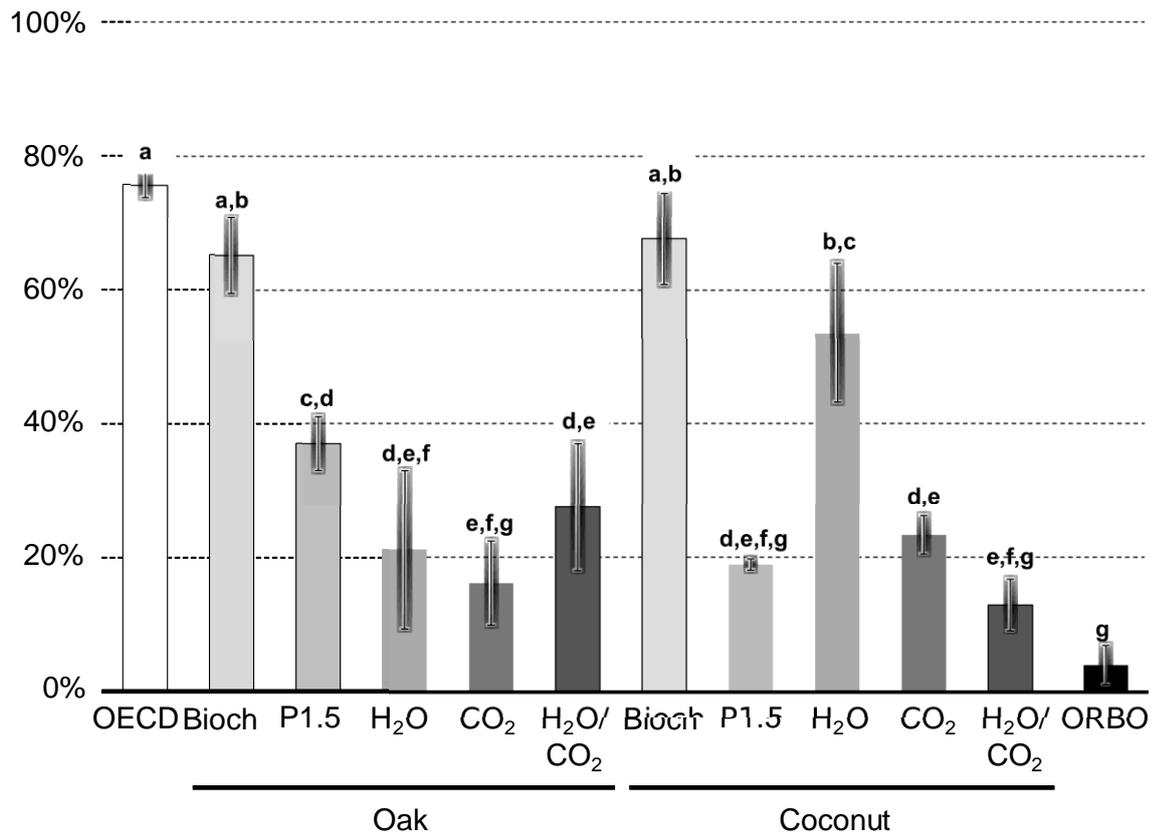


**Figure 6 : CLD availability in OECD soils.**

CLD availability is expressed in %. Values correspond to the mean  $\pm$  SD (n=3 or 6 (OECD, ORBO)). Mean values with different superscript letters (a, b, c, d, e, f, g) are statistically different (P<0.05). Statistical analysis was performed using the one-way ANOVA procedure of R software and Tukey post-hoc test.

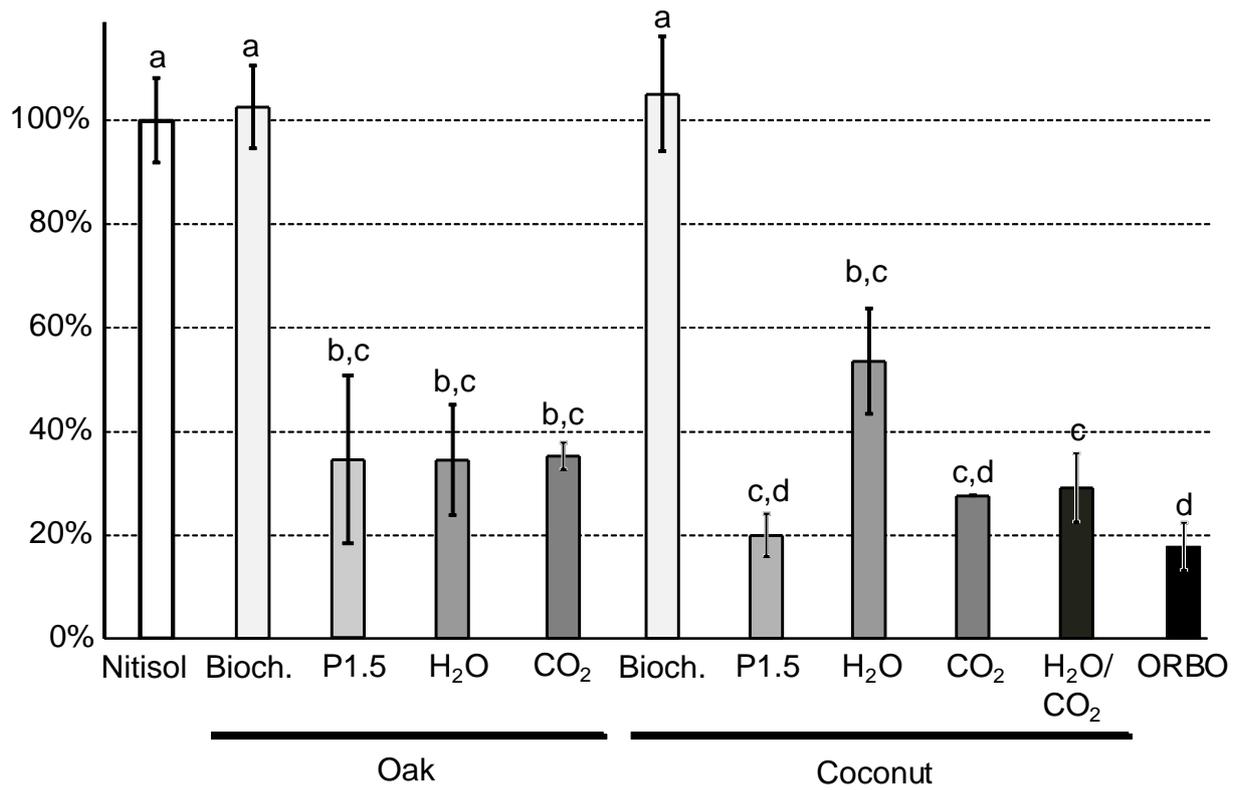


**Figure 7: CLD availability in nitisol after amendment.**

CLD availability is expressed in %. Values correspond to the mean  $\pm$  SD (n=3 excepted for OECD and OFRBO where n= 6 (OECD, DARCO, ORBO)). Mean values with different superscript letters (a, b, c, d) are statistically different (P<0.05). Statistical analysis was performed using the one-way ANOVA procedure of R software and Tukey post-hoc test.

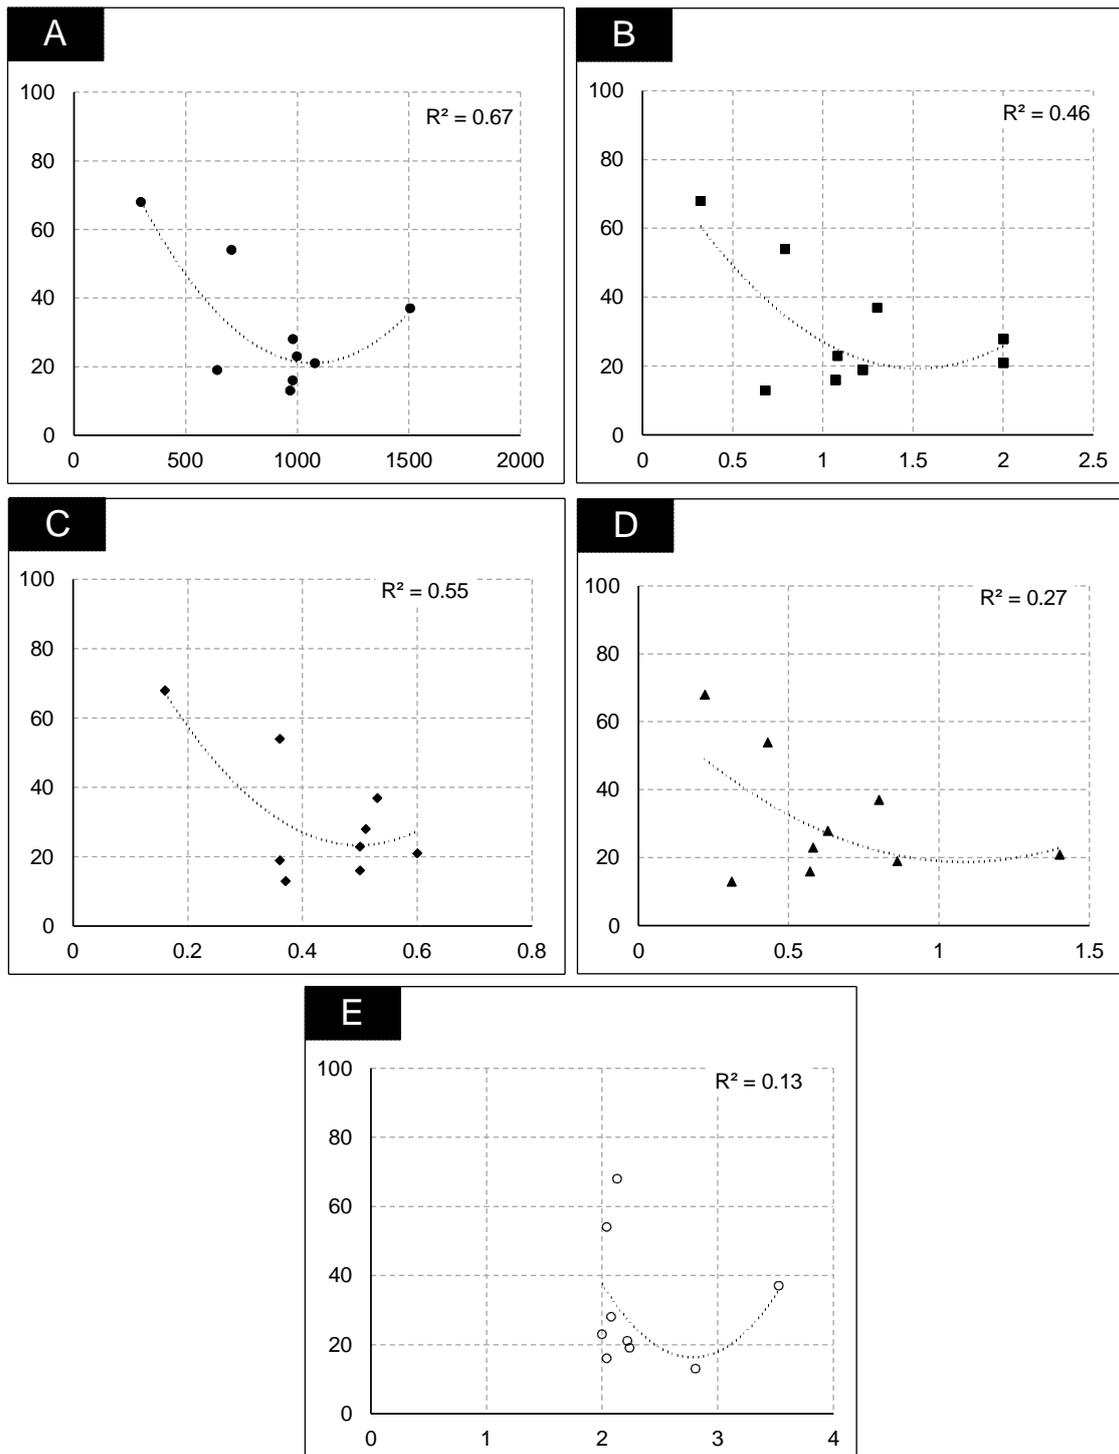

**Figure 8. Textural characteristics and relation with CLD environmental availability reduction for artificial soils**

x-axis corresponds respectively (A) to the BET surface area ( $\text{m}^2 \cdot \text{g}^{-1}$ ), (B) to the total pore volume ( $\text{cm}^3 \cdot \text{g}^{-1}$ ), (C) to the micropore volume ( $\text{cm}^3 \cdot \text{g}^{-1}$ ), (D) to the mesopore volume ( $\text{cm}^3 \cdot \text{g}^{-1}$ ) (E) to Mean pore with  $D_p$  (nm). y-axis corresponds to the mean of CLD environmental availability reduction (% of reduction compared to control) and error bar 95<sup>th</sup> confidence interval (n=4).

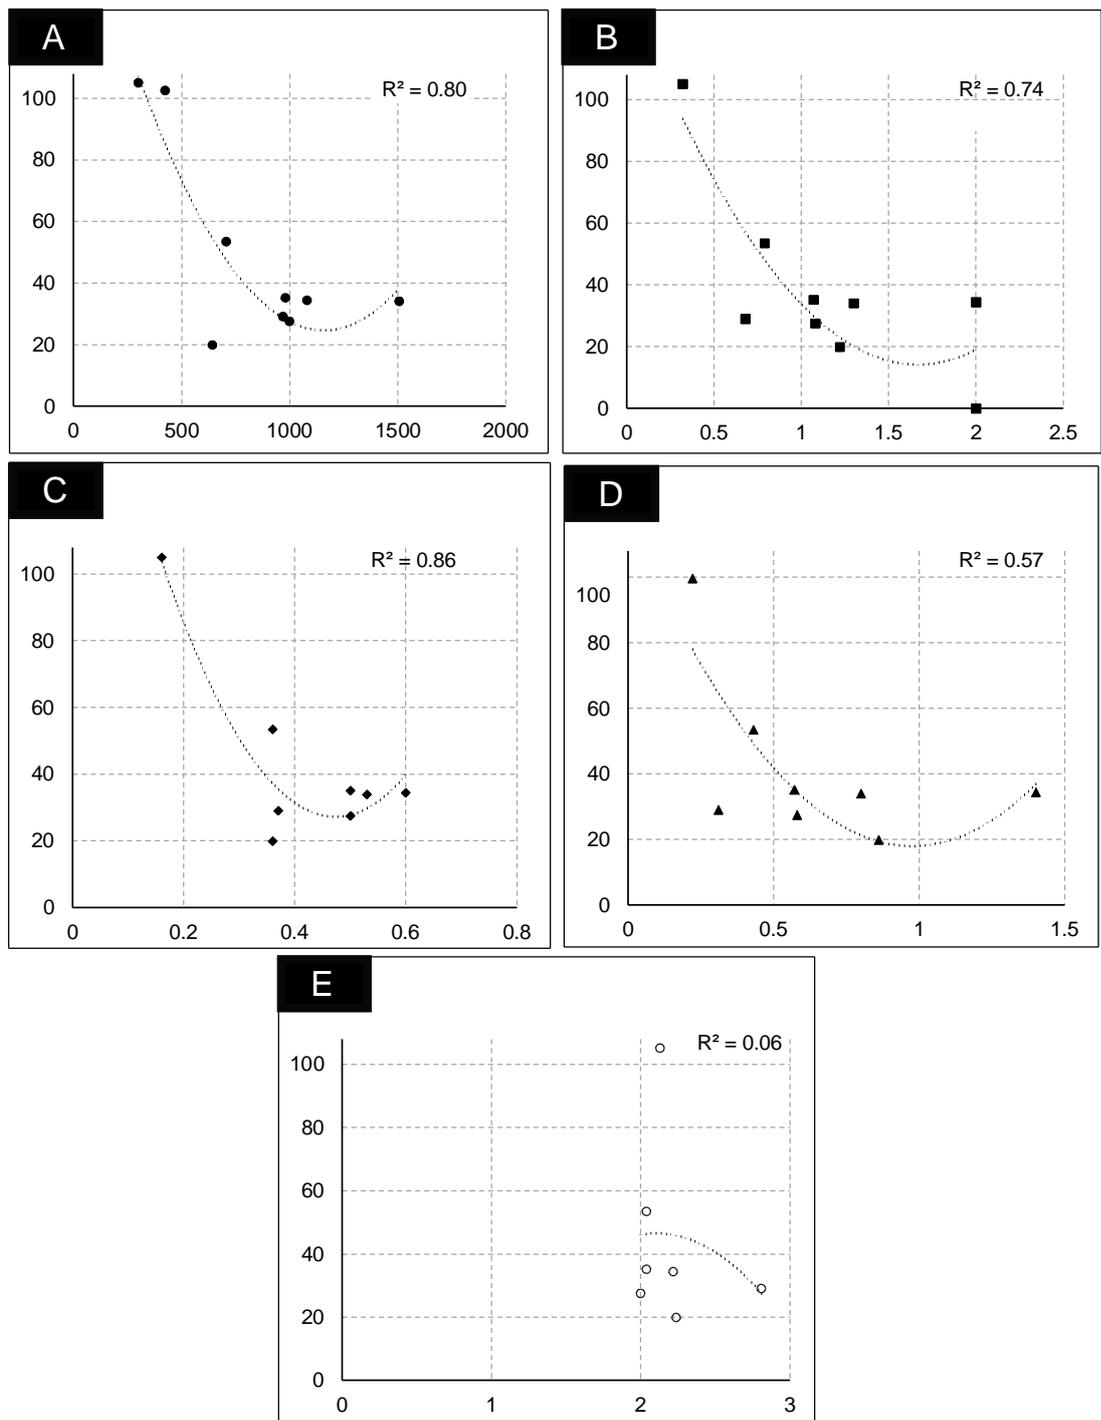

**Figure 9. Textural characteristics and relation with CLD environmental availability reduction for natural soils**

x-axis corresponds respectively (A) to the BET surface area ( $m^2 \cdot g^{-1}$ ), (B) to the total pore volume ( $cm^3 \cdot g^{-1}$ ) (C) to the micropore volume ( $cm^3 \cdot g^{-1}$ ), (D) to the mesopore volume ( $cm^3 \cdot g^{-1}$ ) (E) to Mean pore with  $D_p$  (nm). y-axis corresponds to the mean of CLD environmental availability (n=4).

**Table 1 : Composition of the different artificial soils and treatment of the experiment**

Biochar column presents name and weight percentage of each biochar (source and pyrolyse temperature). Percentages are DM basis of artificial soil. Kepone concentration of each soil is  $5 \mu\text{g}\cdot\text{g}^{-1}$  of soil DM.

	Sand	Kaolin	<i>Sphagnum</i> peat	Activated carbon	Biochar
OECD standard soil	70.0%	20.0%	10%	-	
OECD with oak biochar	66.5%	19.0%	9.5%		5% (oak biochar)
OECD with Oak P1.5	66.5%	19.0%	9.5%	5% (Oak P1.5)	
OECD with Oak CO2	66.5%	19.0%	9.5%	5% (Oak CO2)	
OECD with Oak H2O	66.5%	19.0%	9.5%	5%( Oak H2O)	
OECD with coconut biochar	66.5%	19.0%	9.5%		5% (coconut biochar)
OECD with coconut P1.5	66.5%	19.0%	9.5%	5% (Coconut P1.5)	
OECD with coconut CO2	66.5%	19.0%	9.5%	5% (Coconut CO2)	
OECD with coconut H <sub>2</sub> O	66.5%	19.0%	9.5%	5%( Coconut H2O)	

**Table 2: Textural parameters of the lignocellulosic ACs and biochars.**

Sample	Burn-off (%)	BET Surface area (m <sup>2</sup> .g <sup>-1</sup> )	V <sub>Micropore</sub> (D-R) (cm <sup>3</sup> .g <sup>-1</sup> )	V <sub>Mesopore</sub> (BJH) (cm <sup>3</sup> .g <sup>-1</sup> )	Total volume in pore (cm <sup>3</sup> .g <sup>-1</sup> )	Average pore width Dp (nm)
Biochar Oak	76	424.63	-	-		
OakP1.5	74	1506.19	0.53 (39.85%)	0.80 (60.15%)	1.33	3.53
Oak CO <sub>2</sub>	54	979.62	0.50 (46.73%)	0.57 (53.27%)	1.07	2.04
Oak H <sub>2</sub> O	53	1079.78	0.60 (30%)	1.40 (70%)	2.00	2.22
Oak CO <sub>2</sub> / H <sub>2</sub> O	51	980.70	0.51 (44.74%)	0.63 (55.26%)	1.14	2.08
Biochar Coco	64	299.92	0.16 (42.10%)	0.22 (57.90%)	0.38	2.13
CocoP1.5	77	642.49	0.36 (29.51%)	0.86 (70.49%)	1.22	2.24
Coco CO <sub>2</sub>	54	998.58	0.50 (46.30%)	0.58 (53.70%)	1.08	2.00
Coco H <sub>2</sub> O	52	706.38	0.36 (45.57%)	0.43 (54.43%)	0.79	2.04
Coco CO <sub>2</sub> / H <sub>2</sub> O	51	968.44	0.37 (54.41%)	0.31 (45.59%)	0.68	2.81

## References

- Ahmad M, Rajapaksha AU, Lim JE, Zhang M, Bolan N, Mohan D, Vithanage M, Lee SS, Ok YS (2014) Biochar as a sorbent for contaminant management in soil and water: a review. *Chemosphere* 99: 19–33
- Altenor S, Carene B, Emmanuel E, Lambert J, Ehrhardt JJ, Gaspard S (2009) Adsorption studies of methylene blue and phenol onto vetiver roots activated carbon prepared by chemical activation. *J Hazard Mater* 165(1–3):1029–1039
- Alvarez VA, Vázquez A (2004) Thermal degradation of cellulose derivatives/starch blends and sisal fibre biocomposites. *Polym Degrad Stab* 84(1):13–21
- Barrett EP, Joyner LG, Halenda PP (1951) The determination of pore volume and area distributions in porous substances. I. Computations from nitrogen isotherms. *J Am Chem Soc* 73(1): 373–380
- Bouvet C, Rychen G, Lerch S, Jondreville C, Feidt C (2013) Relative bioavailability of tropical volcanic soil-bound chlordecone in piglets. *J Agric Food Chem* 61(38):9269–9274
- Brunauer S, Emmett PH, Teller E (1938) Adsorption of gases in multi-molecular layers. *J Am Chem Soc* 60(2):309–319
- Cabidoche YM, Achard R, Cattain P, Clermont-Dauphin C, Massat F, Sansoulet J (2009) Long-term pollution by chlordecone of tropical volcanic soils in the French West Indies: a simple leaching model accounts for current residue. *Environ Pollut* 157(5):1697–1705
- Chai Y, Currie RJ, Davis JW, Wilken M, Martin GD, Fishman VN, Ghosh U (2012) Effectiveness of activated carbon and biochar in reducing the availability of polychlorinated dibenzo-p-dioxins/dibenzofurans in soils. *Environ Sci Technol* 46(2):1035–1043
- Chang C-F, Chang C-Y, Tsai W-T (2000) Effects of burn-off and activation temperature on preparation of activated carbon from corn cob agrowaste by CO<sub>2</sub> and steam. *J Colloid Interface Sci* 232(1):45–49
- Choi Y, Cho Y-M, Luthy RG (2014) In situ sequestration of hydrophobic organic contaminants in sediments under stagnant contact with activated carbon. 1. Column studies. *Environ Sci Technol* 48(3):1835–1842
- Daltro M, Kleveston J, Oliveira S, Tomasini D, Pereira G, Schena T, Onorevoli B, Rodrigues T (2018) Production of activated biochar from coconut fiber for the removal of organic compounds from phenolic. *J Environ Chem Eng* 6(2):2743–2750
- Delannoy M, Rychen G, Fournier A, Jondreville C, Feidt C (2014a) Effects of condensed organic matter on PCBs bioavailability in juvenile swine, an animal model for young children. *Chemosphere* 104:105–112
- Delannoy M, Schwarz J, Fournier A, Rychen G, Feidt C (2014b) Effects of Standard Humic Materials on Relative Bioavailability of NDL-PCBs in Juvenile Swine. *PLoS ONE* 9(12)
- Delannoy M, Yehya S, Techer D, Razafitianamaharavo A, Richard A, Caria G, Baroudi M, Montargès-Pelletier E, Rychen G, Feidt C (2018) Amendment of soil by biochars and activated carbons to reduce chlordecone bioavailability in piglets. *Chemosphere* 210: 486–494
- Denyes MJ, Langlois VS, Rutter A, Zeeb BA (2012) The use of biochar to reduce soil PCB bioavailability to *Cucurbita pepo* and *Eisenia fetida*. *Sci Total Environ* 437:76–82
- Denyes MJ, Rutter A, Zeeb BA (2013) In situ application of activated carbon and biochar to PCB-contaminated soil and the effects of mixing regime. *Environ Pollut* 182:201–208
- Denyes MJ, Rutter A, Zeeb BA (2016) Bioavailability assessments following biochar and activated carbon amendment in DDT-contaminated soil. *Chemosphere* 144:1428–1434
- Durimel A, Altenor S, Miranda-Quintana R, Couespel Du Mesnil P, Jauregui-Haza U, Gadiou R, Gaspard S (2013) PH dependence of chlordecone adsorption on activated carbons and role of adsorbent physico-chemical properties. *Chem Eng J* 229:239–249
- Fox J, Sanford W (2011) An {R} companion to applied regression, 2nd edn. Sage, Thousand Oaks CA
- Gaspard S, Altenor S, Dawson EA, Barnes PA, Ouensanga A (2007) Activated carbon from vetiver roots: gas and liquid adsorption studies. *J Hazard Mater* 144(1–2):73–81
- Ghosh U, Luthy RG, Cornelissen G, Werner D, Menzie CA (2011) In situ sorbent amendments: a new direction in contaminated sediment management. *Environ Sci Technol* 45(4):1163–1168
- Gibert O, Benoît L, Fernández M, Bernat X, Paraira M, Pons M (2013) Fractionation and Removal of Dissolved Organic Carbon in a Full-Scale Granular Activated Carbon Filter Used for Drinking Water Production. *Water Research* 47(8):2821–29. <https://doi.org/10.1016/j.watres.2013.02.028>
- Gomez-Eyles JL, Sizmur T, Collins CD, Hodson ME (2011) Effects of biochar and the earthworm *Eisenia fetida* on the bioavailability of polycyclic aromatic hydrocarbons and potentially toxic elements. *Environmental Pollution* 159(2):616–622
- Gu J, Zhou W, Jiang B, Wang L, Ma Y, Guo H, Schulin R, Ji R, Evangelou MWH (2016) Effects of biochar on the transformation and earthworm bioaccumulation of organic pollutants in soil. *Chemosphere* 145:431–437
- Hilber I, Bucheli TD (2010) Activated carbon amendment to remediate contaminated sediments and soils: a review. *Global Nest Journal* 12(3):305–317
- ISO (2015) Environmental availability of non-polar organic compounds – Determination of the potential bioavailable fraction and the non-bioavailable fraction using a strong adsorbent or complexing agent. Draft International Standard. ISO/DIS 16751:2015. International Organization for Standardization
- Jakob L, Hartnik T, Henriksen T, Elmquist M, Brørdli RC, Hale SE, Cornelissen G (2012) PAH-sequestration capacity of granular and powder activated carbon amendments in soil, and their effects on earthworms and plants. *Chemosphere* 88(6):699–705
- Jurjanz S, Jondreville C, Mahieu M, Fournier A, Archimède H, Rychen G, Feidt C (2014) Relative bioavailability of soil-bound chlordecone in growing lambs. *Environ Geochem Health* 36(5):911–917
- Jurjanz S, Jondreville C, Fournier A, Lerch S, Rychen G, Feidt C (2016) Transfer of chlordecone from the environment to animal-derived products. In: *Crisis Management of Chronic Pollution, Urbanization, Industrialization, and the Environment*. CRC Press, Boca Raton, pp 143–160
- Jurjanz S, Collas C, Lastel ML, Godard X, Archimède H, Rychen G, Mahieu M, Feidt C (2017) Evaluation of soil intake by growing creole young bulls in common grazing systems in humid tropical conditions. *Animal* 11(8):1363–1371
- Karhu K, Mattila T, Bergström I, Regina K (2011) Agriculture, ecosystems and environment biochar addition to agricultural soil increased CH<sub>4</sub> uptake and water holding capacity – results from a short-term pilot field study. *Agric Ecosyst Environ* 140(1–2):309–313
- Kim H-S, Kim S, Kim H-J, Yang H-S (2006) Thermal properties of bio-flour-filled polyolefin composites with different compatibilizing agent type and content. *Thermochim Acta* 451(1–2):181–188
- Kołtowski M, Hilber I, Bucheli TD, Oleszczuk P (2016) Effect of steam activated biochar application to industrially contaminated soils on bioavailability of polycyclic aromatic hydrocarbons and ecotoxicity of soils. *Sci Total Environ* 566–567:1023–1031
- Kołtowski M, Hilber I, Bucheli TD, Charnas B, Skubiszewska-Zięba J, Oleszczuk P (2017) Activated biochars reduce the exposure of polycyclic aromatic hydrocarbons in industrially contaminated soils. *Chem Eng J* 310(Part 1):33–40
- Langlois VS, Rutter A, Zeeb BA (2011) Activated carbon immobilizes residual polychlorinated biphenyls in weathered contaminated soil. *J Environ Qual* 40(4):1130–1134
- Le Déaut J-Y, Procaccia C (2009) Les impacts de l'utilisation de la chlordecone et des pesticides aux Antilles : bilan et perspectives d'évolution. Rapport. 1778 (Assemblée Nationale), 487 (Sénat). Paris, France: Assemblée Nationale, Sénat
- Lehmann J, Rillig MC, Thies J, Masiello CA, Hockaday WC, Crowley D (2011) Soil biology & biochemistry biochar effects on soil biota: a review. *Soil Biol Biochem* 43(9):1812–1836. <https://doi.org/10.1016/j.soilbio.2011.04.022>
- Levillain J, Cattain P, Colin F, Voltz M, Cabidoche Y-M (2012) Analysis of environmental and farming factors of soil contamination by a persistent organic pollutant, chlordecone, in a banana production area of French West Indies. *Agric Ecosyst Environ* 159:123–132
- Liesch AM, Weyers SL, Gaskin JW, Das KC (2010) Impact of two different biochars on earthworm growth and survival. *Annals of Environmental Science* 4(1):1–9
- Liu Y, Lonappan L, Kaur S, Yang S (2018) Science of the total environment Impact of biochar amendment in agricultural soils on the sorption, desorption, and degradation of pesticides: a review. *Sci Total Environ* 645:60–70
- Lua AC, Ting Y (2005) Characteristics of Activated Carbon Prepared from Pistachio-Nut Shell by Zinc Chloride Activation under Nitrogen and Vacuum Conditions. *Journal of Colloid and Interface Science* 290(2):505–513. <https://doi.org/10.1016/j.jcis.2005.04.063>
- Marchand AP (1989) Synthesis and chemistry of homocubanes, bishomocubanes, and trishomocubanes. *Chem Rev* 89(5):1011–1033
- Matolcsy G, Nádasy M, Andriška V (1988) Pesticide chemistry, vol 32. Elsevier
- Mouvet C, Bristeau S, Amalric L, Dictor MC, Mercier A, Thannberger L, Mueller J, Valkenburg J, Seech A, Przepiora A (2011) In situ chemical reduction (ISCR) for removal of persistent pesticides; focus on kepone in tropical soils. In: *International Symposium on Bioremediation and Sustainable Environmental Technologies*
- Ncibi MC, Ranguin R, Pintor MJ, Jeanne-Rose V, Sillanpää M, Gaspard S (2014) Preparation and characterization of chemically activated carbons derived from Mediterranean *Posidonia oceanica* (L.) fibres. *J Anal Appl Pyrolysis* 109:205–214
- OECD (1984) Test n° 207 earthworm acute toxicity test. In: *Section 4: effects on biotic systems*. Vol. 4, Guideline for testing of chemicals. OECD publishing, Paris
- Paul P, Ghosh U (2011) Influence of activated carbon amendment on the accumulation and elimination of PCBs in the earthworm *Eisenia fetida*. *Environ Pollut* 159(12):3763–3768
- Perelo LW (2010) Review: in situ and bioremediation of organic pollutants in aquatic sediments. *J Hazard Mater* 177(1–3):81–89

Rouquerol J, Rouquerol F, Llewellyn P, Maurin G, Sing KSW (2013) Adsorption by powders and porous solids: principles, methodology and applications. Academic press

Schmidt MWI, Torn MS, Abiven S, Dittmar T, Guggenberger G, Janssens IA, Kleber M, Kögel-Knabner I, Lehmann J, Manning DAC, Nannipieri P, Rasse DP, Weiner S, Trumbore SE (2011) Persistence of soil organic matter as an ecosystem property. *Nature* 478(7367):49–56

Tammeorg P, Asko S, Pirjo M, Frederick LS, Laura A, Juha H (2014) Biochar Application to a Fertile Sandy Clay Loam in Boreal Conditions: Effects on Soil Properties and Yield Formation of Wheat, Turnip Rape and Faba Bean. *Plant and Soil* 374(1):89–107. <https://doi.org/10.1007/s11104-013-1851-5>

Wang T-T, Cheng J, Liu X-J, Jiang W, Zhang C-L, Xiang-Yang Y (2012) Effect of biochar amendment on the bioavailability of pesticide chlorantraniliprole in soil to earthworm. *Ecotoxicol Environ Saf* 83:96–101

Wang Z, Han L, Sun K, Jin J, Ro KS, Libra JA, Liu X, Xing B (2016) Sorption of four hydrophobic organic contaminants by biochars derived from maize straw, wood dust and swine manure at different pyrolytic temperatures. *Chemosphere* 144:285–291

Woignier T, ClosØF, Fernandes P, Rangan L, Soler A, Lesueur-Jannoyer M (2016) Compost addition reduces porosity and chlordecone transfer in soil microstructure. *Environ Sci Pollut Res Int* 23(1):98–108

Yehya S, Delannoy M, Fournier A, Baroudi M, Rychen G, Feidt C (2017) Activated carbon, a useful medium to bind chlordecone in soil and limit its transfer to growing goat kids. *PLOS ONE* 12(7):e0179548

Zhang Q, Muhammad S, Wang C (2019) Effects of Biochar on the Earthworm (*Eisenia Foetida*) in Soil Contaminated with and/or without Pesticide Mesotrione. *Science of The Total Environment* 671: 52–58. <https://doi.org/10.1016/j.scitotenv.2019.03.364>

## Acknowledgements

---

We thank C. Soligot and P. Hartmeyer (Université de Lorraine, EA 3998) for their valuable technical support.

## Funding information

---

We acknowledge the financial support of the Martinique Prefecture (PITE convention n° DRRT-2015-02) and the ANR (ANR-16 CE210008-01).