



**HAL**  
open science

## Densities of hemp shiv for building: From multiscale characterisation to application

Philippe Glé, Thibaut Lecompte, Arthur Hellouin de Ménibus, Hélène Lenormand, Santiago Arufe, Camille Chateau, Vanessa Fierro, Alain Celzard

### ► To cite this version:

Philippe Glé, Thibaut Lecompte, Arthur Hellouin de Ménibus, Hélène Lenormand, Santiago Arufe, et al.. Densities of hemp shiv for building: From multiscale characterisation to application. *Industrial Crops and Products*, 2021, 164, pp.113390. 10.1016/j.indcrop.2021.113390 . hal-03207569

**HAL Id: hal-03207569**

**<https://hal.univ-lorraine.fr/hal-03207569>**

Submitted on 30 Apr 2021

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# 1 Densities of hemp shiv for building: from multiscale 2 characterisation to application

3 Philippe Glé<sup>1</sup>, Thibaut Lecompte<sup>2\*</sup>, Arthur Hellouin de Ménibus<sup>3,4</sup>, Hélène Lenormand<sup>5</sup>, Santiago  
4 Arufe<sup>5</sup>, Camille Chateau<sup>6</sup>, Vanessa Fierro<sup>7</sup>, Alain Celzard<sup>7</sup>

5 <sup>1</sup>UMRAE, CEREMA, Univ Gustave Eiffel, IFSTTAR, F-67035 Strasbourg, France

6 <sup>2</sup> Univ. Bretagne Sud, UMR CNRS 6027, IRDL, F-56100 Lorient

7 <sup>3</sup> Eco-Pertica, Hôtel Buissonnet, 61340 Perche-en-Nocé, France

8 <sup>4</sup> French National Association of Short Distribution Network Hemp Producers (Association  
9 Nationale des Chanvriers en Circuits Courts), France

10 <sup>5</sup> UniLaSalle, Univ. Artois, ULR 7519-Transformations & Agro-ressources, Normandie Université,  
11 F-76130 Mont Saint Aignan, France

12 <sup>6</sup> Laboratoire Navier, Ecole des Ponts ParisTech, Univ Gustave Eiffel, CNRS, 77455 Marne-la-  
13 Vallée, France

14 <sup>7</sup> Université de Lorraine, CNRS, IJL, F-88000 Epinal, France

15

16 \*Corresponding author: [thibaut.lecompte@univ-ubs.fr](mailto:thibaut.lecompte@univ-ubs.fr)

## 17 **Abstract**

18 This paper concerns the packing of plant particles (hemp shiv) used for building applications and  
19 aims to quantify skeletal, particle and packing densities and associated porosities. These  
20 parameters were measured on hemp particles as a case study and were used to assess the  
21 physical behaviour of this material in terms of water adsorption and absorption, mechanical  
22 compression and thermal and acoustic behaviours. A number of experimental methods have been  
23 used to characterise these parameters including fluid and powder pycnometry, mercury intrusion  
24 and X-ray computed tomography, leading to robust and complementary results as a function of  
25 particle size and level of aging by immersion in water. It was concluded that smaller particles are

26 characterised by higher packing and particle densities, while aged particles present a strong  
27 evolution of their microstructure, which is visible through lower packing and particle densities and  
28 higher skeletal density. By comparing these experimental results with physical property  
29 characterisations, correlations were found between water absorption and open porosity,  
30 compression behaviour and the three density scales, and between acoustic dissipation and intra-  
31 and inter-particle porosities.

32 **Keywords:** bio-based aggregates; building materials; density; porosity; microstructure; acoustics;  
33 mechanics; thermal properties

34

## 35 1. Introduction

36 Due to environmental considerations, bio-based aggregates for building construction have been  
37 increasingly studied and applied in the past three decades. Bio-based aggregates are mainly by-  
38 products, ground during a de-fibration or harvesting process, such as hemp, flax, sunflower, rice,  
39 corn, barley or lavender. They are sold on the market as raw materials, in the form of packed  
40 elongated and flaky particles, from a few millimeters to 4 cm long, with the exception of sunflower  
41 pith. The main assets of these aggregates for building applications are their plant origin and their  
42 high porosity. As a crop product, bio-based aggregates act as a carbon sink and then limit the  
43 greenhouse effect due to their use in construction and building (Ingrao et al., 2015; Pittau et al.,  
44 2018; Lecompte, 2019; Zieger et al., 2020). Their high porosity gives bio-based building materials  
45 a high level of thermal, acoustic and vapor diffusion performances. These particles have numerous  
46 variabilities (Viel et al., 2018). This is due to, firstly, the difference in species, soil composition in  
47 the fields, weather, cultivation practices and fertilisation, harvesting, grinding and sieving  
48 processes (Lenormand et al., 2017) and, secondly, the heterogeneity of measurement protocols  
49 (Amziane and Collet 2017; Lenormand et al., 2018).

50 Among all plant particles that can be used in buildings, hemp shiv is the material on which scientific  
51 studies and real building works have most focused on, due to the developments of hemp-lime bio-  
52 based concrete in the early 90s (Amziane and Arnaud, 2012; Amziane and Collet, 2018).  
53 Historically, hemp was cultivated for fibres. Shiv comes from the woody part of the hemp stem, and  
54 it is increasingly commercialised as a fibre by-product. It can be used alone as a raw material, to  
55 insulate ceilings for example. It can be used for floating floor applications using a thin layer of  
56 hemp shiv to level a surface. It can also be used with a binder (lime, cementitious binder or earth)  
57 as a bio-based composite, to insulate walls, floors and roofs of buildings.


58 In France, hemp is mainly cultivated from April to September. The harvest time depends on  
59 weather conditions and on the technical itinerary followed by the farmer. First, the seeds might be  
60 collected. Then the straw is cut and left on the ground for 1 to 4 weeks for the retting process.  
61 During retting, the plant matter is slightly degraded by microorganisms (Ribeiro et al., 2015), which  
62 facilitates defibration operations (the separation of shiv and fibres). The retting process is aborted  
63 when the weather conditions are mild enough to bale the straw or to chop the hemp directly in the  
64 field. Afterwards, the hemp is stored in a rainproof warehouse to prevent particles and fibres from  
65 being degraded due to prolonged or repeated contact with water. Hemp shiv might encounter  
66 humid conditions again if it is mixed with a binder. It can be exposed to humid conditions for a few  
67 days to several months depending on the building methods and working conditions. After storage,  
68 hemp is defibred and then screened to extract shiv from the fibres. Different shiv granulometry can  
69 be obtained, with particle lengths ranging from 4 to 20 mm, according to the French National  
70 Association of Short Distribution Network Hemp Producers.

71 The present study focuses on density and porosity mainly for two reasons. Firstly, because density  
72 is a method for characterising batches of raw particles. Secondly, because density and porosity are  
73 key characteristics for analysing either the thermal, acoustical or mechanical behaviour of plant  
74 particles alone or mixed with a binder:

- 75 - Thermodynamics: Irrespective of the type of building material, it is well known that thermal  
76 conductivity is strongly correlated with its density. Both the particle density and the inter-  
77 particle porosity affect their hygrothermal behaviour. Studies have been carried out to  
78 model the thermal conductivity of hemp shiv as a raw material or mixed with a binder. In a  
79 study on lime-hemp concrete, only the total porosity is used in the modelling (Collet and  
80 Prétot, 2014). Some authors (Cerezo, 2015) proposed a self-consistent homogenisation  
81 method relating the average particle density, the average particle conductivity and the  
82 density of the packing. Other authors (Tran-Le, 2019) also developed a scale  
83 homogenisation approach for lime-hemp composites, using three densities: the apparent  
84 density of the packing, that of the particles, and that of the particle cell walls (skeleton). In  
85 the same way, (Nguyen et al, 2010; Nguyen et al., 2016; Tronet et al., 2016) distinguished  
86 the intra-particle porosity (encompassing close and open porosity) and the inter-particle  
87 porosity.
- 88 - Acoustics: the acoustic behaviour of hemp shiv and hemp concrete has also been  
89 investigated in (Cerezo, 2005; Glé et al., 2012; Kinnane et al., 2016; Fotsing et al., 2017) at  
90 two main scales of porosity: inter-particle pores and intra-particle pores. It has been shown  
91 by (Glé et al, 2012) that not all of them contribute to sound dissipation, and a new scale of  
92 porosity, called “acoustic porosity” has been proposed.
- 93 - Mechanics: hemp shiv packing, in bulk or mixed with a mineral binder, can be considered  
94 as a granular matter. Then, their compression behaviour (in the fresh state as well as after  
95 hardening in the case of hemp concrete), is strongly related to their packing characteristics:  
96 porosity or solid volume fraction. Tronet et al. (2014, 2016) have used several models from  
97 the literature, each one relating the compression pressure (or the compressive strength) to  
98 the volume, itself depending on compactness, density or porosity, for instance (Walker,  
99 1923; Cooper and Eaton, 1962; Jones, 1960).

100 To summarise, the granular packing of plant particles, as a raw material or mixed with a mineral  
101 binder, presents different scales of porosity and the same packing density can be achieved in

102 different ways. For example, hemp shiv containing residual fibres will be lighter in the bulk state. In  
 103 this case, to reach the same density as a fully defibred shiv, it has to be compressed. Then, the  
 104 two kinds of packing, even with the same density, will show different structures, porosities,  
 105 percolation paths and local contacts, which will affect its acoustic, hydrothermal and mechanical  
 106 performances. It is then crucial to have a thorough knowledge of the densities, at the three different  
 107 scales of the packing: global apparent density, average particle density and particle skeleton  
 108 density. These different scales are illustrated in Fig. 1.

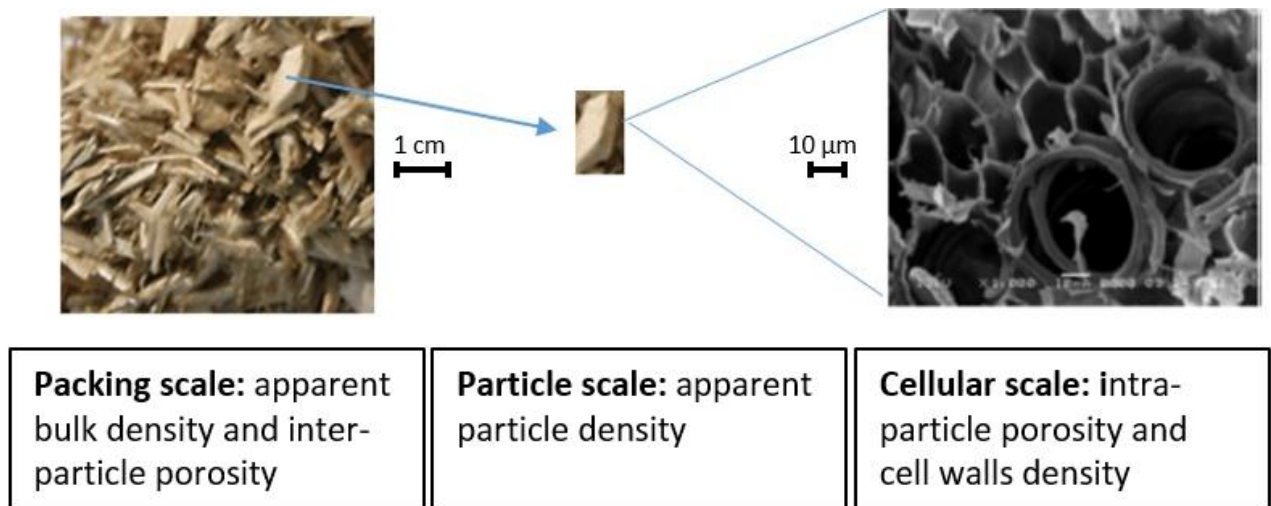

109  
110

Figure 1. The three different scales for studying hemp shiv packing

111

112 The density, compactness and porosity parameters, and their interrelations are defined in Table 1,  
 113 and Eq. (1) to Eq. (8).

114

Parameter	Definition	[unit]	and	related formulas
M	Total mass of a hemp shiv packing	[kg]		
$V_T$	Total, or bulk volume of a plant particles packing	[m <sup>3</sup> ]		
$V_{VT}$	Total volume of void space (irrespective of size) in the packing	[m <sup>3</sup> ]		
$V_P$	Total apparent volume of particles	[m <sup>3</sup> ]		
$V_{VP}$	Volume of void space inside the particles	[m <sup>3</sup> ]		$V_P = V_T - V_{VT} + V_{VP}$ (1)
$\rho_B$	Bulk density : apparent density of a packing	[kg/m <sup>3</sup> ]		$\rho_B = M / V_T$ (2)
$\rho_P$	Particle density: apparent density of particles	[kg/m <sup>3</sup> ]		$\rho_P = M / V_P$ (3)
$\rho_S$	Particle skeleton density	[kg/m <sup>3</sup> ]		$\rho_S = M / (V_P - V_{VP})$ (4)
$\varphi_T$	Total porosity inside a plant particle packing	[-]		$\varphi_T = V_{VT} / V_T = 1 - \rho_B / \rho_S$ (5)
$\varphi_P$	Intra-particle porosity	[-]		$\varphi_P = V_{VP} / V_P = 1 - \rho_P / \rho_S$ (6)
$\varphi_I$	Inter-particle porosity	[-]		$\varphi_I = (V_{VT} - V_{VP}) / V_T = 1 - \rho_B / \rho_P$ $= (\varphi_T - \varphi_P) / (1 - \varphi_P)$ (7)
$\varphi_{acou}$	Acoustic porosity: porosity contributing to sound dissipation	[-]		
$C_B$	Bulk compactness, or total solid volume fraction of the aggregate packing	[-]		$C_B = 1 - \varphi_T = \rho_B / \rho_S$ (8)

116

117 The measurement procedure to assess the bulk density predominantly affects the results: in this

118 state, the loading method of the packing has an impact on the measurement results (vibrations,

119 shocks, pouring, manual or mechanical compression). Several studies have been carried out to

120 identify how to measure the particles bulk density in a robust and repeatable way (Nozahic, 2012;

121 Amziane and Collet, 2017; Evrad, 2008; Fares, 2014). On one hand, the bulk density is not an

122 intrinsic property of an individual shiv since it encompasses the closed and open porosities inside  
123 hemp shiv particles plus a given amount of air between the particles, which depends on the  
124 measurement method. On the other hand, the bulk density gives some indications on the batch  
125 composition in terms of particle shape and size (a smaller particle size results in a higher bulk  
126 density) and of the purity level after the defibration process (the remaining fibres lower the density).  
127 Then, the literature values for the bulk density of hemp shiv range from 50 to 155 kg.m<sup>-3</sup> (Nguyen,  
128 2010; Laborél-Prénéron et al., 2018; Amziane and Collet, 2018; Lenormand et al., 2017).

129 At the particle scale, some attempts have been made to estimate the density of shiv, called  
130 “particle density”. Nguyen (2010) measured the density of the woody core of hemp stems by  
131 weighing and measuring the volume of a de-skinned and defibred stem. Values around 260 kg.m<sup>-3</sup>  
132 have been found. Pierre and Carin (2019), with a similar protocol, found 265±15 kg.m<sup>-3</sup>. The main  
133 problem at this scale is the variability of this material, first from particle to particle in the same  
134 batch, but it also depends on the species and the crop practices. A significant variability is even  
135 observable in the same stem, as reported by Glé (2013) through acoustic measurements on  
136 different types of shiv from the bottom, middle or top of hemp stems, and by Beaugrand et al.  
137 (2014).

138 At the skeleton scale, the measurements are generally achieved with a gas pycnometer. The size  
139 order of cell wall density of hemp shiv, obtained in this way, is 1450 kg.m<sup>-3</sup> (Amziane and Collet,  
140 2018). This value is close to the density of the holo-cellulose 1540 kg/m<sup>3</sup> (Ehrnrooth ,1984) that  
141 mainly composes the cell walls of hemp shiv.

142 There are still a number of key questions concerning the measurements, the values and the  
143 variability in the densities of plant particles, such as:

- 144 - If the measurement of particle density has been made on pristine, full hemp stem samples  
145 collected directly after harvesting, then they have not undergone retting, grinding and  
146 sieving during their life cycle. The outer cell wall would be mechanically damaged (by  
147 grinding), and the inner cells could be biochemically damaged (by retting).



- 148 - If the differentiation between open and closed intra-particle porosities has never been  
149 made, it may have some consequences on performances, particularly in acoustics.
- 150 - And even if some clear recommendations have been made by a RILEM technical  
151 committee concerning the measurement of bulk density, it still remains difficult to interpret  
152 the results from different density measurement methods from a physical point of view.

153 Thus, the aim of this paper is to provide an overview of the densities and porosities of plant  
154 particles used as building aggregates, focusing on: what are the different porosities, how to  
155 measure them and how to use them to predict their properties in building applications. The case  
156 study uses a commercialised hemp shiv in two different states: the raw (initial) shiv being  
157 compared to a shiv that has been wetted over a long period of time.

158 The particles are described, followed by experimental measurements (batch density, pycnometry,  
159 mercury porosimetry and X-ray tomography). Finally, the results are analysed and compared, and  
160 discussions are based on applications in different contexts (mechanics, hydrothermal behaviour  
161 and acoustics).

162 The main contributions and originalities of this paper lie in: the measurement of particle densities  
163 by correlating tomography measurements and powder pycnometry in the same batches, to provide  
164 reliable values; the comparison of skeletal densities depending on the life cycle of the aggregate,  
165 and of its chemical composition; the understanding of what a bulk state is, depending on the  
166 conditioning process.

167

## 168 2. Materials and Methods

### 169 2.1. Hemp shiv: morphological and chemical description

#### 170 2.1.1. Description of hemp shiv samples

171 A commercial hemp shiv, lightly retted (yellow colour) was used in this study. Homogenous  
172 samples of particles have been sampled from a 200 L bag of shiv following RILEM TC 236-BBM  
173 procedures. This raw shiv is referred to as L in this paper.

174 To investigate the potential effects of the particle size of hemp shiv on densities, a fraction of this  
175 raw shiv was preserved as it was, while the rest was sieved in order to artificially produce other  
176 shiv with different particle sizes. These shiv are referred to as  $L_{xy}$  where  $x$  and  $y$  are respectively  
177 the lower and the higher sizes (in mm) of the associated sieves. Three shiv were thus produced:  
178  $L_{12}$ ,  $L_{24}$  and  $L_{4+}$  (particles that do not pass through the 4mm sieve).

179 Shiv can dramatically change in terms of microstructure depending on their environment. In  
180 consideration of this, it was decided to study raw samples ( $L$ ,  $L_{12}$ ,  $L_{24}$  and  $L_{4+}$ ) as well as  
181 samples artificially aged through immersion in water.

182 The aged samples consisted of shiv immersed for 8 days in laboratory temperature conditions  
183 ( $T=20^{\circ}\text{C} \pm 2^{\circ}\text{C}$ ) using nets ballasted in buckets filled with 10 L of mains water. The duration of 8  
184 days was chosen on the basis of previous results of Glé and Gourlay (2015) showing that the  
185 skeletal density of immersed shiv increases significantly during this time and then stabilises. This  
186 duration can also be considered as a state of extreme aging in the fields where hemp is cultivated.

187 After 8 days, the water had a very strong smell of fermentation. The drying of these samples was  
188 carried out in two steps: first, the samples were kept for several days in the open air, then the  
189 samples were placed in an oven at  $50^{\circ}\text{C}$  until their mass stabilised at 0.01%. After stabilisation, the


190 samples were then sent to the different laboratories for measurements. These modified samples of  
191 shiv are named  $L_{xyM}$ .

## 192           **2.1.2. Particle size distribution**

193 The particle size distribution of original shiv ( $L$ ,  $L12$ ,  $L24$  and  $L4+$ ) and modified shiv ( $LM$ ,  $L12M$ ,  
194  $L24M$  and  $L4+M$ ) was determined by image analysis using the protocol described by Amziane and  
195 Collet (2017). Images of each sample were taken using an optical system (Keyence, CA-MX500M)  
196 by placing the particles on a plate (CA-DSW15). The particle size was then determined employing  
197 a scale factor of 0.0609 mm/pixel. At least 1000 particles of each sample were measured. This  
198 number allows guaranteeing a certain accuracy of measurement. Indeed, a study based on 10  
199 various hemp shiv  $\mu$  (Glé, 2013) showed that the analysis of 1000 particles led to an uncertainty  
200 for particle width and length distributions strictly lower than 5%, and confirmed previous results by  
201 Ceyte (2008).

202 Fig. 2 shows the accumulated particle frequency of length and width for all studied samples. The  
203 four size distributions are correlated with the sampling sieves, in terms of length and width. The  
204 larger size of the corresponding sieve used results in a particle size distribution with a higher  
205 percentage of larger and longer particles. For example, the corresponding width for 50% of  
206 cumulated particle frequency increased from 1.2 ( $L12$ ) to 1.8 mm ( $L4+$ ),  $L$  having the smallest (1  
207 mm).

208 Regarding the effect of the immersion of hemp shiv in water for 8 days ( $LM$ ,  $L12M$ ,  $L24M$ ,  $L4+M$ )  
209 compared to the same sampling without immersion, particle size distributions show a higher  
210 percentage of large particles. The characteristic dimensions of the shiv (mean and median of  
211 distributions) presented in Table 2 increase from 15 to 22% in length and from 7 to 21% in width,  
212 which highlights a significant swelling of particles caused by water.

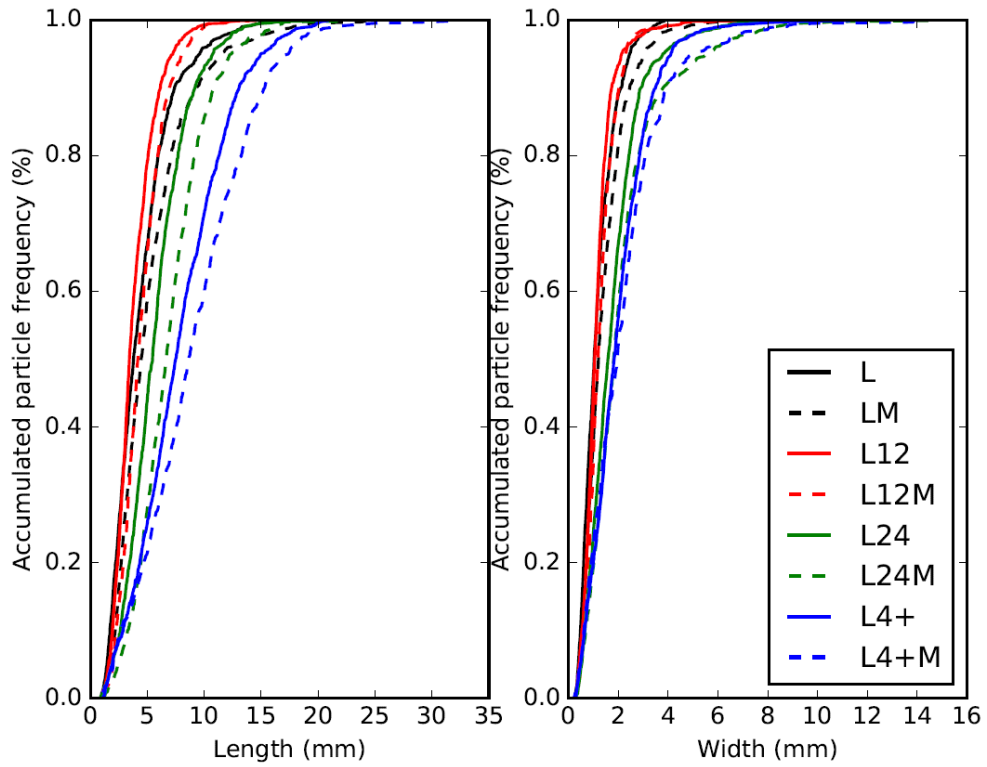

213

214 Figure 2. Particle size distribution of hemp shiv in length and width, characterized through 2D-  
 215 image analysis

216 Table 2. Characteristic dimensions of shiv, deduced from 2D-image analysis (mean and standard deviation values are  
 217 derived from a lognormal distribution)

Shiv	Length (mm)					Width (mm)				
	Median	Mean	Std Dev	Mean (log(L))	Std Dev (log(L))	Median	Mean	Std Dev	Mean (log(W))	Std Dev (log(W))
<b>L</b>	3.78	4.36	2.58	3.72	1.77	1.02	1.17	0.66	1.00	1.74
<b>LM</b>	4.45	5.24	3.31	4.43	1.77	1.20	1.40	0.92	1.16	1.84
<b>L12</b>	3.42	3.82	1.76	3.46	1.57	1.05	1.15	0.63	1.03	1.61
<b>L12M</b>	4.16	4.48	1.88	4.10	1.54	1.17	1.27	0.62	1.14	1.60
<b>L24</b>	5.46	5.70	2.69	5.06	1.67	1.58	1.77	1.10	1.49	1.82
<b>L24M</b>	6.63	6.93	3.06	6.23	1.63	1.81	2.14	1.58	1.72	1.95
<b>L4+</b>	7.47	7.87	3.98	6.74	1.83	1.83	2.00	1.21	1.66	1.91
<b>L4+M</b>	8.62	9.01	4.75	7.55	1.93	1.95	2.21	1.64	1.72	2.08

218

### 219                    **2.1.3.        Chemical composition**

220    The chemical composition of hemp shiv (with contents of ash, lignin, cellulose, hemicellulose and  
221    soluble matter) was determined according to the Van Soest method (NF V 18-122). To carry out  
222    this measurement, hemp shiv (previously dried at 40°C until obtaining a constant weight) were  
223    milled using a micro impact mill (Culatti, Switzerland). The rotor speed was adjusted to 7, and a  
224    standard sieve of 1 mm mesh size was used.

225    Hemp shiv L and LM show very close standard compositions (g/100 g dry solid). These values  
226    presented in Table 3 are in line with the data in the literature (Amziane and Arnaud, 2012; Amziane  
227    and Collet, 2017; Cappelletto et al., 2001; Beaugrand et al., 2014; Viel et al., 2018; Delannoy et al.  
228    2020). Scatter between studies might come from the variability in particle batches due to plant  
229    variability or different retting conditions. It could also come from the measurement procedures (Van  
230    Soest, TAPPI) or from the way compositions are calculated by percentage.

231    The method used for the determination of the chemical composition is based on the calculation of  
232    the percentages of each component by their elimination during the experiment, which gives the  
233    relative proportion of each component in the sample. This can explain the fact that, for example,  
234    hemicellulose and lignin had slightly higher values for LM hemp shiv compared to L hemp shiv. In  
235    this context, it must be taken into account that LM has a mass loss due to immersion, which leads  
236    to lower quantities of all compounds compared to L hemp shiv in an absolute scale. Taking into  
237    account the mass loss caused by water immersion for 8 days, it seems that the main affected  
238    compounds may be soluble matter and ashes. For example, Thygens et al. (2013) found a 38 %  
239    mass loss on hemp stems after immersion in water at 35°C for 4 days. Water treatment generated  
240    a decrease in hemicellulose and pectin (soluble) contents. Differences in plant matter (hemp stems  
241    for Thygens et al. (2013), hemp shiv for this study), conditions of treatment (temperature, duration)  
242    and probably the degree of retting explain the variability.

243

244 Table 3. Chemical composition of the different shiv samples, and values found in the literature (Amziane and Arnaud,  
 245 2012; Amziane and Collet, 2017; Cappelletto et al., 2001; Beaugrand et al., 2014; Viel et al., 2018; Delannoy et al. 2020)

g/100g dry solid	Soluble matter	Hemicellulose	Cellulose	Lignin	Ashes
L	9.5±1.2	16.8±2.5	60.8±2.2	10.4±1.1	2.5±0.1
LM	8.1±0.5	18.6±0.5	59.4±0.9	12.03±0.3	2.0±0.1
Literature	5.1 – 12	9 - 25.9	34.5 - 54.9	9 - 28	1.2 - 6.5

## 246 2.2. Microstructure and density characterisation methods

### 247 2.2.1. Methods for measuring the bulk density

248 Four methods for the measurement of bulk particle density have been explored in the literature:

- 249 • **Trimmed density:** shiv is gently placed in a cylinder, progressively dropping the particles in  
 250 the form of a light rain, then the particles are levelled and the cylinder is weighed (Nozahic,  
 251 2012).
- 252 • **Apparent density:** shiv is placed in a cylinder and overturned ten times, then the packing  
 253 volume and mass are measured (Amziane and Collet, 2017).
- 254 • **Tapped density:** shiv is placed in a cylinder, and the container is tapped on a rigid surface  
 255 a given number of times (or alternatively a weight is dropped from a given height on the  
 256 table where the cylinder is placed). Hemp shiv is progressively compacted up to a  
 257 saturation point (Evrard, 2008; Fares, 2014). Two methods based on an automatic process  
 258 have been used to measure this density, firstly using a MICROMERITICS GeoPyc 1360  
 259 pycnometer (GeoPyc density), and secondly a QUANTACHROME AT-6 Autotap device  
 260 (Autotap density). With the Geopyc, the sample chamber is rotated and agitated while a  
 261 force is applied to the sample. The measurements were repeated 12 times (or for 12  
 262 cycles) and carried out in a cell with an internal diameter of 12.7 mm and subjected to a  
 263 piston applying a force of 5N. With the Autotap, the samples were shaken with a given  
 264 tapping rate, tapping force and cylinder diameter, to obtain a stabilised packing. The  
 265 measurements were carried out in a 100 cm<sup>3</sup> test tube (internal diameter 2.5 cm and height

266 of the graduations 18 cm) and subjected to 4500 consecutive shakes or strokes (speed 260  
267 strokes per minute, displacement in the height direction of 2 mm).

268 • **Compacted:** shiv is compacted manually using a wooden structure, up to saturation point  
269 following the protocol of Chiasson-Poirier et al. (2020).

270  
271 The first three methods measure a “random loose packing” (RLP) while the latter measures a  
272 “close packing” (CP). The random loose packing corresponds to a momentum state of the packing  
273 for which the percolation and the contacts between particles only compensate for gravity. The  
274 different random loose packing methods are not equivalent since the difference between tapped  
275 and loose density gives some indication about how particles flow (Lam et al., 2007). The close  
276 packing supposes a higher energy of compaction to rearrange the particles and reach an optimum  
277 of compactness without particle deformation. For example, the RLP compactness of uniform rigid  
278 spheres packing is about 0.555 while its CP compactness is 0.645 (Onoda and Liniger, 1990).

279 All these bulk measurement methods were carried out with shiv at equilibrium in laboratory  
280 conditions (20 - 23 °C / 50%HR). For trimmed, apparent and compacted densities, glass cylinders  
281 were used with a 16 cm inner diameter and a height of 32 cm.

## 282 **2.2.2. Pycnometry**

283 Pycnometry is the technique of measuring the volume of a solid by placing a sample in a cell of a  
284 certain and very precise volume, and measuring the quantity of fluid that can be placed in it  
285 afterwards. Depending on whether or not this fluid can penetrate the porosity of the solid, *i.e.*,  
286 whether it is a gas or a fine powder, the volume of the solid skeleton or the envelope of the solid  
287 can be determined. By knowing the sample mass, its skeletal (true) or apparent (envelope) density  
288 can be deduced.

289 The true density, or skeletal density, of the hemp particles, after being dried at 60°C for at least  
290 24h under vacuum, was investigated with a MICROMERITICS Accupyc II 1340 pycnometer using  
291 two different inert gases, helium (He) and nitrogen (N<sub>2</sub>). These methods were applied to all the

292 samples, on the raw particles as well as on powdered particles, with the aim of observing possible  
293 differences due to closed porosity in the raw particles. Mercury intrusion porosimetry has also been  
294 used to estimate the skeletal density (See Section 2.2.3).

295 The Accupyc device, equipped with a 10 cm<sup>3</sup> cell (internal diameter 1.85 cm and height 3.8 cm)  
296 without insert, was used as follows: a filling pressure of 1.4 bars (19.5 psig) was first applied with  
297 an equilibrium rate of 0.005 psig / min. The analysis stopped when the volume obtained from the  
298 measurement cycle deviated by less than 0.1% from the average of the volumes of the last five  
299 cycles. Each density determination thus requires around fifty cycles. After the measurements were  
300 carried out, the samples were recovered and ground for 45 min in the 250 mL agate bowl of a  
301 Retsch PM100 planetary mill. By doing so, the particle size was reduced to between 100 and 500  
302 µm, and the measurements were repeated under the same conditions.

303 The envelope density of the particles was evaluated after being dried for 24h at 60°C under  
304 vacuum with a MICROMERITICS GeoPyc 1360 pycnometer (and with mercury intrusion  
305 porosimetry, see Section 2.2.3), using a cylindrical cell of volume 7.6 cm<sup>3</sup> (inner diameter 1.27 cm  
306 and length 6 cm). The larger particles (length 1 cm, width 0.3 - 0.5 cm, except for the smaller L12  
307 sample) were selected for this type of measurement, as they are more representative in cases  
308 where a significant part of closed porosity is present.

309 The characteristics, targets and limitations of these various pycnometry approaches is summarised  
310 in Table 4.

311



Hemp particles size/shape	Fluid	Measured deduced parameter	or Experimental device	Experimental validity/ limitation
<b>Aggregate (Shiv particles)</b>	Dry Flo powder (Micro-Meritics®)	Apparent (« envelope » particle density)	Geopyc 1346 Sample volumes between 0.3 cm <sup>3</sup> and 0.8 cm <sup>3</sup>	Typical range of sizes : 100 – 200 µm > capillary pore diameter
	Helium (He)	Open porosity	Accupyc II 1340 Volume: 10 cm <sup>3</sup>	Kinetic diameter of N <sub>2</sub> : 0.364 nm;
	Nitrogen (N <sub>2</sub> )			
	Air			Kinetic diameter of He: 0.26 nm
				(Breck ,1974)
<b>Ground powder (100&lt;X&lt;500 µm)</b>	Helium (He)	Particle walls density, deduction of closed porosity by comparison with the skeletal density measured on raw particles.	Accupyc II 1340 Volume: 10 cm <sup>3</sup>	Size of the ground powder (be sure to not have remaining closed porosity)

313

314 **2.2.3. Porosimetry by mercury intrusion**

315 Mercury porosimetry involves forcing mercury to penetrate the porosity of a porous solid. As  
 316 mercury is a non-wetting liquid, it is necessary to increase its pressure for it to intrude into smaller  
 317 and smaller pores. At low pressure, the mercury follows the contours of the material sample; its  
 318 volume and therefore its apparent density can be deduced. However, it can never be certain that  
 319 the mercury penetrated all the pores at the pressure applied. On the contrary, at very high  
 320 pressure, when the mercury is supposed to have penetrated all the accessible porosity, the  
 321 skeletal density of the material can be deduced. Here, another assumption must be made,

322 according to which there is no narrower porosity remaining that mercury could have penetrated if  
323 the device had been able to access higher pressures.

324 Mercury porosimetry is therefore an interesting technique because it can make it possible to  
325 determine these two types of density, but subject to assumptions that are difficult to verify, except  
326 by comparing the results with gas and powder pycnometry techniques. Any significant difference in  
327 the results will then be indicative of the limitations of mercury porosimetry. This method can in  
328 particular have difficulty in separating interparticle porosity from intraparticle porosity. In addition,  
329 the necessarily limited pressure that the porosimeter can reach prevents the intrusion into the  
330 narrowest pores, producing significant errors in the case of nanoporous solids.

331 Mercury porosimetry is nevertheless a valuable technique since it is possible to deduce the  
332 distribution of pore sizes from it. The corresponding calculation is based on the knowledge of the  
333 relationship between the pressure and intruded pore diameter (known as the Washburn equation),  
334 but is again based on questionable assumptions, including the fact that pores are considered to be  
335 cylindrical and that they are gradually intruded from the widest to the narrowest when the pressure  
336 increases. However, nothing prevents large porous volumes being downstream of narrow pores.  
337 These pores, called "ink-bottle" pores, then lead to the overestimation of the volume of narrow  
338 pores and to the underestimation of the larger ones, and consequently the diameters determined  
339 by the method are not pore diameters but neck diameters, *i.e.* diameters of the restrictions giving  
340 access to real pores. This is well known in the case of lignocellulosic biomass, where tracheids  
341 have a diameter in the order of 10  $\mu\text{m}$  and are accessible only by pits that ensure the connections  
342 between them, which have a diameter in the order of 1  $\mu\text{m}$ .

343 In this work, an Autopore IV Micromeritics device has been used. Prior to analysis, the samples  
344 were dried at 60°C in a vacuum oven, and then placed in a glass penetrometer (total volume of  
345 3.54  $\text{cm}^3$  with a 3.13  $\text{cm}^3$  reservoir). The particles were introduced by hand and the penetrometer  
346 gently agitated to allow dense stacking. The procedure was repeated as many times as necessary  
347 to introduce the maximum number of particles. The experiments were performed in two steps: low

348 pressure (0.001–0.24 MPa) and high pressure (0.24–414 MPa). The low- and high- pressure  
349 equilibration time setting was 10 seconds.


#### 350 **2.2.4. X-ray computed tomography**

351 X-ray computed tomography (XRCT) is a non-destructive imaging technique, which is now widely  
352 used in materials science. It provides 3D images of objects that reveal their internal structure (see  
353 e.g. (Brisard et al., 2020) for detailed information on the method). It has been used, for example, to  
354 visualise the microstructure of hemp shiv (Ceyte, 2008; Jiang et al., 2018; Bennai et al., 2018).  
355 Here, we propose to obtain the 3D envelope of the particles individually, to estimate their apparent  
356 volume and then deduce their apparent density from a mass measurement.

357 Image acquisition was performed using an XRCT laboratory scanner (Ultratom from RX-Solutions).  
358 Several hemp shiv of different sizes, were imaged together to minimise the number of image  
359 acquisitions. In order to make image processing easier, the particles were separated from each  
360 other by placing them into individual compartments made from adhesive tape strips covered with  
361 expanded polystyrene (EPS) beads with a diameter of about 1 mm. Tape strips were sewn with  
362 cotton thread to form the compartments. It was necessary to use such low attenuating materials to  
363 minimise the absorption contrast with hemp shiv, and then to avoid streak artefacts on the images.  
364 Once set, the particles were put vertically into a plastic container.

365 Two scans were necessary to examine 29 particles. The magnification (*i.e.* the voxel size) was  
366 chosen to limit the number of image acquisitions whilst still having a sufficient resolution to  
367 characterise the envelope accurately. Each scan lasted about 12 hours (image acquisition settings  
368 are given in Appendix). Note that the exposure time needs to be long enough to improve the  
369 signal-to-noise ratio of the images and thus to overcome the low X-ray attenuation of the hemp  
370 shiv. The final 3D images have been reconstructed with a voxel size of 12  $\mu\text{m}$ , using the X-Act  
371 software provided by the manufacturer of the XRCT device, and regions of interest were cropped  
372 around each particle. As illustrated in Fig. 3a and the cross-sections provided as supplementary

373 material, the images reveal the heterogeneous microstructure of the particles, including growth  
374 rings. Although the largest vessels can be seen, the spatial resolution is not fine enough to  
375 characterise porosity. Finally, the images were processed to select the particle only (segmentation)  
376 and to estimate its apparent volume, as described in Appendix. As illustrated in Fig. 3, the  
377 envelope of the particle is correctly extracted, retaining most of the fine details.

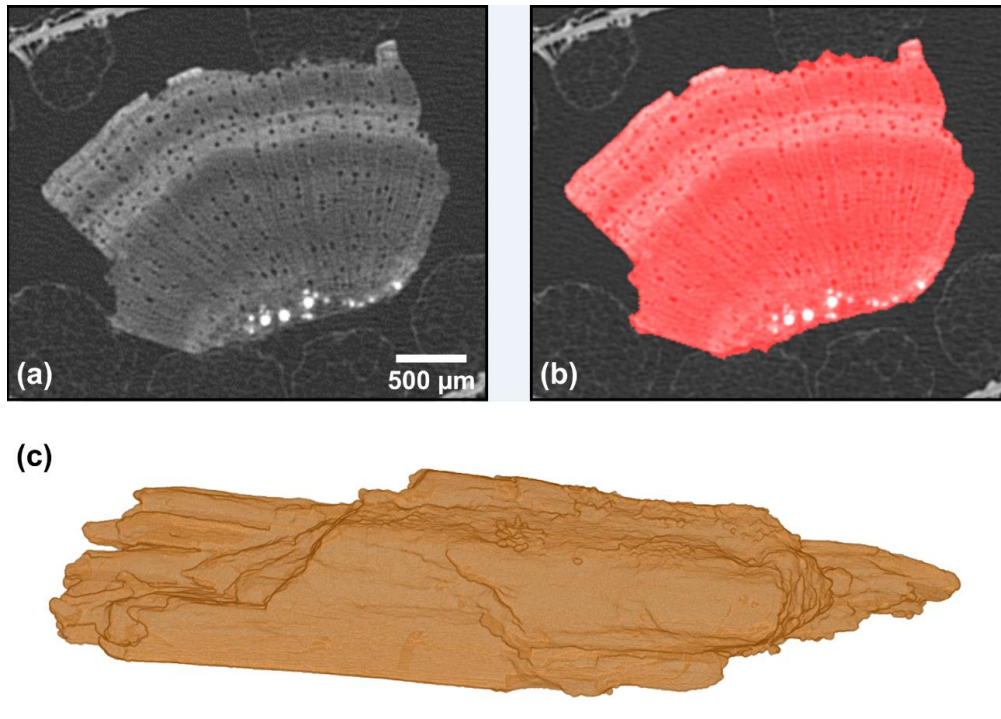

378  
379 Figure 3. Extraction of the envelope of a L24 particle (approx. 11 mm long) : (a) cross-section of  
380 the XRCT image, (b) result of image segmentation superimposed on the original slice, (c) 3D  
381 rendering of the envelope, obtained using Volume Viewer plugin included in Fiji (Schindelin et al.,  
382 2012).

383  
384 An analysis was conducted on two *L12*, one *L24* and one *L4+* particles to estimate the sensitivity  
385 of the volume measurement to image processing parameters. Their values were varied in ranges  
386 resulting in a qualitatively good segmentation. Thus, the volume measurement was found to be  
387 mainly sensitive to grey level thresholding with an uncertainty ranging from 1% to 4.5%, without  
388 any correlation with particle sizes. Furthermore, preliminary tests were conducted on a few

389 particles with a finer resolution (voxel size of 4  $\mu\text{m}$ ) and showed the discrepancy to be less than  
390 2%. Thus, the results take into account of a 5% uncertainty in the measurement of the volume of  
391 all particles. In addition, each particle was weighed with an analytical balance with a precision of  
392 100 $\mu\text{g}$ , which produces an uncertainty of measurements of 11% for the smallest *L12* particle, of  
393 less than 2.5% for *L24/L24M* particles, and less than 1% for *L4+/L4+M* particles. Finally, the  
394 apparent densities  $\rho_p$  (as defined in Table 1, Eq. (3)) and the corresponding uncertainties have  
395 been estimated for each particle individually and grouped by type of shiv (Table 5), where *L/LM*  
396 refers to all particles, all sizes included. The overall uncertainties reach 10%, 6.5%, 5% and 6% for  
397 *L12/L12M*, *L24/L24M*, *L4+/L4+M* and *L/LM* particles, respectively. Average particle densities are  
398 discussed in the following sections of the paper but densities per particle are available in  
399 supplementary material for information.

## 400       **2.3. Methods to characterise the physical properties of** 401           **hemp shiv**

### 402       **2.3.1. Study of water sorption**

403 Water sorption isotherms of hemp shiv were determined at 23°C using a Dynamic Vapour Sorption  
404 machine (SPS-Sorption Test System, proUmid), using nitrogen as the carrier gas in order to  
405 control relative humidity. Each sample was at least measured in duplicate (219  $\pm$  34 mg as  
406 average sample weight). Different equilibrium points were determined corresponding to a fixed  
407 relative humidity (RH): 0, 5, 10, 15, 20, 30, 35, 50, 75, 85 and 90% for adsorption experiments, and  
408 0, 15, 30, 35, 50, 75, 85, and 90% for desorption experiments. The samples used for the  
409 adsorption experiments were previously dried at 40°C in an oven until reaching a constant weight.  
410 The samples for desorption were previously exposed to a relative humidity of 90% for hydration  
411 until they reached a constant weight.

412 Guggenheim-Anderson-de Boer (GAB) (Van den Berg and Bruin, 1981) model was used to fit the  
413 experimental water sorption data (equilibrium moisture content,  $X_{eq}$ , and relative humidity, RH) Eq.  
414 (9):

$$415 \quad X_{eq} = \frac{X_m K C R H}{(1 - K R H)(1 - K R H + C K R H)} \quad (9)$$

416 where  $X_m$  is the monolayer moisture content (kg water/kg dry solid), C (dimensionless, -) and K  
417 (dimensionless, -) are parameters related to the heat of sorption of the multilayer in the GAB  
418 model.

419 The water absorption kinetics of different samples were determined at 5, 15, 60, 480, 1444 and  
420 2880 min. Samples (~1 g) previously dried at 40°C until reaching a constant weight were placed in  
421 water using a tea strainer ball, then removed, filtered under a vacuum filter to remove excess water  
422 from the surface of the material, and dried in an oven at 105°C until reaching a constant weight to  
423 determine the mass loss during water absorption (SS, kg solid loss/ kg dry solid). SS was  
424 calculated as follows, Eq. (10):

$$425 \quad SS = \frac{\text{Dry mass before immersion (kg)} - \text{Dry mass after immersion (kg)}}{\text{Dry mass after immersion (kg)}} \quad (10)$$

426

### 427 **2.3.2. Acoustics**

428 Every hemp shiv in this study has been characterised following the method developed in (Glé et  
429 al., 2012).

430 The experimental data were obtained through an AcoustiTube impedance tube, having a diameter  
431 of 10 cm and a [50; 2000Hz] frequency range. The three-microphone method without cavity,  
432 developed by Iwase et al. (1998), was applied to measure the sound absorption coefficient  $\alpha$  as  
433 well as the intrinsic dynamic properties (dynamic density  $\rho$  and dynamic bulk modulus  $K$ ). For each

434 shiv, three densities of the mixes have been tested, ranging between 70 and 150 kg.m<sup>-3</sup> depending  
435 on the particle size distribution. For each density, the acoustic measurements were repeated three  
436 times.

437 The effective acoustic porosity, referred to here as  $\varphi_{acou}$ , was evaluated from the acoustic  
438 measurements. From  $\varphi_{acou}$ , it was then possible to evaluate for a given shiv the associated  
439 density  $\rho_{acou}$  so that  $\varphi_{acou} = 1 - \frac{\rho_B}{\rho_{acou}}$ . The initial assumption made in (Glé et al., 2012) was that  
440  $\rho_{acou} \approx \rho_P$ .

### 441 **2.3.3. Bulk compressive behaviour**

442 To measure the compressive behaviour of the hemp shiv granular packing, a steel cylinder die with  
443 an inner diameter of 30mm and a height of 170mm was used. The die was placed under a  
444 hydraulic press fitted with a force transducer (capacity of 500 kN), and a displacement sensor  
445 measured the position of the press crossbeam.

446  
447 A lower punch (40mm in height) was inserted into the die and the shiv was poured in, with a  
448 protocol similar to that of trimmed density measurements (Section 2.2.1), so the initial height of the  
449 granular packing was 130mm. Then, an upper punch of 30mm in height and a plain steel-cylinder-  
450 spacer of 100mm in height were set up.

451  
452 The compression was then controlled with displacement and speed, in three sequences:  
453 - a movement of 60 mm with a rate of 40 mm/min;  
454 - a movement of 40 mm with a rate of 20 mm/min;  
455 - a movement with a rate of 6mm/min, up to a compressive force of 110 kN (upper punch  
456 compressive stress of 155 MPa).

457  
458 This protocol is very close to the protocol developed by Tronet et al. (2014, 2016).

459

460 The compressive stress is calculated with the force given by the transducer, plus the weight of the  
461 upper punch and the spacer. The height of the sample during compression is deduced from the  
462 crossbeam position and is corrected, using a preliminary blank made on the stack of punches,  
463 spacer and transducer only. The size order of the stiffness of this solid stack is 5  $\mu\text{m}/\text{MPa}$ , which  
464 becomes significant for the highest compressive stresses.

465  
466 At the end of compression, the shiv packing is stiff and cohesive enough to be pulled out, and  
467 weighed. From the weight and initial height of the sample, an initial bulk density can be deduced,  
468 and then the evolution of the packing density versus upper punch compressive stress can be  
469 graphically represented.

470

#### 471 **2.3.4. Thermal properties in the bulk state**

472 The samples of hemp shiv were dried at 60°C before being tested. Two different protocols were  
473 carried out on the shiv packing: guarded hot plate and hot disk.

474

475 For the guarded hot plate, the measurements were performed at 23°C with a temperature  
476 difference between the plates of 20°C using a HFM 436/3/1E Lambda (NETZSCH). The sample  
477 size was 7x30x30 cm. The supplier indicates that the uncertainty on the measurement is 1 to 3%,  
478 and the repeatability is better than 0.25%.

479 Hot disk measurements were performed at room temperature (21°C) using a HOT DISK TPS 2500  
480 S. Hemp shiv was poured into a 1 liter plastic cylinder with a slot for the probe. The supplier  
481 indicates that the uncertainty on the measurement is lower than 5%, and the repeatability is better  
482 than 1%.



## 483 3. Results and discussion

### 484 3.1. Characteristics of hemp shiv

#### 485 3.1.1. Densities

486 All results are shown in Table 5, from the packing scale ( $\rho_B$ ) to the particle skeleton scale ( $\rho_S$ ). A  
 487 comparison of the approaches is first proposed scale by scale, then, the differences between  
 488 samples related to immersion and particle size effects are analysed.


489

490 *Table 5 : Bulk, particle and skeletal densities of hemp shiv scale by scale*

	<i>Bulk density <math>\rho_B</math> (kg.m<sup>-3</sup>)</i>					<i>Particle density <math>\rho_P</math> (kg.m<sup>-3</sup>)</i>			<i>Particles skeleton density <math>\rho_S</math> (kg.m<sup>-3</sup>)</i>				
	<i>Geopyc</i>	<i>Autotap</i>	<i>Trimmed</i>	<i>Apparent</i>	<i>Compacted</i>	<i>Hg</i>	<i>Geopyc</i>	<i>XRCT</i>	<i>Acou</i>	<i>N<sub>2</sub></i>	<i>Hg</i>	<i>He</i>	<i>He *</i>
<b>L</b>	137	133	99	108	140	290	330	311	478	1150	1211	1413	1460
<b>LM</b>	118	105	82	84	109	282	210	245	443	1450	1144	1441	1455
<b>L12</b>	150	128	105	136	159	305	326	286	515	1190	1247	1420	1457
<b>L12M</b>	108	101	83	87	107	246	254	252	469	1490	1238	1445	1450
<b>L24</b>	120	125	105	104	138	281	299	318	502	1170	1154	1430	1456
<b>L24M</b>	84	91	80	85	105	230	242	262	441	1480	1270	1454	1452
<b>L4+</b>	117	103	94	104	136	218	286	311	447	1140	1266	1407	1455
<b>L4+M</b>	91	79	64	73	102	236	274	241	396	1460	1260	1445	1450

491 \* *milled/ground particles*

492 The five methods used to evaluate bulk density lead to values ranging between 64 and 159 kg.m<sup>-3</sup>.  
 493 The two automatic methods for tapped density (Geopyc and Autotap) give similar results. These  
 494 values are compared to the manual methods in Fig. 4. Considering the other values, it appears that  
 495 trimmed densities are systematically the lowest, and that compacted densities are generally the  
 496 highest. The apparent density method lies between the trimmed density and the tapped density.  
 497 Such differences in values from one technique to another were expected, given the uncertainty  
 498 with this type of measurement and the rather different methods for obtaining them.

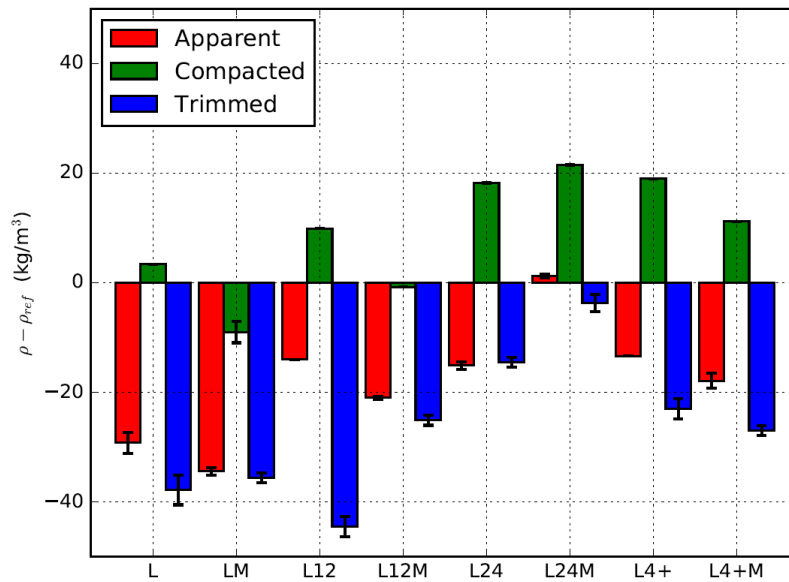


499  
 500 Figure 4. Bulk density of hemp shiv. Differences between manual and automatic methods (here  
 501 “reference density” corresponds to the average of the results from the Geopyc and Autotap  
 502 methods)

503

504 The particle densities evaluated using mercury intrusion and Geopyc, range between 210 and 330  
 505 kg.m<sup>-3</sup> and are relatively close, especially for the batches without large particles (L12, L12M, L24,  
 506 L24M) for which differences lower than 6% were observed. It can be observed that the values  
 507 obtained from Hg porosimetry are generally the lowest, suggesting that part of the inter-particle  
 508 porosity was not completely filled by mercury at the low pressure used for the measurement.  
 509 Regarding XRCT measurements, densities are also relatively close to Geopyc and Hg values.  
 510 Differences with Geopyc values are the lowest, ranging from 1% to 12% (all batches except L/LM).  
 511 Nevertheless, the final result could not be conclusive because of the significant variations observed  
 512 from one particle to another (see Fig. 5 and supplementary material), with relative standard  
 513 deviations ranging from 7% to 33% depending on the shiv. Two extreme values were observed (as  
 514 detailed in Appendix) that are very different from the general trend. They illustrate the variability in  
 515 the particle densities, but they seem to be only rare occurrences. The number of observed particles  
 516 was probably not enough to be statistically representative of the shiv, contrary to Geopyc

517 measurements, which were performed on larger sets of particles (cell of volume 7.6 cm<sup>3</sup>).  
 518 Therefore, at this scale, it was decided to focus mainly on Geopyc results for the remainder of the  
 519 paper.

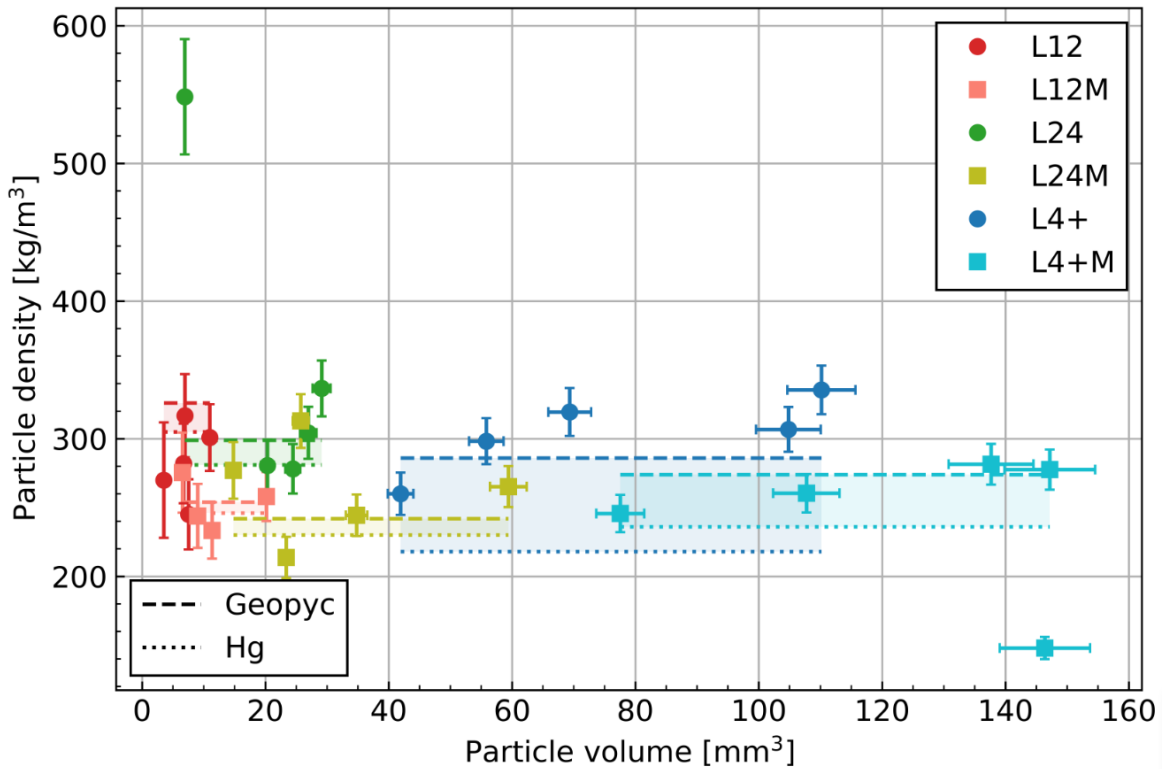

520  
 521 Figure 5. Particle densities estimated by tomography compared to mercury intrusion and Geopyc  
 522 measurements.

523  
 524 Finally, the skeletal density of the particles was analysed using four approaches. Values are in the  
 525 range of [1100 - 1500 kg.m<sup>-3</sup>] and globally respect the ranking  $\rho_{N_2} < \rho_{Hg} < \rho_{He} < \rho_{He\ powder}$ . Hg  
 526 intrusion values, at the highest pressure, 414 MPa, are indicated for information and are between  
 527 N<sub>2</sub> and He values. At such a pressure, the Washburn equation shows that the narrowest pores that  
 528 can be intruded have a diameter of only 3.6 nm.

529 On this basis, many features can be observed by comparing these results between reference and  
 530 immersed samples. At the loose packing scale, a decrease ranging between 14% and 30% of the  
 531 initial value in the density due to immersion is clearly visible, whether measured with Geopyc or

532 Autotap. This is associated to a dimensional swelling of particles which has also been observed  
533 elsewhere in previous studies (Castel et al., 2016; Delannoy et al., 2018). Concurrently, the  
534 envelope densities of the particles decreased after immersion, which is again related to this  
535 swelling effect. These results were confirmed by the three techniques (powder pycnometry, Hg  
536 porosimetry and X-ray computed tomography) used for measuring them. At the skeleton scale, an  
537 increase in the measured density is clearly visible after immersion (on the basis of N<sub>2</sub> and He  
538 pycnometry). This change has already been pointed out in other studies (Glé and Gourlay, 2015;  
539 Delannoy et al., 2018) and is a consequence of the degradation of the microstructure, resulting in  
540 an opening of pores that were initially not accessible. The measurements on finely ground samples  
541 (“He\*” column in Table 5) show that the density in this case is remarkably constant, with a value of  
542  $1455 \pm 5 \text{ kg}\cdot\text{m}^{-3}$ , irrespective of whether the materials were aged in water or not. However,  
543 differences between immersed and raw samples are visible in various ranges with He and N<sub>2</sub>  
544 pycnometry, and the values obtained with N<sub>2</sub> were either equal or lower than those obtained with  
545 He. N<sub>2</sub> is a molecule with a kinetic diameter of 0.364 nm, whereas He is a monoatomic gas with a  
546 kinetic diameter of 0.26 nm (Breck, 1974). These differences thus suggest either that a significant  
547 fraction of extremely narrow pores, smaller than about 0.4 nm, were opened in some materials  
548 after immersion, or that He atoms were able to diffuse to poorly accessible porosity. It is useful to  
549 recall here that the diffusivity of He is typically 10 times higher than that of other common gases,  
550 and He can therefore migrate in many materials that remain impervious to other gases.

551 Plant matter can be considered as a composite composed of different macromolecules each  
552 having specific true density. The literature provides a true density of about 1541-1549 kg/m<sup>3</sup> for  
553 holocellulose, 1490-1800 kg/m<sup>3</sup> for hemicellulose (Ehrnrooth, 1984) and 1420-1460 kg/m<sup>3</sup> for  
554 cellulose (Sun, 2005) and 1335-1400 kg/m<sup>3</sup> for lignin. According to the chemical composition  
555 obtained by the Van Soest method, a rough estimation of the true density of hemp shiv can be  
556 deduced. The estimated values for both the L and LM samples range between 1420 and 1520  
557 kg/m<sup>3</sup>, and include the experimental result.


558 Concerning the size effect of the particles, the results show that the particle skeleton density is the  
559 same for all batches in a given state (raw or after immersion). It also appears that smaller particles  
560 are denser (in terms of particle density). This can be related to the original position of the particles  
561 in the stem, and that bigger particles coming from the lower part are more porous and thus less  
562 dense. In addition, the two automatic methods (Geopyc and Autotap) agree on the bulk density of  
563 the associated mixes, showing higher densities for smaller particles, which is directly related to a  
564 more compact stacking of the particles. However, this trend is not confirmed by the tomography  
565 approach in Fig. 5, where it is observed that there is no trend in density evolution as a function of  
566 particle volume.

567

568

### 3.1.2. Pore size distribution

569 The results of mercury intrusion are presented in three ways in Fig. 6.

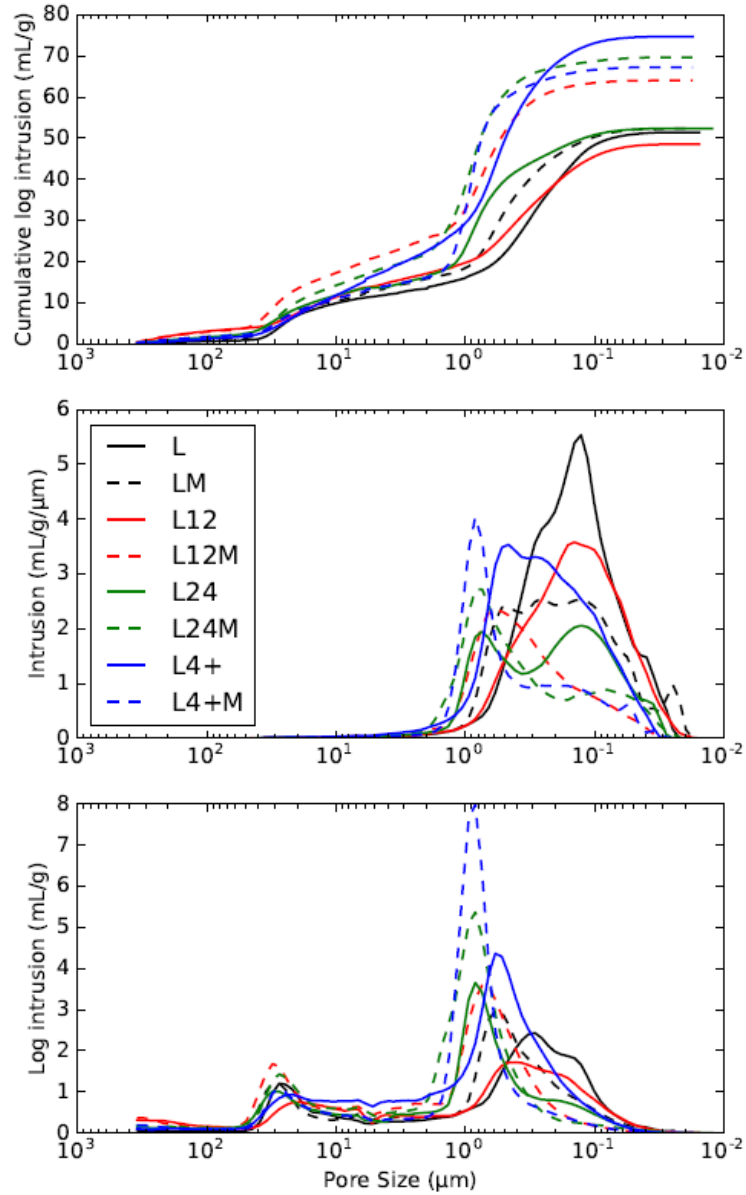

570

571 Figure 6. Mercury intrusion porosimetry : Cumulative intrusion in mL/g (top, the extrusion curves  
572 are not shown), differential intrusion in mL/g/μm (middle) and differential log intrusion in mL/g  
573 (bottom) as a function of pore size in μm

574

575 Pore size is presented here in decreasing order to underline the process of pressure increase  
576 during the measurement. The first representation is a cumulative curve of Hg Intrusion, where  
577 horizontal pseudo-plateaus represent different families of pores. The extrusion curves are not  
578 shown for clarity, but are perfectly horizontal indicating that all the intruded mercury has remained  
579 trapped in the porosity of the materials. In other words, all the mercury remains trapped because of  
580 the narrow necks giving access to most of the pores, which the mercury can only pass through  
581 under increasing pressure, but cannot cross in the other direction when the pressure decreases.  
582 This observation confirms the ink bottle-pore character of these materials, which is moreover a  
583 well-known morphological characteristic of the vascular network of wood and related plants. Only a  
584 fraction of the lumens indeed have an open side, and can therefore be directly intruded by  
585 mercury, but the vast majority of them are only accessible (and therefore intruded) by  
586 punctuations, typically an order of magnitude smaller in diameter. As a first approximation, the two  
587 steps observed on the intrusion curves therefore suggest that the pore size distribution is bimodal.  
588 Two other representations are differential and thus correspond to the pore size distributions. The  
589 log distribution is more responsive to larger pores (Meyer and Klobes, 1999), and clearly shows the  
590 bimodal character of the porosity, which cannot be so clearly seen in the middle of Fig. 6, due to  
591 the scale.

592 On this basis, these experimental results indicate two groups of pores:

- 593 . Pores between 10 and 50  $\mu\text{m}$ ;
- 594 . Pores between 0.02 and 2  $\mu\text{m}$ .

595 A parallel can be drawn between these groups and the families of pores existing in hemp particles.  
596 Vessels are the bigger pores in hemp and have a dimension around 50  $\mu\text{m}$  while tracheids have  
597 diameters of about 10-20  $\mu\text{m}$ , and pits have diameters of 1-2  $\mu\text{m}$  (Delannoy et al., 2018). However,  
598 as explained in section 2.2.3, it is important to recall that mercury intrusion tends to overestimate  
599 the volume related to small pores as soon as ink-bottle pores are present, which is more than likely  
600 the case here.

601 Indeed, not only is this geometry confirmed by the structure of the plant cells and the impossibility  
602 of extracting the mercury from them, but also by the fact that the samples observed after the  
603 mercury porosimetry test show no deformation, and that their weighing enables the intruded  
604 quantities measured by the device to be retrieved. This means that mercury under pressure did not  
605 alter the structure of the materials, which was to be expected given the presence of large pores  
606 and a very wide pore size distribution.


607 It also appears that the pores are systematically greater after immersion, which is visible through  
608 the shift of the plots towards larger pore sizes. In addition, the results show an increase of the total  
609 porosity after immersion, for all shiv except for the case of L4+. This is clearly correlated with N<sub>2</sub>  
610 and He pycnometry observations, and can be explained by the degradation (opening) of the  
611 microstructure after immersion.

## 612 **3.2. Physical properties of hemp shiv**

### 613 **3.2.1. Water sorption**

614 The GAB model satisfactorily fitted the experimental data ( $R^2 > 0.9996$  using parameters in Table  
615 6). Regarding the corresponding parameters, no clear difference was observed between raw and  
616 immersed samples over the whole range of relative humidity tested (*i.e.*, *L* and *LM* shiv, Fig. 7).



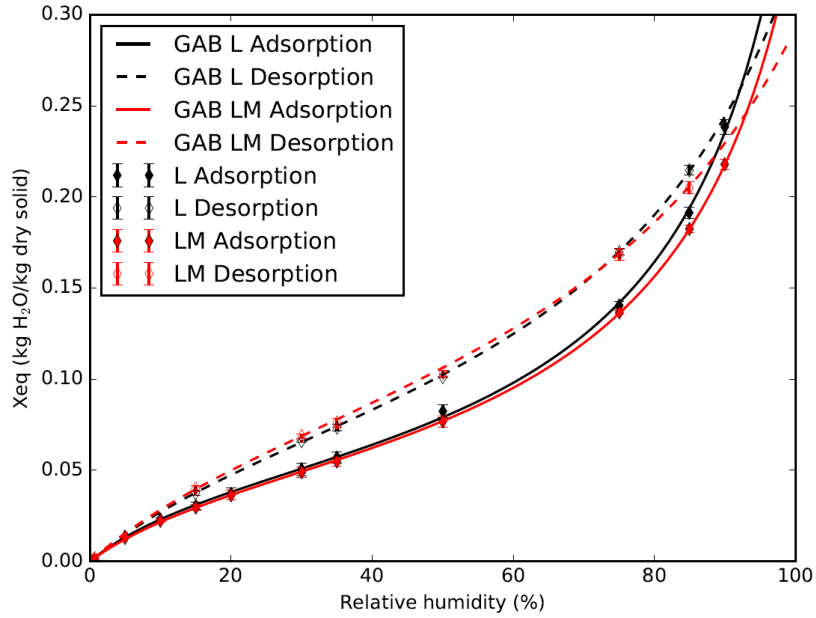

617

618 Figure 7. Adsorption and desorption isotherms of water on shiv L and LM

619

620 Table 6 : GAB model parameters (Eq. (9)),  $R^2$  are not detailed but are systematically greater than 0.99

Param	L	LM	L12	L12M	L24	L24M	L4+	L4+M
C (-)	6.9±1.0	6.2±0.8	7.4±0.7	6.5±0.7	6.6±0.9	6.6±0.8	6.2±0.7	6.7±0.8
K (-)	0.871±0.00	0.849±0.00	0.873±0.00	0.851±0.00	0.868±0.00	0.853±0.00	0.853±0.00	0.854±0.00
<b>Adsorption</b>	3	3	8	5	9	3	7	4
$X_m$ ( $10^{-3}$ d.b.)*	53±1	54±1	53±2	53±1	52±1	53±1	54±1	52±1
$E_{RMS}$ ( $10^{-3}$ d.b.)*	2	1	2	1	2	1	1	1
C (-)	5.2±0.6	5.2±0.9	5.3±0.2	5.1±0.6	5.0±0.2	5.0±0.6	4.8±0.4	5.0±0.8
K (-)	0.764±0.02	0.706±0.03	0.768±0.00	0.704±0.02	0.758±0.00	0.704±0.03	0.735±0.01	0.701±0.03
<b>Desorption</b>	3	6	6	8	6	1	9	7
$X_m$ ( $10^{-3}$ d.b.)*	83±5	93±7	82±0	93±6	82±3	93±6	88±3	93±8
$E_{RMS}$ ( $10^{-3}$ d.b.)*	2	2	1	2	2	2	2	2

621

\*d.b.: dry basis, in kg water/kg dry solid

### 622 3.2.2. Water absorption by immersion

623 Fig. 8a shows the kinetics of water absorption (WA) for the raw samples. As can be observed, the  
624 samples with a higher percentage of small particle size ( $L$ ) sorb water faster than the others when  $t$   
625  $\leq 480$  min. This behaviour could be related to the different tortuosity of the studied samples, which  
626 could lead to a higher absorption rate for samples with lower diffusional resistance (lower  
627 tortuosity). A similar effect was observed between treated samples.


628 Regarding the effect of immersion in water for 8 days on the absorption kinetics, it was observed  
629 that immersed samples had a lower capacity of water absorption compared to the raw ones (Fig.  
630 8b). This behaviour can be explained by the loss of mass after 8 days of immersion in water by  
631 leaching and/or by the increase in open porosity ( $\varphi_{N_2} = 1 - \frac{\rho_B}{\rho_{N_2}}$ ). As can be seen in Fig. 8b, raw  
632 samples lose more mass than samples previously immersed, indicating that those immersed have  
633 already lost mass before the water absorption kinetics analysis. This fact suggests that raw hemp  
634 shiv could have a higher number of hydrophilic compounds compared to the immersed ones due to  
635 the leaching effect, which led to a lower water retention capacity. For example, when equilibrium  
636 was achieved (2880 min)  $L$  sample had a WA of  $\approx 4.3$  kg water/ kg initial dry solid whereas the  $LM$   
637 sample had a lower value ( $\approx 3.9$  kg water/ kg initial dry solid). In addition, in Fig. 8b, it can also be  
638 seen that the rate of water absorption seems to be the same for both types of hemp shiv (constant  
639 difference between WA at each time for both types). Furthermore, it should be noted that even the  
640 samples that were previously immersed in water for 8 days continued to lose mass at 2880 min  
641 (which means 10 days of total immersion time). This result is in line with those previously published  
642 by Glé and Gourlay (2015).

643

644


645

646 a)

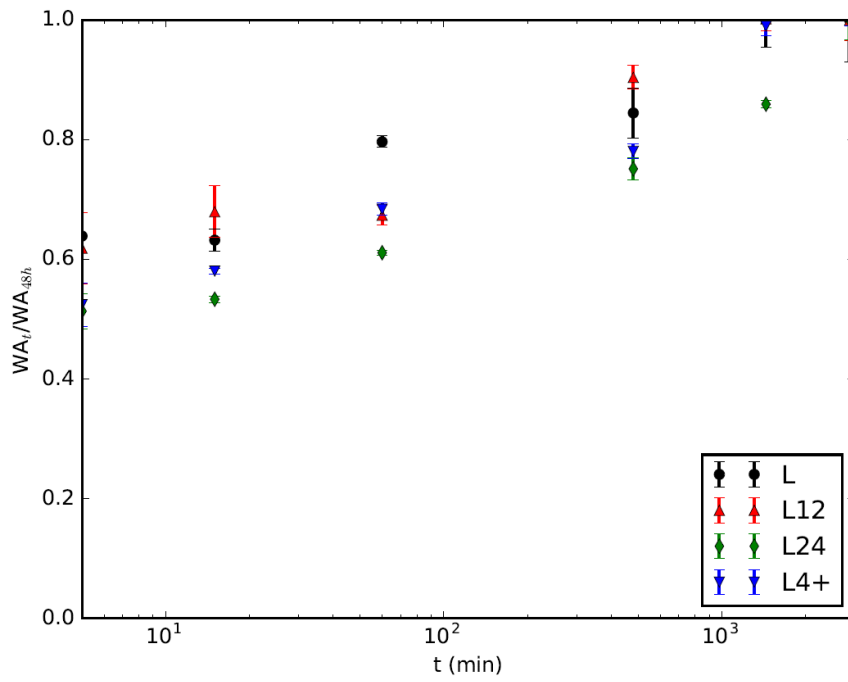

647

648 b)

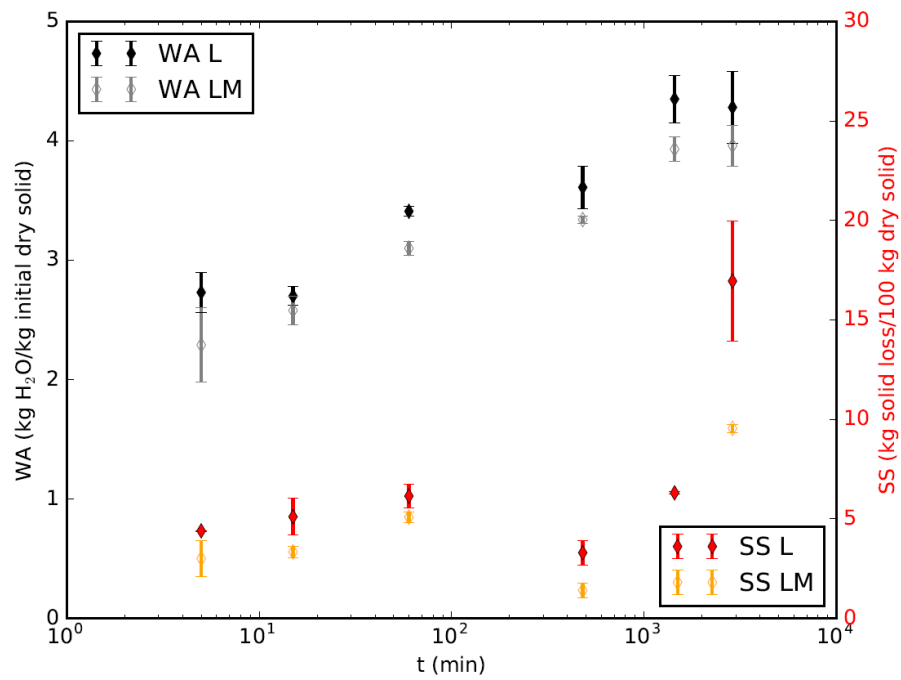

649

650 Figure 8. Water demand of hemp shiv. Comparison between raw shiv (a) and the effect of  
651 immersion on shiv (b). SS is the mass loss during water absorption defined in Eq. (10).

652

653 Finally, it should be noted that pre-immersed samples show a WA closer to the ideal behaviour  
654 than those not immersed. If it is considered that WA is the result of a complete filling of the open  
655 porosity of samples with water molecules, then:


$$656 \quad WA = \frac{\varphi_{P-open} * \rho_{water}}{(1 - \varphi_{P-open}) \rho_S} \quad (11)$$

657 Fig. 9 compares the theoretical WA calculated with Eq. (11) with those obtained experimentally at  
658 48 h. Results for immersed samples (*LM, L12M, L24M, L4+M*) are quite close to this theoretical  
659 behaviour, contrary to raw samples (*L, L12, L24, L4+*). Porosity, density and particle size  
660 distributions suggest that modified samples swelled irreversibly during their immersion treatment.  
661 The fact that the WA estimation of Eq. (11) underestimates the WA for raw particles suggests that  
662 these particles are swelling, in addition to filling their open porosity with water.

663 On this basis, it is possible to propose a new equation for the theoretical WA accounting for  
664 swelling:

$$665 \quad WA = \frac{\varphi_{P-open} * \rho_{water} * (1+s)^3}{(1 - \varphi_{P-open}) \rho_S} \quad (12)$$

666 with *s* the dimensional swelling of particles, estimated at about 15% due to the shift of size  
667 distribution curves from the raw samples to modified samples (see Table 2 – the same value has  
668 been taken for the thickness as data is missing). This corrected evolution is also plotted in Fig. 9  
669 and shows a better agreement with data on raw samples.

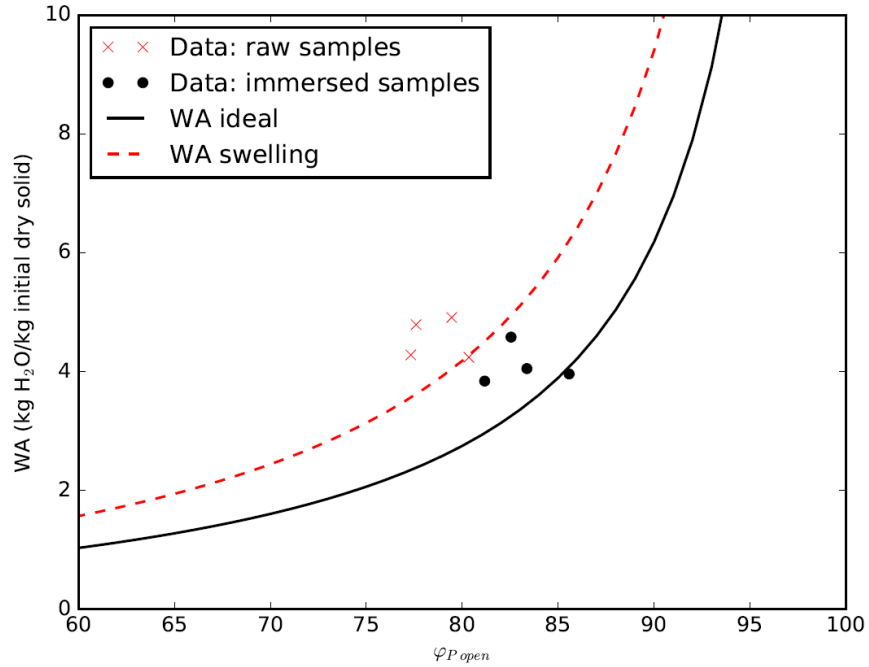

670  
 671 Figure 9. Comparison between measured water absorption and theoretical evolution as a function  
 672 of the open porosity of particles (WA ideal Eq. (11) and WA swelling Eq. (12)).

673

### 674 3.2.3. Compression behaviour

675 The mechanisms of granular packing compression are generally distinguished in three steps, as  
 676 first described by Seeling and Wülf (1946): 1. rearrangement of particles; 2. local elastic and  
 677 plastic deformation of particles and 3. fragmentation of particles and new rearrangement. For this  
 678 reason, Cooper and Eaton (1962) created a model that considers void filling that is dependent on  
 679 pore size, *i.e.* when rearrangement and filling of small voids occur or when plastic deformation and  
 680 fragmentation occur. Tronet et al. (2014) and a later study (Chiasson-Poirier et al., 2020) observe  
 681 that this model is in very close agreement with the compression behaviour of bulk hemp shiv (dry  
 682 or wet) and lime and hemp mixtures (dry or wet), considering only the two first steps (Eq. (13)).

683 
$$\frac{1-C_0/C}{1-C_0} = a_1 \exp(P_r/\sigma_{UP}) + a_2 \exp(P_d/\sigma_{UP}) \quad (13)$$

684 With  $C$  the compactness, or solid volume fraction achieved by the compressive stress  $\sigma_{UP}$  applied  
685 on the upper punch (negative value).  $a_1$  and  $a_2$  are constants. In fact, the constants  $a_1$  and  $a_2$  are  
686 not independent, as theoretically, when  $\sigma_{UP}$  tends towards  $-\infty$ ,  $C$  must tend towards 1. Then  $a_1 +$   
687  $a_2 = 1$ .  $C_0$  is the initial compactness, which can be considered as a “trimmed” bulk compactness  
688 ( $C_{B-trim}$ ) taking into account the experimental process of the present study (see section 2.3.3). In  
689 Cooper and Eaton's model,  $P_r$  and  $P_d$  are coefficients related to the pressure needed to perform  
690 the process that has the greatest probability of occurring; for instance, according to these authors,  
691  $P_r = 21$  MPa and  $P_d = 345$  MPa for compacting an alumina powder. This consistently higher value  
692 for  $P_d$  indicates that filling small voids requires considerably higher pressures than filling large  
693 ones. For shiv and lime-hemp mixtures,  $P_d$  values are also ten to twenty times higher than  $P_r$ , but  
694 these values are very low compared with metal or mineral powder beds, similarly to straw particles,  
695 wet or dry, which are very flexible and compressible (Mani et al., 2004) Both rearrangement and  
696 deformation phases are easier to discern for biomass resource particles than for rigid and frictional  
697 ones. In comparison, Tronet et al. (2014) found a  $P_r$  value of 450 kPa and  $P_d$  value of about 5 MPa  
698 for the compaction of dry shiv.

699 By applying the hypotheses of Cooper and Eaton's modelling, it could theoretically be possible to  
700 de-correlate the two phenomena (rearrangement and deformation), and write Eq. (14), which only  
701 considers the rearrangement phase:

$$702 \quad \frac{1-C_0/C_{r\infty}}{1-C_0} = \lim_{\sigma_{UP} \rightarrow -\infty} [a_1 \exp(P_r/\sigma_{UP})] = a_1 \quad (14)$$

703 Where  $C_{r\infty}$  would be the rearrangement occurring under infinite pressure, without any deformation  
704 of the particles. Considering a perfect layout of the particles in the packing under infinite pressure,  
705  $C_{r\infty}$  can be directly related to the particle density and the skeletal density. Similarly,  $C_0$  can be  
706 expressed with trimmed bulk density and skeletal density, Eq. (15):

$$707 \quad C_{r\infty} = \rho_P / \rho_S \quad ; \quad C_0 = C_{B-trim} = \rho_{B-trim} / \rho_S \quad (15)$$

708 Then Eq. (13) can be reformulated in terms of densities as follows (Eq. (16)):

$$709 \quad \rho = \left[ \frac{1 - \exp(P_r/\sigma_{UP})}{\rho_{B-trim}} + \frac{\exp(P_r/\sigma_{UP}) - \exp(P_d/\sigma_{UP})}{\rho_P} + \frac{\exp(P_d/\sigma_{UP})}{\rho_S} \right]^{-1} \quad (16)$$

710 The different samples of shiv were compressed using the protocol described in section 2.3.3 (Fig.  
711 10a). The experimental curves are clearly gathered by shiv type (“pristine”  $Lxy$  or “modified”  $LMxy$ )  
712 and these bundles are distinct for compressive stresses higher than 15 MPa. At lower stresses, the  
713 initial bulk density and internal and wall-die frictions could dramatically affect the packing’s  
714 compressive behaviour, as shown by Tronet et al., (2014) and Chiasson-Poirier et al. (2020). By  
715 zooming in on the experimental curves (Fig. 10b), it appears that the coarser the particles, the  
716 easier the compaction: for example, in the deformation step,  $L4+$  reaches a given density for a  
717 much lower pressure than  $L12$ , even if its initial density is lower. This can be due to two  
718 phenomena: small particles induce more particle/particle contacts than big ones and are stiffer in  
719 bending. However, modified samples ( $LMxy$ ) reached lower densities, even though they are  
720 generally larger than pristine particles ( $Lxy$ ). This is due to their much lower particle density (about  
721 -20%) induced by the degradation of some internal cell walls (see Figure 4 and Table 5).


722 The experimental results “L” and “LM” are compared to the model of Eq. (16), taking the average  
723 density values of Table 5:  $\rho_S=1454 \text{ kg/m}^3$  for each sample (column “skeleton, He<sup>\*\*</sup>”);  $\rho_{B-trim}=99$   
724  $\text{kg/m}^3$  for L samples and  $82 \text{ kg/m}^3$  for LM samples (column “packing, trimmed”);  $\rho_P=310 \text{ kg/m}^3$  for L  
725 samples and  $245 \text{ kg/m}^3$  for LM samples (column “particle, Geopyc”). The only two fitting  
726 parameters of the model are  $P_r$  and  $P_d$ . The same value was taken for  $P_r=0.53 \text{ MPa}$ , while the  $P_d$   
727 values are slightly different for the two shiv samples:  $P_d=2.5 \text{ MPa}$  for “L” group, and  $2 \text{ MPa}$  for “LM”  
728 group. These values are of the same order of magnitude as those of Tronet et al. (2014).

729

730


731

732 a)

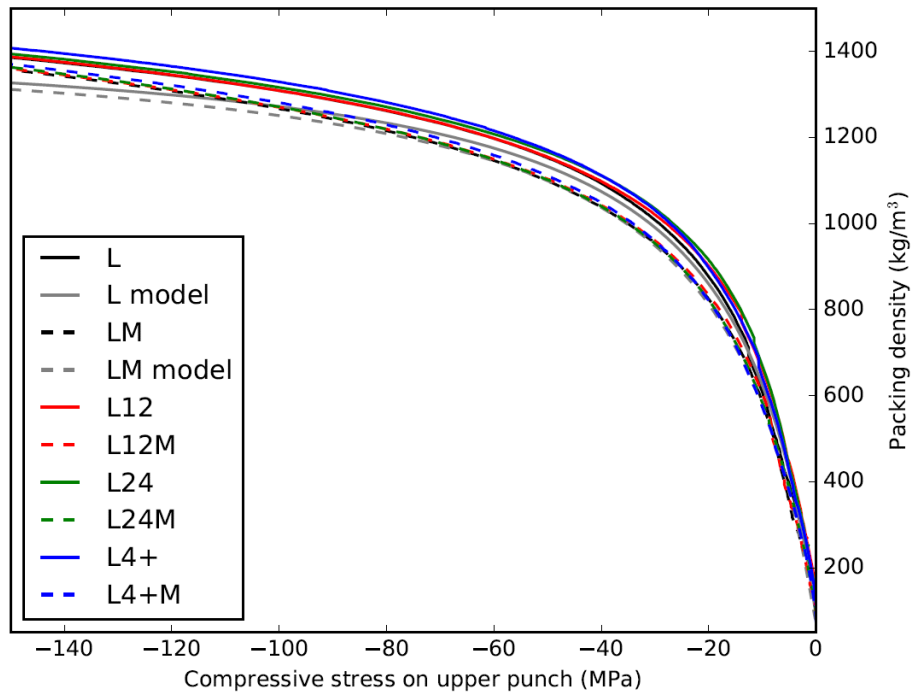

733

734 b)

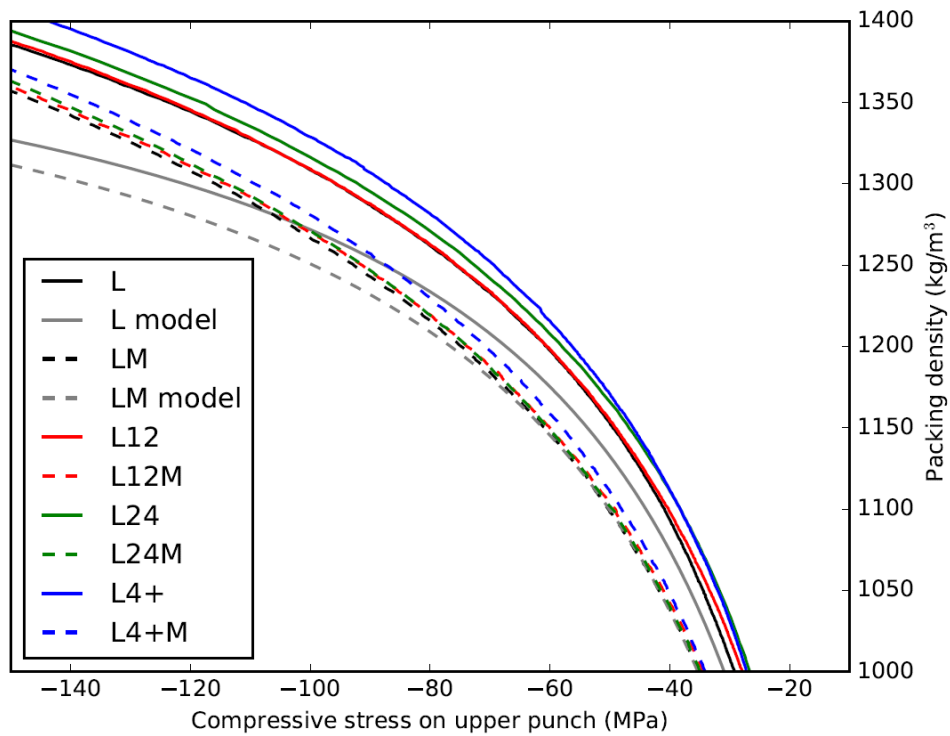

735

736 Figure 10. Left: experimental curves and the Cooper & Eaton model with  $P_r=0.53$  MPa (model L:  
737  $P_d=2.5$  MPa,  $\rho_S=1454$  kg/m<sup>3</sup>,  $\rho_{B-trim}=100$  kg/m<sup>3</sup>,  $\rho_P=310$  kg/m<sup>3</sup>; model LM:  $P_d=2$  MPa,  $\rho_S=1454$   
738 kg/m<sup>3</sup>,  $\rho_{B-trim}=80$  kg/m<sup>3</sup>,  $\rho_P=245$  kg/m<sup>3</sup>); Right: zoom of the experimental values.




739 A fairly close agreement between the model and the experiments is observed, up to a compressive  
740 stress of about 70 MPa. In fact, to transform Eq. (14) to Eq. (16), the implicit assumption that a  
741 compactness of 1 corresponds to a density  $\rho_S$  was performed. This assumption does not take into  
742 account the compressibility of the skeleton's cell wall itself. To summarise, the successive  
743 phenomena that drive the packing behaviour in the die are firstly a rearrangement that should be  
744 achieved when  $\rho = \rho_P$ . Then, the deformation of the particles drives the compressive behaviour  
745 (bending at the macroscale; buckling of the cell walls and closing of the intra-porosity at the  
746 microscale) up to a density level for which the volume deformation of the cell walls themselves can  
747 no longer be neglected. The model should then be completed by considering  $\rho_S$ , which depends on  
748 the compressive stress:

$$749 \quad \rho_S = \rho_{S0} (1 + \sigma_{UP} / K_S) \quad (17)$$

750 Where  $\rho_{S0}$  is the skeletal density in atmospheric conditions (values of Table 3), and  $K_S$  is the  
751 elastic bulk modulus of the cell walls. Beaugrand et al. (2014) measured indentation moduli from  
752 nanoindentation on the woody core of hemp stems around 9 GPa. The bulk modulus should be of  
753 the same order of magnitude. The curves of models *L* and *LM* were drawn again, varying the  
754 skeletal density as a function of compressive stress (Eq. (17)). A bulk modulus of 3.8 GPa gave the  
755 best agreement with the experimental values (Fig. 11).

756

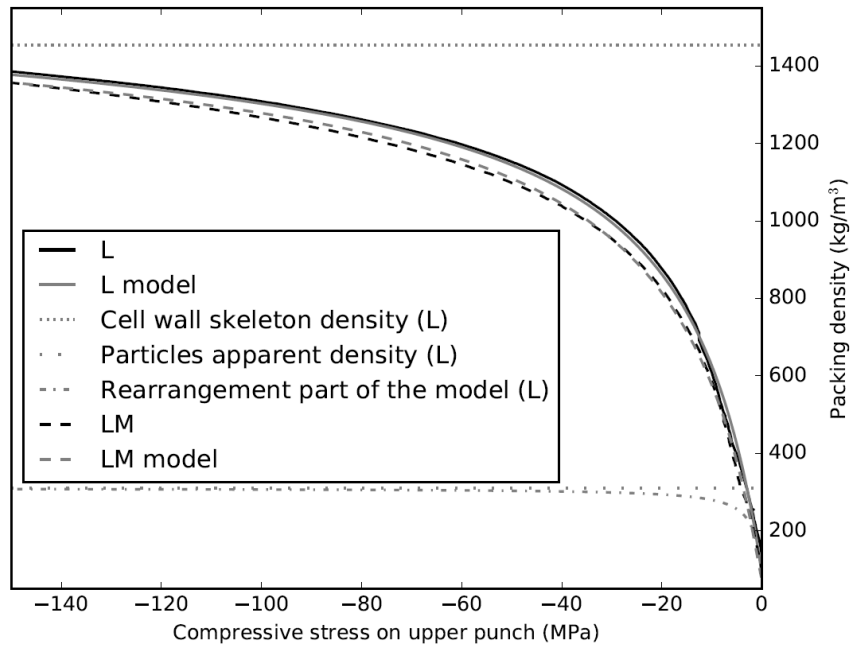

757  
 758 Figure 11. Compression model and experiments, considering that the cell wall density depends on  
 759 compressive stress ( $K_s = 3.8$  GPa).

760  
 761 The rearrangement part of the Cooper and Eaton model is also drawn in Fig. 11. This curve clearly  
 762 shows that the rearrangement phase is the driving phenomenon at the beginning of the  
 763 compression, and is rapidly achieved. The whole model tends asymptotically towards the cell walls  
 764 skeletal density.

765 The rearrangement pressure  $P_r$  found is the same for all shiv samples, and is quite similar to the  
 766 value found by Tronet et al. (2014). This pressure is driven by several parameters, mainly inter-  
 767 particle porosity and inter-particle friction. This result indicates that, irrespective of the type of shiv,  
 768 the porosity and the nature of the outer cell walls are sufficiently similar to drive the rearrangement  
 769 phase in the same way and with the same pressure levels. On the contrary, the deformation  
 770 pressure  $P_d$  is related to the stiffness of the particle (in flexion and compression), *i.e.*, to the particle  
 771 density. This explains why the  $P_d$  value is lower for LM samples than for L samples.

### 772 3.2.4. Thermal behaviour

773 The thermal models usually proposed for a diphasic granular packing and formulated in terms of  
774 densities are written in Eq. (18) to (21) :

775 - Series Model:

$$776 \quad \lambda_B = \frac{1}{1/\lambda_{air} + \frac{\rho(1/\lambda_S - 1/\lambda_{air})}{\rho_S}} \quad (18)$$

777 - Parallel Model:

$$778 \quad \lambda_B = \lambda_{air} + \frac{\rho}{\rho_S}(\lambda_S - \lambda_{air}) \quad (19)$$

779 - Krischer Model (Dietrich et al., 2010): (semi empirical model, mixing series and parallel  
780 (weighted harmonic average of the Series and Parallel models-  $0 < f < 1$ )

$$781 \quad \lambda_B = \left[ f * (1/\lambda_{air} + \frac{\rho(1/\lambda_S - 1/\lambda_{air})}{\rho_S}) + (1 - f)/\lambda_{air} + \frac{\rho}{\rho_S}(\lambda_S - \lambda_{air}) \right]^{-1} \quad (20)$$

782 - Self Consistent Model (Bruggeman, 1935):

$$783 \quad \left( \frac{\rho}{\rho_S} \right) \frac{\lambda_S - \lambda_B}{\lambda_S - 2\lambda_B} + \left( 1 - \frac{\rho}{\rho_S} \right) \frac{\lambda_{air} - \lambda_B}{\lambda_{air} - 2\lambda_B} = 0 \quad (21)$$

784

785 Where  $\lambda_B$ ,  $\lambda_S$  and  $\lambda_{air}$  are respectively the thermal conductivity of the packing at a given density,  
786 that of the cell-wall skeleton and that of air ( $\lambda_{air} = 26 \text{ mW.m}^{-1}\text{K}^{-1}$ ).

787 Considering the internal structure of hemp particles, *i.e.*, of almost only longitudinal capillaries, it is  
788 theoretically possible to correlate the conductivity along a particle  $\lambda_{P//}$  and the conductivity of the

789 cell walls  $\lambda_S$ , using a parallel model:


$$790 \quad \lambda_{P//} = \lambda_{air} + \frac{\rho_P}{\rho_S}(\lambda_S - \lambda_{air}) \quad (22)$$

791

792 Pierre and Carin (2019) measured the conductivity of individual hemp shiv particles by infrared  
793 thermography. They found  $\lambda_{P//} = 124 \pm 23 \text{ mW.m}^{-1}\text{K}^{-1}$  on particles of density  $\rho_P = 265 \pm 15 \text{ kg.m}^{-3}$ .

794 Applying Eq. (22) with  $\rho_S = 1454 \text{ kg.m}^{-3}$  and  $\lambda_{air} = 26 \text{ mW.m}^{-1}\text{K}^{-1}$  gives a value  $\lambda_S = 564 \pm 126 \text{ mW.m}^{-1}$

795  $^1\text{K}^{-1}$  for the conductivity of the cell wall skeleton. The models of Eq. (18) to (21) are applied with this  
 796 value, and plotted in Fig. 12.

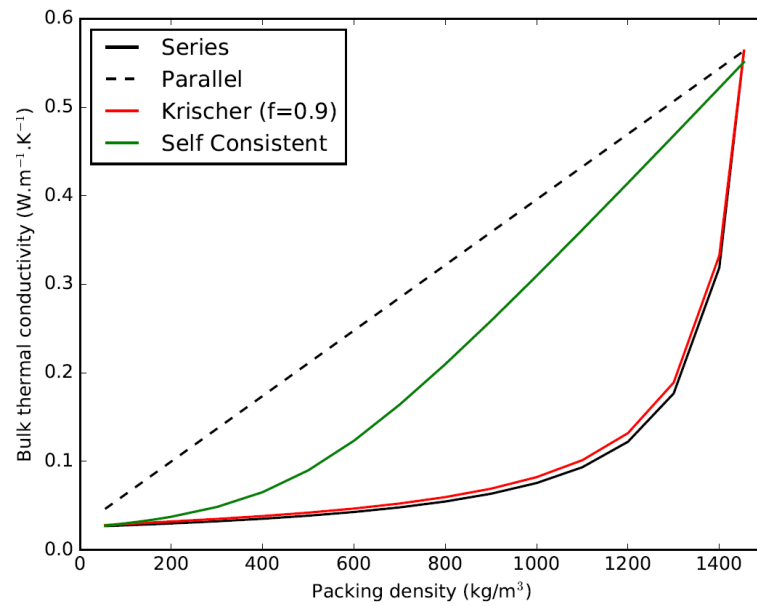

797  
 798 Figure 12. Evolution of the theoretical conductivity of hemp shiv packing, according to four models  
 799 of the literature ( $\rho_S=1454 \text{ kg.m}^{-3}$ ;  $\lambda_{\text{air}}=26 \text{ mW.m}^{-1}\text{K}^{-1}$ ;  $\lambda_S=564 \text{ mW.m}^{-1}\text{K}^{-1}$ )

800  
 801 It can be observed that, except for the Parallel Model, the bulk conductivity varies very slightly  
 802 between  $60$  and  $160 \text{ kg.m}^{-3}$ , *i.e.*, the maximum packing density that can be reached by hand on dry  
 803 shiv (see compacted bulk densities, Table 5).

804 Another way to evaluate the thermal conductivity of a hemp shiv packing is to consider the particle  
 805 conductivity in the models and develop a 2-scale approach. The difficulty is that the hemp particles  
 806 are orthotropic, or at least transverse isotropic from a thermal point of view. In any case, by  
 807 applying the Series model to a particle, the transverse conductivity of a particle can be estimated:


808 
$$\lambda_{P\perp} = \frac{1}{1/\lambda_{\text{air}} + \frac{\rho_P(1/\lambda_S - 1/\lambda_{\text{air}})}{\rho_S}} = 31 \text{ mW.m}^{-1}\text{K}^{-1} \quad (23)$$

809 This value is certainly a lower boundary of  $\lambda_{P\perp}$ , as it considers perfectly parallel layers of air and  
 810 solid, without any thermal bridges. Similar measurements on balsa (Carré and Le Gall, 1990;  
 811 Pierre and Carin, 2019), in the longitudinal and transverse directions showed a ratio of about  $\frac{1}{2}$   
 812 between longitudinal conductivity and transverse conductivity. Considering that the skeleton's

813 structures of balsa and hemp shiv are similar, this could lead to  $\lambda_{p\perp} \sim 62 \text{ mW}\cdot\text{m}^{-1}\text{K}^{-1}$ . In her PhD  
 814 thesis, Cerezo (2005) deduced a mean value of  $102 \text{ mW}\cdot\text{m}^{-1}\text{K}^{-1}$  for hemp shiv particles using an  
 815 inverse analysis applied to her experimental values on lime and hemp concrete with a spherical  
 816 self-consistent model. This value lies between  $\lambda_{p\perp}$  (Eq. (23)) and  $\lambda_{p//}$ , which is consistent. In order  
 817 to take into account the transverse isotropy of particles, the Krischer model can be reformulated  
 818 (Eq. (24)).

$$819 \quad \lambda_B = \left[ f * \left( \frac{1}{\lambda_{air}} + \frac{\rho (1/\lambda_{p\perp} - 1/\lambda_{air})}{\rho_P} \right) + (1 - f)/\lambda_{air} + \frac{\rho}{\rho_P} (\lambda_{p//} - \lambda_{air}) \right]^{-1} \quad (24)$$

820 In a loose packing state, the particles are almost randomly oriented (geometric isotropy of the  
 821 packing of particles). But under compression, the particles are increasingly oriented to lie flat, and  
 822 tend towards a transverse isotropy, as shown by Williams et al. (2016, 2017) on lime and hemp  
 823 composites. The weight coefficient  $f$  in Eq. (24) can then vary with the overall orientation of the  
 824 particles, from an isotropic behaviour of the loose packing ( $f=0.5$ ) towards a packing of almost  
 825 parallel layers at the very end of the rearrangement phase (see section 3.2.3) for which  $f$  is  
 826 chosen equal to 1. A linear evolution of  $f$  as a function of packing density is proposed. The model  
 827 of Eq. (24) is then plotted in Fig. 13, and compared with the experimental results.

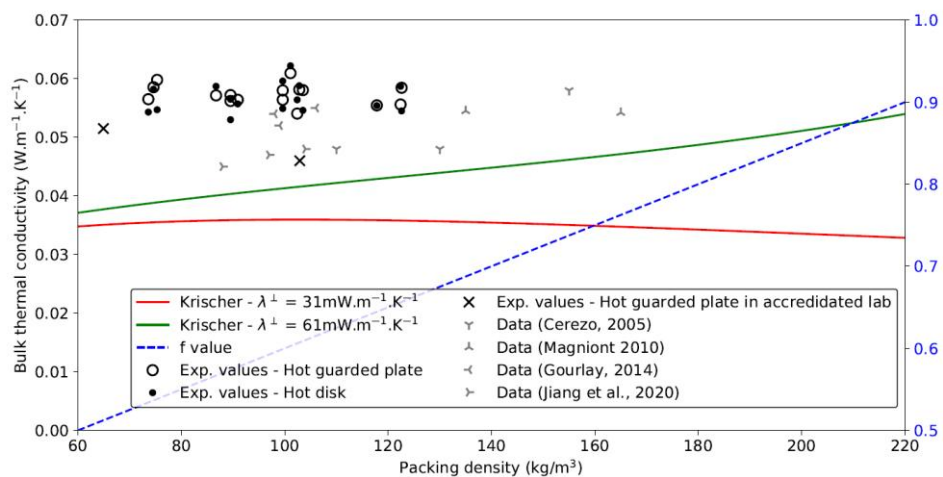

828

829 Figure 13. Krischer Model, considering the anisotropy induced by compaction ( $\rho_p=265\text{kg.m}^{-3}$  ;  
830  $\lambda_{\text{air}}=26 \text{ mW.m}^{-1}\text{K}^{-1}$  ;  $\lambda_{p//}=124 \text{ mW.m}^{-1}\text{K}^{-1}$  ; “Series Model” :  $\lambda_{p\perp}=31 \text{ mW.m}^{-1}\text{K}^{-1}$  “Balsa ratio” :  $\lambda_{p\perp}=62$   
831  $\text{mW.m}^{-1}\text{K}^{-1}$ )

832 The experimental values of the present study are not close to those of the modelling, probably due  
833 to three main reasons:

- 834 - at low densities, convection and radiation could affect the thermal properties. This  
835 should not be predominant in the range of density and sample thickness considered  
836 here, but the proposed model overlooks these phenomena;
- 837 - the values taken from (Pierre and Carin, 2019) were not obtained in the same room  
838 conditions and on the same shiv than in the present study, and strong assumptions  
839 were made on transverse values of the thermal conductivity of particles, and on the  
840 weight coefficient  $f$ ;
- 841 - the measurement method and the sample conditioning can affect the experimental  
842 results, as shown by Colinart et al. (2019).

843 The real average thermal conductivity of the skeleton could be estimated by an inverse analysis.  
844 However, this approach is risky because the experimental data are highly scattered. A clear  
845 conclusion cannot be drawn regarding the best model for the thermal conductivity of hemp shiv,  
846 due to the large scatter in the experimental data and the range of uncertainty in the model input  
847 data. However, such an approach illustrates how porosity can be used in physical models to  
848 understand in more depth the thermal behaviour of hemp shiv packing.

### 849 3.2.5. Acoustic properties

850 The densities resulting from the acoustic characterisation are presented in Table 5. Compared to  
851 Geopyc and Hg-intrusion particle density values, it appears that acoustic densities are

852 systematically much higher. However, the acoustic densities show exactly the same tendencies as  
853 the other methods concerning particle size and immersion effects, described above in 3.1.1.


854 These observations indicate that the acoustic density does not correspond to the particle density.  
855 Practically, this means that acoustic dissipation occurs not only in interparticle porosity, but also in  
856 part of the intra-particle porosity. The pore size distribution measured by mercury intrusion and  
857 presented in Fig. 5 highlighted the existence of two groups of pores. It is thus likely that at least a  
858 part of the bigger pores (measuring about 10 to 50  $\mu\text{m}$ ) also contribute to the sound dissipation in  
859 hemp shiv.

860 To develop this theory, a comparison was made between acoustic data and modelling approaches  
861 based on four hypotheses:

- 862 - H1: Double porosity without coupling as described in (Glé et al., 2012), 1 scale of porosity -  
863  $\varphi_{acou}$ ;
- 864 - H2: Double porosity without coupling: 1 scale of porosity -  $\varphi_I$ : This hypothesis is similar to  
865 the first approach but considers that only inter-particle pores participate in acoustic  
866 dissipation.  $\varphi_I = 1 - \frac{\rho_B}{\rho_P}$  is different than  $\varphi_{acou}$  and is deduced here from the Geopyc  
867 envelope density;
- 868 - H3: Double porosity with coupling: 2 scales -  $\varphi_I + \varphi_P$ : here, all open pores participate in the  
869 dissipation,  $\varphi_I$  (deduced from the Geopyc particle density) as well as  $\varphi_P$  calculated as the  
870 difference (in volume) between the open porosity  $\varphi_{N_2} = 1 - \frac{\rho_B}{\rho_{N_2}}$  and the interparticle  
871 porosity  $\varphi_I$ , so that  $\varphi_P = \frac{\varphi_{N_2} - \varphi_I}{1 - \varphi_I}$ . The model presented by (Olny and Boutin, 2003) is  
872 applied.
- 873 - H4: Partial double porosity with coupling: 2 scales -  $\varphi_I + \eta \times \varphi_P$ : This case is a derivation of  
874 the previous case, where  $\eta \times \varphi_P$  corresponds to the portion of  $\varphi_P$  participating in the sound  
875 dissipation, a portion fixed at 50%.

876


877 These four hypotheses are illustrated by the schematic given in Fig. 14.

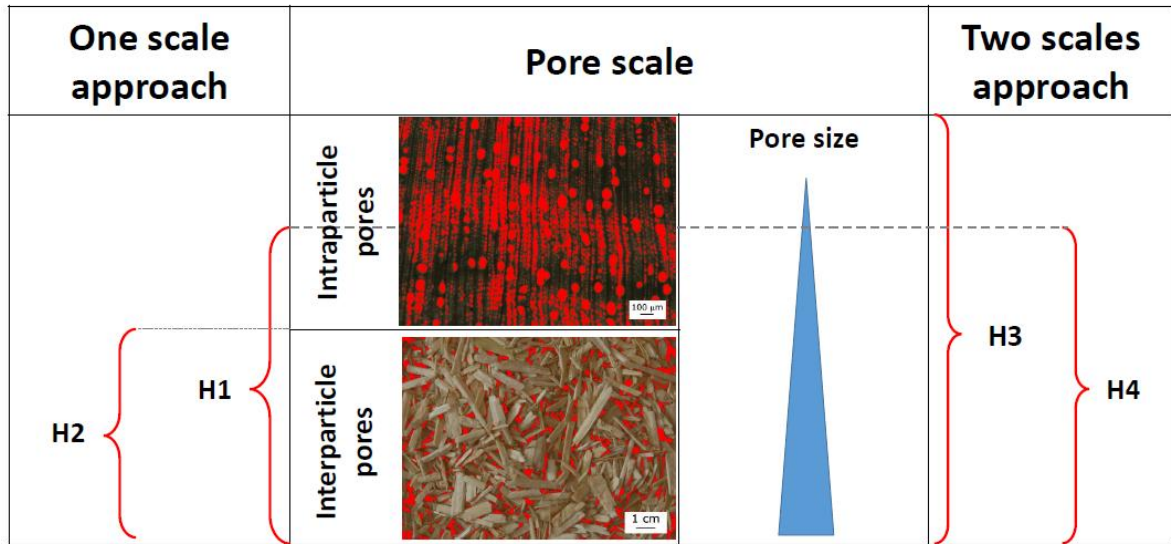

878

879 Figure 14. Illustration of the four modelling assumptions

880

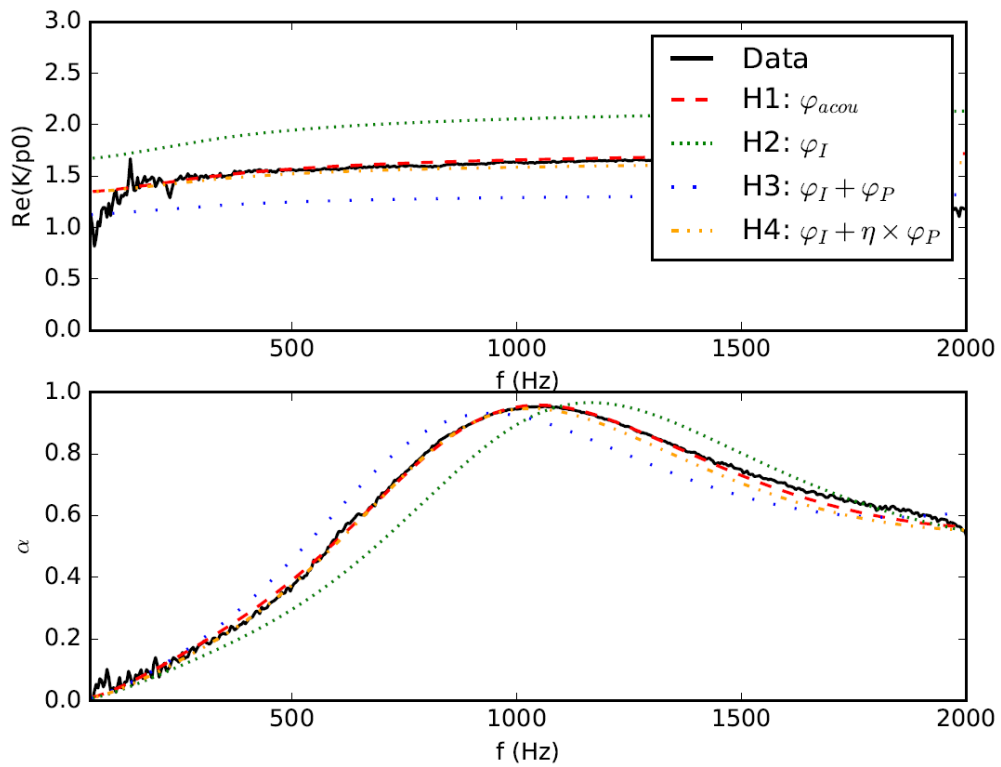

881

882 Figure 15. Comparison between acoustic data for hemp shiv L12 ( $130 \text{ kg.m}^{-3}$ ) and modelling for  
 883 the real part of the bulk modulus (top) and for the sound absorption coefficient (bottom)



884

885 The real part of the bulk modulus is a property of the material that is related to thermal effects in  
886 acoustic dissipation (Allard and Atalla, 2009). This property is mainly related to the porosity of the  
887 material, and ranges between two asymptotic values,  $K = \frac{p_0}{\phi}$  (at low frequency) and  $K = \gamma \frac{p_0}{\phi}$  (at  
888 high frequency). This acoustic data as well as sound absorption  $\alpha$  are plotted versus frequency  
889 and compared to experimental data for hemp shiv L12 ( $130 \text{ kg}\cdot\text{m}^{-3}$ ) in Fig. 15. It can be observed  
890 that two of the four hypotheses proposed can be clearly distinguished from the reference data. The  
891 approach based on  $\phi_I$  only gives an overestimate of  $Re(K)$ . On the contrary, the approach based  
892 on  $\phi_I + \phi_P$  underestimates these data. The reason is that the contributing porosity is respectively  
893 under- and overestimated with these hypotheses. In this context, the partial double porosity  
894 approach (H4) with coupling seems to be satisfactory. The reference approach (H1, described by  
895 Glé et al. (2012)) is also close to the data, but relies on an acoustic inversion of the effective  
896 porosity.

897 The results regarding the sound absorption coefficient are in line with the previous remarks. The  
898 two best approaches predict  $\alpha$  with a deviation lower than 5% compared to the data.

## 899 4. Conclusion

900 This paper aimed to investigate the densities and microstructures of plant particles used for bio-  
901 based building applications. It combines experimental determination of the density at three scales,  
902 *i.e.* packing, particle and skeleton of hemp shiv. Analyses were carried out regarding the  
903 implications of these characteristics on the physical behaviour of the material. The work focused on  
904 eight shiv having the same origin but different particle size distribution and aging.

905 The cross-analysis of different methods proved to be relevant to fully characterise these materials.  
906 Powder pycnometry appeared to be one of the most efficient and representative methods to

907 characterise particle density. Mercury intrusion porosimetry enabled the validation of the range of  
908 densities but with stronger limitations due to the "ink-bottle" effects expected for plant particles.  
909 Finally, X-ray computed tomography enabled the characterisation of the particles individually and  
910 the validation the range of data from the two other methods. Because image acquisition and  
911 processing are very time-consuming, it was therefore not appropriate for the statistical and  
912 systematic assessment of particle density, but more suited for local microstructure  
913 characterisation.

914 It has been demonstrated that smaller particles have higher packing and particle densities,  
915 probably due to the original position of particles in the stems. In addition to this, particles aged  
916 through immersion in water presented a significant evolution of their microstructure, leading to  
917 lower packing and particle densities and higher skeletal density. This evolution is related to the  
918 combined effects of particles swelling with the opening of intra-particle pores. It would be  
919 interesting to complement these results by direct tomographic observations at high resolution to  
920 characterise the morphology and the evolution of porosity.

921 The links of these densities with the physical properties were explored. Correlations were found  
922 between water absorption and open porosity, compression behaviour and the three scales of  
923 densities, and between acoustic dissipation and intra- and inter-particle porosities. Theoretical links  
924 also exist with water adsorption and thermal dissipation, but they could not be demonstrated  
925 experimentally.

926 These results thus facilitate an interesting advance in the knowledge of the microstructure of plant  
927 particles, which could be used to optimise the formulation of materials derived from hemp shiv,  
928 identify their extreme limits in terms of density, and propose better modelling of their physical  
929 performance in buildings.

## 930 5. Acknowledgments

931 This study is a part of the ECO-TERRA project (Development of light earth construction materials  
932 for efficient green buildings), with the support of ADEME.

933 The authors would like to thank Philippe Gadonneix (Université de Lorraine, IJL) for additional  
934 measurements using Autotap, Geopyc, Accupyc and Autopore devices, and Patrick Aimedieu  
935 (Laboratoire Navier) for his valuable advice on the acquisition of the X-ray tomographic images.

## 936 6. References

937 NF V 18-122 - Aliments des animaux - Détermination séquentielle des constituants pariétaux -  
938 Méthode par traitement aux détergents neutre et acide et à l'acide sulfurique.

939 Allard, J.F., Atalla, N., 2009. Propagation of sound in porous media: Modelling sound absorbing  
940 materials, second edition. Wiley.

941 Amziane, S., Arnaud, L. (Eds.), 2012. Bio-aggregate-based Building Materials: Applications to  
942 Hemp Concretes, Wiley.

943 Amziane, S., Collet, F. (Eds.), 2017. Bio-aggregates Based Building Materials, Vol. 23 of RILEM  
944 State-of-the-Art Reports, Springer Netherlands, Dordrecht.

945 Amziane, S., Collet, F. (Eds.), 2018. Bio-aggregates Based Building Materials: State-of-the-Art  
946 Report of the RILEM Technical Committee 236-BBM.

947 Beaugrand, J., Nottez, M., Konnerth, J., Bourmaud, A., 2014. Multiscale analysis of the structure  
948 and mechanical performance of woody hemp core and the dependence on the sampling location,  
949 Ind. Crop. Prod. 60, 193-204.

950 Bennai, F., El Hachem, C., Abahri, K., Belarbi, R., 2018. Microscopic hydric characterization of  
951 hemp concrete by X-ray microtomography and digital volume correlation, *Constr. Build. Mater.* 188,  
952 983-999.

953 Van den Berg, C., Bruin, S., 1981. Water activity and its estimation in food systems. *Water Activity:  
954 Influences on Food Quality*, L.B. Rockland & G.F. Stewart, 147–177. Academic Press, New York.

955 Breck, D., 1974. *Zeolite Molecular Sieves*, 1 ed.; John Wiley & Sons: New York.

956 Brisard, S., Serdar, M., Monteiro, P.J.M., 2020. Multiscale X-ray tomography of cementitious  
957 materials: A review. *Cem. Concr. Res.* 128, 105824.

958 Bruggeman, D., 1935. Berechnung verschiedener Physikalischer Konstanten von heterogenen  
959 Substanzen, *Annalen Physik* 24, 636-679.

960 Cappelletto, P., Brizzi, M., Mongardini, F., Barberi, B., Sannibale, M., Nenci, G., Poli, M., Corsi, G.,  
961 Grassi, G., Pasini, P., 2001. Italy grown hemp yield, composition and cannabinoid content. *Ind.  
962 Crop. Prod.* 13 (2), 101-113.

963 Carré, P., Le Gall, R., 1990. Définition et détermination des conductivités thermiques dans les  
964 structures C.V.R. – balsa, *Rev. Gén. Therm. Fr.* 340, 211–215.

965 Castel, Y., Amziane, S., Sonebi, M., 2016. Durabilité du béton de chanvre : résistance aux cycles  
966 d'immersion hydrique et séchage. 1ère Conférence EuroMaghrébine des BioComposites,  
967 Marrakech, Maroc.

968 Cerezo, V., 2005. Propriétés mécaniques, thermiques et acoustiques d'un matériau à base de  
969 particules végétales: approche expérimentale et modélisation théorique, PhD thesis, INSA,  
970 ENTPE, Lyon.

971 Ceyte, I., 2008. Béton de chanvre, définition des caractéristiques mécaniques de la chènevotte,  
972 Master thesis, ENTPE.

973 Chiasson-Poirier, L., Lecompte, T., Hellouin de Menibus, A., 2020. Static and long term  
974 compression behavior of hemp shiv for floating floor application, *Constr. Build. Mater.* 268, 121220.

975 Collet, F., Prétot, S., 2014. Thermal conductivity of hemp concretes: variation with formulation,  
976 density and water content. *Constr. Build. Mater.* 65, 612-619.

977 Colinart, T., Vincelas, T., Lenormand, H., Hellouin de Menibus, A., Hamard, E., Lecompte, T.,  
978 2019. Hygrothermal properties of light-earth building materials. *J. Build. Eng.* 29, 101134.

979 Cooper, A.R., Eaton, L.E., 1962. Compaction behavior of several ceramic powders. *J. Am. Ceram.*  
980 *Soc.* 45 (3), 97-101.

981 Delannoy, G., Marceau, S., Glé, P., Gourlay, E., Gueguen-Minerbe, M., Diafi, D., Nour, I.,  
982 Amziane, S., Farcas, F., 2018. Aging of hemp shiv used for concrete. *Mater. Des.* 160, 752–762.

983 Delannoy, G., Marceau, S., Glé, P., Gourlay, E., Gueguen-Minerbe, M., Diafi, D., Amziane, S.,  
984 Farcas, F., 2020. Impact of hemp shiv extractives on hydration of Portland cement. *Constr. Build.*  
985 *Mater.* 244, 118300.

986 Dietrich, B., Schell, G., Bacharsky, E.C., Oberacker, R., 2010. Determination of the thermal  
987 properties of Ceramic sponges, *Int. J. Heat Mass Transf.* 53, 198-205.

988 Ehrnrooth, E.M.L., 1984. Change in Pulp Fibre Density With Acid-Chlorite Delignification, *J. Wood*  
989 *Chem. Technol.* 4 (1), 91-109.

990 Evrard, A., 2008. Transient hygrothermal behavior of Lime-Hemp Materials, Ph.D. thesis,  
991 Université Catholique de Louvain.

992 Fares, H., 2014. Paramètres de composition des mélanges de particules de chènevotte pour  
993 l'élaboration de béton de chanvre, Montpellier, France

994 Fotsing, E.R., Lecompte, T., Ross, A., 2017. Acoustic properties of lime/hemp concrete produced  
995 by compression molding, Second ICBBM, Clermont-Ferrand.

- 996 Glé, P., Gourdon, E., Arnaud, L., 2012. Modelling of the acoustical properties of hemp particles.  
997 Constr. Build. Mater. 37, 801-811.
- 998 Glé, P., 2013. Acoustique des matériaux du bâtiment à base de fibres et particules végétales –  
999 Outils de caractérisation, modélisation et optimisation. PhD Thesis, MEGA ENTPE, Vaulx-en-Velin.
- 1000 Glé, P., Gourlay, E., 2015. Rapport de recherche MABIONAT, Étude de l'influence de la teneur en  
1001 eau et du vieillissement sur les performances acoustiques et thermiques des matériaux  
1002 biosourcés.
- 1003 Gourlay, E., 2014. Caractérisation expérimentale des propriétés mécaniques et hygrothermiques  
1004 du béton de chanvre : détermination de l'impact des matières premières et de la méthode de mise  
1005 en œuvre, PhD thesis, ENTPE, Lyon.
- 1006 Gouillart, E., Nunez-Iglesias, J., Van der Walt, S., 2016. Analyzing microtomography data with  
1007 Python and the scikit-image library. Adv. Struct. Chem. Imaging 2 (1), p. 18.
- 1008 Ingrao, C., Lo Giudice, A., Bacenetti, J., Tricase, C., Dotelli, G., Fiala, M., Siracusa, V., Mbohwa,  
1009 C., 2015. Energy and environmental assessment of industrial hemp for building applications: A  
1010 review, Renew. Sust. Energ. Rev. 51, 29-42.
- 1011 Iwase, T., Izumi Y., Kawabata, R. A., 1998 new measuring method for sound propagation constant  
1012 by using sound tube without any air spaces back of a test material. Internoise 98, Christchurch,  
1013 New Zealand.
- 1014 Jiang, Y., Lawrence, M., Ansell, M.P., Hussain, A., 2018. Cell wall microstructure, pore size  
1015 distribution and absolute density of hemp shiv, R. Soc. open sci. 5, 171945.
- 1016 Jiang, Y., Lawrence, M., Zhang, M., Cui, J., 2020. Industrial bio-based plant aggregates as hygric  
1017 and insulating construction materials for energy efficient building, Front. Chem. Sci. Eng.

- 1018 Jones, W.D., 1960. Fundamental Principle of Powder Metallurgy, Edward Arnold Publisher Ltd,  
1019 London, UK.
- 1020 Kinnane, O., Reilly, A., Grimes, J., Pavia, S., Walker, R., 2016. Acoustic absorption of hemp-lime  
1021 construction, *Constr. Build. Mater.* 122, 674-682.
- 1022 Laborel-Préneron, A., Magniont, C, Aubert, J.E., 2018. Characterization of Barley Straw, Hemp  
1023 Shiv and Corn Cob as Resources for Bioaggregate Based Building Materials, *Waste and Biomass*  
1024 *Valorization*, 9, 1095-1112.
- 1025 Lam, P., Sokhansanj, S., Bi, X., Lim, C., Naimi, L., Hoque, M., Mani, S., Womac, A., Ye, X.,  
1026 Narayan, S., 2007. Bulk density of wet and dry wheat straw and switchgrass particles, *Appl. Eng.*  
1027 *Agric.* 24 (3), 351–358.
- 1028 Lecompte T., 2019. Matériaux biosourcés pour le bâtiment et stockage temporaire de carbone,  
1029 *Techniques de l'Ingénieur*, C8124 v1.
- 1030 Lenormand, H., Hellouin de Menibus, A., Besnier, J.B., Leblanc, N., 2017. Variability of hemp  
1031 shives : study through ibis and chanvrisol projects, ICCBM 2017, Clermont-Ferrand, France.
- 1032 Lenormand, H., Zmamou, H., Leblanc, N., 2018. Agricultural by-products : variability impact of  
1033 characterization protocols on biosourced materials performances, Euromagh 2018, Hammamet,  
1034 Tunisie.
- 1035 Magniont, C., 2010. Contribution à la formulation et à la caractérisation d'un écomatériau de  
1036 construction à base d'agroressources, PhD Thesis, Toulouse III.
- 1037 Maire, E., Withers, P.J., 2014. Quantitative X-ray tomography, *International Materials Reviews* 59,  
1038 1–43.
- 1039 Mani, S., Tabil, L.G., Sokhansanj, S., 2004. Evaluation of compaction equations applied to four  
1040 biomass species, *Can. Biosyst. Eng.* 46 (3), 55–61.

- 1041 Meyer, K., Klobes, K.P., 1999. Comparison between different presentations of pore size  
1042 distribution in porous materials, *Fresenius J. Anal. Chem.* 363, 174–178.
- 1043 Nguyen, T.T, Picandet, V., Carré, P., Lecompte, T., Amziane, S., Baley, C., 2010. Effect of  
1044 compaction on mechanical and thermal properties of hemp concrete, *Eur. J. Environ. Civ. Eng.* 14  
1045 (5), 545-560.
- 1046 Nguyen, T.T., 2010. Contribution à l'étude de la formulation et du procédé de fabrication  
1047 d'éléments de construction en béton de chanvre. PhD thesis, Université Bretagne Sud, Lorient.
- 1048 Nguyen, S.T., Tran-Le, A.D., Vu, M.N., To, Q.D., Douzane, O., Langlet, T., 2016. Modeling thermal  
1049 conductivity of hemp insulation material: A multi-scale homogenization approach, *Build. Environ.*  
1050 107, 127-134.
- 1051 Nozahic, V., 2012. New eco-conception approach for biobased concrete based on the  
1052 understanding of the binder/granulate interface : application to hemp and sunflower with a lime-  
1053 pumice binder, Ph.d. thesis, Blaise Pascal University, Clermont Ferrand.
- 1054 Olny, X., Boutin, C., 2003. Acoustic wave propagation in double porosity media. *J. Acoust. Soc.*  
1055 *Am.* 114 (1), 73–89.
- 1056 Onoda, G.Y., Liniger, E.G., 1990. Random loose packings of uniform spheres and the dilatancy  
1057 onset, *Phys. Rev. Lett.* 64, 2727.
- 1058 Pierre, T., Carin, M., 2019. Characterization of the thermal properties of millimeter-sized insulating  
1059 materials, *Int. J. of Therm. Sci.* 135, 247-255.
- 1060 Pittau, F., Krause, F., Lumia, G., Habert, G., 2018. Fast-growing bio-based materials as an  
1061 opportunity for storing carbon in exterior walls, *Build. Environ.* 129, 117-129.
- 1062 Ribeiro, A., Pochart, P., Day, A., Mennuni, S., Bono, P. Baret, J.L., Spadoni, J.L., Mangin, I., 2015.  
1063 Microbial diversity observed during hemp retting. *Appl. Microbiol. Biotechnol.* 99, 4471–4484.



1064 Schindelin, J., Arganda-Carreras, I., Frise, E., Kaynig, V., Longair, M., Pietzsch, T., Preibisch, S.,  
1065 Rueden, C., Saalfeld, S., Schmid, B., Tinevez, J.Y., White, D.J., Hartenstein, V., Eliceiri, K.,  
1066 Tomancak, P., Cardona, A., 2012. Fiji: an open-source platform for biological-image analysis. *Nat.*  
1067 *Methods* 9, 676–682.

1068 Seeling, P., Wulff, J., 1946. Pressing operation in fabrication of articles by powder metallurgy,  
1069 *Trans. Am. Inst. Min. Metall. Eng.* 166, 492–505.

1070 Sun, C., 2005. True density of microcrystalline Cellulose, *J. Pharm. Sci.* 94 (10), 2132-2134.

1071 Thygens, A., Liu, M., Meyer, A., Daniel, G., 2013. Hemp fibres: enzymatic effect of microbiol  
1072 processing on fibre bundle structure. *Proceeding of the 34th Riso International symposium of*  
1073 *materials science*, 373-380.

1074 Tran-Le, A.D., Nguyen, S.T., Langlet, T., 2019. A novel anisotropic analytical model for effective  
1075 thermal conductivity tensor of dry lime-hemp concrete with preferred spatial distributions, *Energy*  
1076 *Build.* 182, 75-87.

1077 Tronet, P., Lecompte, T., Picandet, V., Baley, C., 2014. Study of lime and Hemp composite  
1078 precasting by compaction of fresh mix- A Fitted die to measure friction and stress state, *Powder*  
1079 *Technol.* 258, 285-296.

1080 Tronet, P., Lecompte, T., Picandet, V., Baley, C., 2016. Study of lime hemp concrete (LHC)-Mix  
1081 design, casting process and mechanical behavior, *Cem. Concr. Compos.* 67, 60-72.

1082 Viel, M., Collet, F., Lanos, C., 2018. Chemical and multi-physical characterization of agro-  
1083 resources' by-product as a possible raw building material, *Ind. Crops Prod.* 120, 214-237.

1084 Walker, E.E., 1923. The properties of powders — part VI: the compressibility of powders, *Trans.*  
1085 *Faraday Soc.* 19 (1), 73-82.

- 1086 Williams, J., Lawrence, M., Walker, P., 2016. A method for the assessment of the internal structure  
1087 of bio-aggregate concretes. *Constr. Build. Mater.* 116, 45-51.
- 1088 Williams, J., Lawrence, M., Walker, P., 2017. The influence of the casting process on the internal  
1089 structure and physical properties of hemp-lime. *Mater. Struct.* 50(2), 108.
- 1090 Zieger, V., Lecompte, T., Hellouin de Menibus, A., 2020. Impact of GHGs temporal dynamics on  
1091 the GWP assessment of building materials: A case study on bio-based and non-bio-based walls,  
1092 *Build. Environ.* 185, 107210.

## 1093 7. Appendix: Acquisition and processing of XRCT 1094 images


1095 Image acquisition was performed at Navier laboratory using a XRCT laboratory scanner (Ultratom  
1096 from RX-Solutions), with a 230 kV micro-focus source Hamamatsu L10801 and a flat-panel  
1097 detector Varex 4343 DX-I. The tube voltage and the tube current of the source were set to 70 kV  
1098 and 170  $\mu\text{A}$ , respectively. The frame rate of the detector was set to 1 projection/s and 16  
1099 radiographs were averaged at the same angular position to improve the signal-to-noise ratio of the  
1100 projections. Under these imaging conditions, one scan lasted about 12 hours to acquire 2336  
1101 projections over  $360^\circ$ . After reconstruction, it results in a 3D image of about  $2000 \times 2000 \times 2500$   
1102 voxels with a voxel size of  $12 \mu\text{m}$ .

1103 Sub-volumes containing only one particle were manually defined. After conversion in 8-bit integer  
1104 format, they were processed as follows:

- 1105 • denoising: a total variation minimisation filter is applied to reduce noise and artefacts while  
1106 preserving the particle edges;
- 1107 • segmentation: the grey levels are thresholded above a value determined using the Triangle  
1108 method. For most particles, the threshold is calculated for the whole 3D image. For a few  
1109 images presenting artefacts, the thresholding is computed locally on transverse slices.  
1110 Morphological operations (binary closing, opening and filling holes) are then applied to  
1111 obtain the final binary image, which isolates the particle, and possible residual parts of EPS  
1112 beads or adhesive tape, from the rest of the image;
- 1113 • volume measurement: the connected regions are labelled and their volumes are defined as  
1114 the number of voxels  $N$  associated with their respective labels. The hemp shiv's apparent  
1115 volume corresponds to the largest region. The volume  $V$  in metric units is given by  $= Nl^3$  ,  
1116 where  $l$  is the side length of a voxel.

1117 This procedure has been automatically performed on all particles using Python, relying on NumPy,  
1118 SciPy, and scikit-image packages (Gouillart et al., 2016). The error in volume measurement has  
1119 been estimated by analysing the effect of the denoising weight, the grey level threshold and the  
1120 size of the structuring element used in morphological operations.

1121 The resulting envelopes have been checked visually for all particles. Furthermore, Fig. A.1 shows  
1122 that the measured apparent densities are consistent with grey levels in particles. In fact, in perfect  
1123 absorption contrast XRCT images, grey level is usually assumed to vary linearly with the X-ray  
1124 attenuation coefficient, which increases with material density. Under certain experimental  
1125 conditions, including equipment and calibration, grey levels can be used directly to estimate the  
1126 material densities (Maire and Withers, 2014). In this study, the purpose of Fig. A.1 is only to  
1127 validate the particle density assessment, in particular with regard to extreme values.

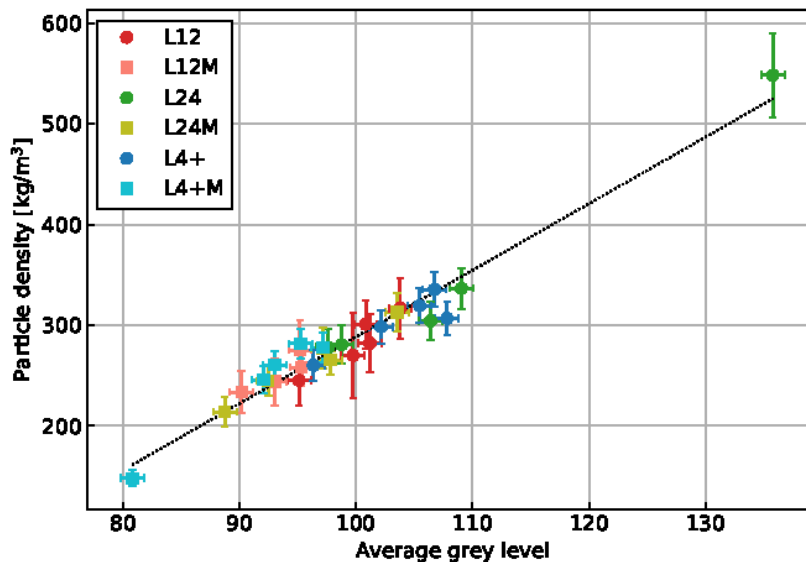

1128  
1129 Figure A.1. Particle densities calculated from volume and mass measurements as a function of the  
1130 average grey level within the particles. The uncertainty in the average grey level has been  
1131 estimated by analysing the effect of thresholding only.

1132