



**HAL**  
open science

## A numerical study of reversible plasticity using continuum dislocation mechanics

Stéphane Berbenni, Ricardo A. Lebensohn

► **To cite this version:**

Stéphane Berbenni, Ricardo A. Lebensohn. A numerical study of reversible plasticity using continuum dislocation mechanics. *Comptes Rendus. Physique*, 2021, 22 (S3), pp.1-18. 10.5802/crphys.54 . hal-03207583

**HAL Id: hal-03207583**

**<https://hal.univ-lorraine.fr/hal-03207583>**

Submitted on 27 Apr 2021

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# A numerical study of reversible plasticity using continuum dislocation mechanics

Stéphane Berbenni<sup>\*, a, b</sup> and Ricardo A. Lebensohn<sup>c</sup>

<sup>a</sup> Université de Lorraine, Arts et Métiers Paris Tech, CNRS, LEM3, F-57000 Metz, France

<sup>b</sup> Laboratory of Excellence on Design of Alloy Metals for low-mAss Structures (DAMAS), Université de Lorraine, France

<sup>c</sup> Theoretical Division, Los Alamos National Laboratory, Los Alamos, NM 87845, USA.  
*E-mails:* stephane.berbenni@univ-lorraine.fr (S. Berbenni), lebenso@lanl.gov (R. A. Lebensohn).

## Abstract.

In this contribution, an elasto-viscoplastic fast Fourier transform-based (EVPFFT) numerical implementation of the Mesoscale Field Dislocation Mechanics (MFDM) formulation, called MFDM-EVPFFT, is applied to study the reversible plastic behavior of periodic two-phase crystalline composites with an elasto-viscoplastic plastic matrix and a purely elastic second phase. Periodic laminate microstructures of this kind with different periods (i.e. sizes) are considered to examine the size dependence of the Bauschinger effect and hardening during cyclic loading. Comparisons with classic composite effects obtained with conventional crystal plasticity are discussed. Specifically, the MFDM-EVPFFT results shed light on the hardening mechanisms due to piling-up/unpiling-up of geometrically-necessary dislocations (GND) during reverse loading.

**Keywords.** Hardening mechanisms, geometrically-necessary dislocations, Bauschinger effect, size effect, FFT.

**Mathematical subject classification (2010).** 00X99.

**Funding.** The first author is supported by the French State (ANR) through the program "Investment in the future" (LabEx "DAMAS" grant ANR-11-LABX-0008-01) for financial support. The second author is supported by Los Alamos National Laboratory Laboratory-Directed Research and Development (LDRD) program.

## 1. Introduction

Among the different physically-based micromechanical formulations/numerical methods developed in recent years to study plasticity of crystalline materials: discrete methods like discrete dislocation dynamics (DDD) [48, 29, 10, 77, 33, 73], continuum approaches like strain-gradient plasticity [28, 50, 51, 17, 18, 75, 22, 63, 52, 32], continuum dislocation dynamics [26, 76, 64, 31, 65],

---

\* Corresponding author.

another continuum approach, called phenomenological Mesoscopic Field Dislocation Mechanics (MFDM) [5, 61, 62, 4, 54, 55, 6] has emerged as an efficient numerical method to model plasticity mechanisms at the mesoscopic scale, including reversible loading. MFDM combines continuum dislocation mechanics and strain-gradient crystal plasticity, integrating the mobilities of both geometrically-necessary dislocations (GNDs) and statistically-stored dislocations (SSDs). Regarding the calculation of backstress, the MFDM theory involves one spatial derivative of the plastic distortion, see e.g. [54], whereas other phenomenological strain-gradient plasticity theories as the ones recalled above involve two spatial derivatives, see e.g. [28, 50, 17, 75, 39]. Fundamental kinematics and thermodynamics aspects of the MFDM theory can be found elsewhere [1, 2, 5, 4]. In this mesoscale theory, the constitutive equations for slip, GND mobility, and strain-hardening need to be specified phenomenologically. MFDM requires solving the GND density transport equation, together with the stress-balance field equation, which allows the prediction of the collective arrangement and evolution of GNDs and associated long-range stresses. Originally, the MFDM theory was numerically implemented in the framework of the finite element method (FEM) [60, 61, 72, 71, 54, 59, 58, 27].

More recently, an alternative numerical implementation of the MFDM theory using an approach based on fast Fourier transforms (FFT) was introduced to improve computational efficiency. FFT-based methods were originally developed and applied to composite materials [44, 45, 43], in which the mechanical heterogeneity is given by the spatial distribution of phases with different mechanical properties. Later, the method was adapted to polycrystals to accelerate crystal plasticity (CP) calculations for different constitutive behaviors and applications [36, 37, 40, 38, 68, 66, 41, 42, 30]. In polycrystals, the mechanical heterogeneity is related to the spatial distribution of anisotropic crystals with different orientations. These original CP FFT-based implementations showed the feasibility of efficiently solving the micromechanical behavior of complex polycrystalline unit cells. FFT-based methods were also recently extended to consider constitutive behavior based on field dislocation mechanics (FDM) [15, 11, 20, 21] and MFDM [19, 12, 24], and were also coupled with DDD methods [14, 25, 13], providing better efficiency to these powerful and numerically-demanding formulations.

In this contribution, an elasto-viscoplastic fast Fourier transform-based method (EVPFFT) coupled with MFDM [19, 12, 24] is used to study the reversible plasticity of two-phase composites with a elasto-viscoplastic matrix and a purely elastic second phase. We consider the case of periodic laminate microstructure with various periods (i.e. sizes) and phase volume fractions of the elastic channel to examine both the effects of second phase volume fraction and channel size on the local and overall behaviors. Comparisons with corresponding results using the standard EVPFFT model with no strain-gradient effects (called in what follows CP-EVPFFT) are presented and discussed.

The plan of the paper is as follows: in section 2 we provide details of the numerical implementation of the MFDM-EVPFFT formulation. In section 3 we present new results of the microscopic and macroscopic responses of laminate microstructures during reverse plasticity, including the study of the Bauschinger effect and non linear hardening mechanisms due to piling-up and unpiling-up of GNDs during the forward and the reverse strain-paths. In section 4, we provide the conclusions of this study.

## 2. Theory and numerical implementation

### 2.1. Theory

The displacement field  $\mathbf{u}$ , the strain field  $\boldsymbol{\varepsilon}$ , and the stress field (Cauchy stress tensor)  $\boldsymbol{\sigma}$  are solved using a FFT-based micro-mechanical formulation in a small deformation setting for elasto-viscoplastic materials. It is assumed that dislocations are present and drive plastic flow within

the material. Therefore, a mesoscale continuum dislocation mechanics framework is adopted to describe both dislocation kinematics and kinetics. The field equations of this problem are solved at any material point  $\mathbf{x}$  of a periodic unit cell  $V$ . The set of field equations are:

$$\begin{aligned} \mathbf{div} \boldsymbol{\sigma} &= 0 \\ \boldsymbol{\sigma} &= \mathbf{C} : \boldsymbol{\varepsilon}^e \\ \mathbf{U} &= \mathbf{grad} \mathbf{u} = \mathbf{U}^e + \mathbf{U}^p \\ \mathbf{u} - \langle \boldsymbol{\varepsilon} \rangle \cdot \mathbf{x} &\text{ periodic, } \boldsymbol{\sigma} \cdot \mathbf{n} \text{ anti-periodic} \end{aligned} \quad (1)$$

where  $\langle \cdot \rangle$  denotes a volume average over  $V$ ,  $\boldsymbol{\varepsilon}^e = (\mathbf{U}^e)^{sym}$  and  $\mathbf{C}$  is the fourth order elastic stiffness tensor, which is known at each point  $\mathbf{x}$  of  $V$ . Generally, the components of the macroscopic strain  $\langle \boldsymbol{\varepsilon} \rangle = \mathbf{E}$  or stress  $\langle \boldsymbol{\sigma} \rangle = \boldsymbol{\Sigma}$  (or a mixed of both) are prescribed.

During plastic deformation, both the plastic distortion  $\mathbf{U}^p$ , which results from dislocation motion, and the elastic distortion  $\mathbf{U}^e$  are incompatible fields. Depending on the resolution scale, dislocations are classified as GNDs [8] or SSDs. We make use of the MFDM formulation developed by Acharya and co-workers [5, 61, 4, 54] based on extensions of the seminal works of Kröner [34] and Mura [47]. In contrast with DDD, this theory is based on the evolution of a mesoscale value of the dislocation density tensor  $\boldsymbol{\alpha}$  (also called the Nye tensor [49]) considered as a state variable [34, 35]. Here, a *reduced* version of MFDM is considered [62] in the framework of the FFT-based formulation, instead of the *full* MFDM theory of Acharya and Roy [5]. Therefore, the plastic distortion rate tensor denoted  $\dot{\mathbf{U}}^p$  reads:

$$\dot{\mathbf{U}}^p = \boldsymbol{\alpha} \times \mathbf{v} + \mathbf{L}^p \quad (2)$$

The SSD mobility is represented by the mesoscale plastic distortion rate, denoted  $\mathbf{L}^p$ , which is defined from an averaging procedure [4, 5]. Considering a crystal plasticity framework for FCC (face-centered cubic) metals, the plastic distortion rate tensor  $\mathbf{L}^p$  due to slip of SSD is given by:

$$\mathbf{L}^p = \sum_{s=1}^N \dot{\gamma}^s \mathbf{m}^s \quad (3)$$

where  $\mathbf{m}^s$  is the crystallographic orientation tensor such that  $\mathbf{m}^s = \mathbf{b}^s \otimes \mathbf{n}^s$ . For each slip system  $s$ , the unit vector  $\mathbf{b}^s$  denotes the slip direction and  $\mathbf{n}^s$  the slip plane unit normal.  $N$  is the total number of possible slip systems in the single crystal, i.e.  $N = 12$  for FCC metals deforming by  $\{111\} \langle 110 \rangle$  slip. The slip rate  $\dot{\gamma}^s$  is defined with a viscoplastic flow rule as a power law relationship:

$$\dot{\gamma}^s = \dot{\gamma}^0 \left( \frac{|\tau^s|}{\tau_c} \right)^n \text{sgn}(\tau^s) \quad (4)$$

where  $n$  is the power exponent which represents the inverse of the strain rate sensitivity of the material,  $\tau^s = \mathbf{m}^s : \boldsymbol{\sigma}$  is the resolved shear stress,  $\dot{\gamma}^0$  is a reference slip rate and  $\tau_c$ , the reference shear stress, is considered identical for all slip systems.

The space-time evolution of the dislocation density tensor  $\boldsymbol{\alpha}$  is prescribed as:

$$\dot{\boldsymbol{\alpha}} = -\mathbf{curl} \dot{\mathbf{U}}^p \quad (5)$$

This hyperbolic-type equation is numerically solved with a spectral approach. In terms of the constitutive specifications of the dislocation velocity  $\mathbf{v}$  and the slip distortion rate  $\mathbf{L}^p$ , considering plastic flow incompressibility ( $Tr(\mathbf{L}^p) = 0$  and  $Tr(\boldsymbol{\alpha} \times \mathbf{v}) = 0$ , where  $Tr(\cdot)$  means the trace of  $(\cdot)$ ), the GND velocity  $\mathbf{v}$  reads:

$$\mathbf{v} = \frac{\mathbf{g}}{|\mathbf{g}|} \nu \quad \text{with} \quad \nu \geq 0 \quad (6)$$

where  $\mathbf{g}$  is the glide force parallel to  $\mathbf{v}$  and  $\nu$  is the magnitude of  $\mathbf{v}$ . The constitutive equation adopted for  $\nu$  is based on the Orowan law for mobile GNDs [54]:

$$\nu = \frac{\zeta^2 b}{N} \left( \frac{\mu}{\tau_c} \right)^2 \sum_{s=1}^N |\dot{\gamma}^s| \quad (7)$$

where  $\zeta$  is a material constant,  $b$  is the magnitude of the Burgers vector,  $\tau_c$  is the shear strength and  $\mu$  is the isotropic elastic shear modulus of the material. From [5, 54, 19],  $\mathbf{g}$  reads:

$$\mathbf{g} = \boldsymbol{\epsilon} : (\mathbf{S} \cdot \boldsymbol{\alpha}) - \boldsymbol{\epsilon} : \boldsymbol{\alpha} \frac{\mathbf{S} \cdot \boldsymbol{\alpha} \cdot (\boldsymbol{\alpha}^t - \boldsymbol{\alpha})}{\boldsymbol{\alpha} : (\boldsymbol{\alpha}^t - \boldsymbol{\alpha})} \quad (8)$$

where  $\boldsymbol{\epsilon}$  denotes the third-order permutation tensor,  $\mathbf{S} = \boldsymbol{\sigma} - \frac{1}{3} Tr(\boldsymbol{\sigma}) \boldsymbol{\delta}$  denotes the deviatoric stress tensor with  $\boldsymbol{\delta}$  being the second order unit tensor.

The evolution law for the shear strength  $\tau_c$  follows the strain-hardening model developed by [54, 19, 12]:

$$\dot{\tau}_c = \theta_0 \frac{\tau_s - \tau_c}{\tau_s - \tau_0} \dot{\Gamma} + k_0 \frac{\zeta^2 \mu^2 b}{2(\tau_c - \tau_0)} \left( \sum_{s=1}^N |\boldsymbol{\alpha} \cdot \mathbf{n}^s| |\dot{\gamma}^s| + \sum_{s=1}^N |\boldsymbol{\alpha} \cdot \mathbf{n}^s| |\boldsymbol{\alpha} \times \mathbf{v}| \right) \quad (9)$$

where  $\dot{\Gamma} = |\boldsymbol{\alpha} \times \mathbf{v}| + \sum_{s=1}^N |\dot{\gamma}^s|$ ,  $\tau_0$  is the yield strength due to lattice friction (which is very low for FCC metals),  $\tau_s$  is the saturation stress,  $\theta_0$  is the stage II hardening rate for FCC metals,  $k_0$  is related to a geometric mean free path due to GND forest on slip system  $s$ .

## 2.2. FFT-based numerical implementation

The FFT-based MFDM numerical implementation starts from the small-strain elasto-viscoplastic crystal plasticity formulation [38]. Using a backward Euler implicit time discretization and Hooke's law, the expression of the stress tensor  $\boldsymbol{\sigma}$  at  $t + \Delta t$  is given by:

$$\boldsymbol{\sigma}^{t+\Delta t} = \mathbf{C} : \boldsymbol{\epsilon}^{e,t+\Delta t} = \mathbf{C} : (\boldsymbol{\epsilon}^{t+\Delta t} - \boldsymbol{\epsilon}^{p,t} - \dot{\boldsymbol{\epsilon}}^{p,t+\Delta t} (\boldsymbol{\sigma}^{t+\Delta t}) \Delta t) \quad (10)$$

In what follows, the supra-indices  $t + \Delta t$  are omitted, and only the fields corresponding to the previous time step  $t$  will be explicitly indicated. The unknown total strain field  $\boldsymbol{\epsilon}$  is solved through an integral Lippmann-Schwinger-Dyson equation for the unknown strain field  $\boldsymbol{\epsilon}$ :

$$\boldsymbol{\epsilon}(\mathbf{x}) = \langle \boldsymbol{\epsilon} \rangle - \int_V \boldsymbol{\Gamma}^0(\mathbf{x} - \mathbf{x}') : \boldsymbol{\tau}(\mathbf{x}') dV' \quad (11)$$

where  $\langle \boldsymbol{\epsilon} \rangle$  represents the average value of  $\boldsymbol{\epsilon}$  in  $V$ ,  $\boldsymbol{\Gamma}^0$  is the modified Green tensor associated with a homogeneous elastic stiffness  $\mathbf{C}^0$  and  $\boldsymbol{\tau} = \boldsymbol{\sigma} - \mathbf{C}^0 : \boldsymbol{\epsilon}$  is the stress polarization field. In what follows, Eq. 11 is solved using a numerical scheme based on FFT and augmented Lagrangians [43]. Let  $\boldsymbol{\xi}$  be the Fourier vector of magnitude  $\xi = \sqrt{\boldsymbol{\xi} \cdot \boldsymbol{\xi}}$  and  $i$  the complex imaginary number  $i = \sqrt{-1}$ . Let  $\widehat{\boldsymbol{\epsilon}}(\boldsymbol{\xi})$  and  $\widehat{\boldsymbol{\Gamma}}^0(\boldsymbol{\xi})$  be, respectively, the Fourier transform of  $\boldsymbol{\epsilon}(\mathbf{x})$  and  $\boldsymbol{\Gamma}^0(\mathbf{x})$ . The Fourier transform of the integral equation 11 yields:

$$\begin{aligned} \widehat{\boldsymbol{\epsilon}}(\boldsymbol{\xi}) &= -\widehat{\boldsymbol{\Gamma}}^0(\boldsymbol{\xi}) : \widehat{\boldsymbol{\tau}}(\boldsymbol{\xi}) \quad \forall \boldsymbol{\xi} \neq \mathbf{0} \\ \widehat{\boldsymbol{\epsilon}}(\mathbf{0}) &= \langle \boldsymbol{\epsilon} \rangle \end{aligned} \quad (12)$$

The Green operator associated with  $\mathbf{C}^0$  in Fourier space,  $\widehat{\boldsymbol{\Gamma}}^0$ , is given in [45, 74].

Let us assume now that  $\boldsymbol{\lambda}^{(n)}$  and  $\mathbf{e}^{(n)}$  are, respectively, the auxiliary guess stress and strain fields at iteration (n). The stress polarization tensor becomes:  $\boldsymbol{\tau}^{(n)} = \boldsymbol{\lambda}^{(n)} - \mathbf{C}^0 : \mathbf{e}^{(n)}$ . An alternative fixed-point expression, which requires computing the Fourier transform of the stress field instead of that of the polarization field was reported in [43]:

$$\begin{aligned} \widehat{\boldsymbol{\epsilon}}^{(n+1)}(\boldsymbol{\xi}) &= \widehat{\boldsymbol{\epsilon}}^{(n)}(\boldsymbol{\xi}) - \widehat{\boldsymbol{\Gamma}}^0(\boldsymbol{\xi}) : \widehat{\boldsymbol{\lambda}}^{(n)}(\boldsymbol{\xi}) \quad \forall \boldsymbol{\xi} \neq \mathbf{0} \\ \widehat{\boldsymbol{\epsilon}}^{(n+1)}(\mathbf{0}) &= \langle \boldsymbol{\epsilon}^{(n)} \rangle \end{aligned} \quad (13)$$

Once  $\mathbf{e}^{(n+1)} = \text{FFT}^{-1}(\widehat{\mathbf{e}}^{(n+1)}(\boldsymbol{\xi}))$  is obtained in real space by using the inverse Fourier transform ( $\text{FFT}^{-1}$ ), the nullification of the residual  $\mathbf{R}$ , which depends on the stress and strain tensors  $\boldsymbol{\sigma}^{(n+1)}$  and  $\boldsymbol{\varepsilon}^{(n+1)}$ , is solved:

$$\mathbf{R}(\boldsymbol{\sigma}^{(n+1)}) = \boldsymbol{\sigma}^{(n+1)} + \mathbf{C}^0 : \boldsymbol{\varepsilon}^{(n+1)}(\boldsymbol{\sigma}^{(n+1)}) - \boldsymbol{\lambda}^{(n)} - \mathbf{C}^0 : \mathbf{e}^{(n+1)} = 0 \quad (14)$$

This nonlinear equation was solved in [38] using a Newton-Raphson scheme. The  $(p+1)$ -guess for the stress field  $\boldsymbol{\sigma}^{(n+1)}$  is given by:

$$\boldsymbol{\sigma}^{(n+1,p+1)} = \boldsymbol{\sigma}^{(n+1,p)} - \left( \left( \frac{\partial \mathbf{R}}{\partial \boldsymbol{\sigma}} \right)_{\boldsymbol{\sigma}^{(n+1,p)}} \right)^{-1} : \mathbf{R}(\boldsymbol{\sigma}^{(n+1,p)}) \quad (15)$$

Using the constitutive equation, the Jacobian matrix in the above expression reads:

$$\left( \frac{\partial \mathbf{R}}{\partial \boldsymbol{\sigma}} \right)_{\boldsymbol{\sigma}^{(n+1,p)}} = \boldsymbol{\delta} \otimes \boldsymbol{\delta} + \mathbf{C}^0 : \mathbf{C}^{-1} + \Delta t \mathbf{C}^0 : \left( \frac{\partial \dot{\boldsymbol{\varepsilon}}^p}{\partial \boldsymbol{\sigma}} \right)_{\boldsymbol{\sigma}^{(n+1,p)}} \quad (16)$$

where  $\otimes$  is the dyadic (or tensorial) product.

The expression of  $\partial \dot{\boldsymbol{\varepsilon}}^p / \partial \boldsymbol{\sigma}$  was already reported in [19, 12] for the numerical MFDM-EVPFFT formulation. Once the convergence is achieved on  $\boldsymbol{\sigma}^{(n+1)}$  and  $\boldsymbol{\varepsilon}^{(n+1)}$ , the new guess for the auxiliary stress field  $\boldsymbol{\lambda}$  is given by using the Uzawa descent algorithm:

$$\boldsymbol{\lambda}^{(n+1)} = \boldsymbol{\lambda}^{(n)} + \mathbf{C}^0 : (\mathbf{e}^{(n+1)} - \boldsymbol{\varepsilon}^{(n+1)}) \quad (17)$$

The iterative procedure stops when the normalized average differences between the stress fields  $\boldsymbol{\sigma}$  and  $\boldsymbol{\lambda}$ , and the strain fields  $\boldsymbol{\varepsilon}$  and  $\mathbf{e}$ , are smaller than a given threshold error (typically  $10^{-5}$ ). This condition implies the fulfillment of both stress equilibrium and strain compatibility up to sufficient accuracy. The FFT-based resolution of the Lippmann-Schwinger-Dyson equation used a DFT-scheme coupled to a rotated centered finite difference scheme [74]. In the algorithm described above, an overall macroscopic strain  $\mathbf{E} = \langle \boldsymbol{\varepsilon}^{(n)} \rangle$  is applied to the periodic unit cell  $V$  in the form of:

$$\mathbf{E} = \mathbf{E}^t + \dot{\mathbf{E}} \Delta t \quad (18)$$

In cases of mixed boundary conditions with imposed macroscopic strain rate  $\dot{\mathbf{E}}$  and stress  $\boldsymbol{\Sigma}$ , the  $(n+1)$ -guess of the macroscopic strain  $\mathbf{E}^{(n+1)}$  was given in [43, 38].

Let  $\widehat{\boldsymbol{\alpha}}(\boldsymbol{\xi})$  be the Fourier transform of  $\boldsymbol{\alpha}(\mathbf{x})$ . Following [20, 19], it reads at  $t + \Delta t$  in component form:

$$\widehat{\alpha}_{ij}^{t+\Delta t} = \kappa(\eta) \left( \widehat{\alpha}_{ij}^t - \Delta t i \xi_k \left( \widehat{(\alpha_{ij} v_k)}^t - \widehat{(\alpha_{ik} v_j)}^t \right) \right) - \Delta t i \xi_k e_{jkl} \widehat{(L_{il}^p)}^t \quad (19)$$


where an exponential second order spectral low-pass filter was used to stabilize the numerical approximation of by eliminating high frequencies leading to spurious oscillations. The exponential filter is defined as function of discrete frequencies  $\eta$  as:

$$\kappa(\eta) = \exp\left(-\beta(\eta)^{2p}\right) \quad (20)$$

where the damping parameter  $\beta$  is defined as  $\beta = -\log \varepsilon_M$ , where  $\varepsilon_M$  is low value parameter that was optimized in [20]. To fix the time step  $\Delta t$  in eq. 19 to satisfy stability requirements for numerically solving the dislocation density transport equation, a user-specified fraction denoted  $c = 0.25$  of Courant-Friedrichs-Lewy (CFL) limit is used in the numerical applications such that:

$$\Delta t_{CFL} = c \frac{\delta}{v_{max}} \quad (21)$$

where  $\delta$  is the voxel size and  $v_{max}$  is the maximal GND velocity. The time step is given as  $\Delta t = \min(\Delta t_{CFL}, \Delta t_\varepsilon)$  where  $\Delta t_{CFL}$  and the time step  $\Delta t_\varepsilon$  is the time step classically used in the EVPFFT formulation.

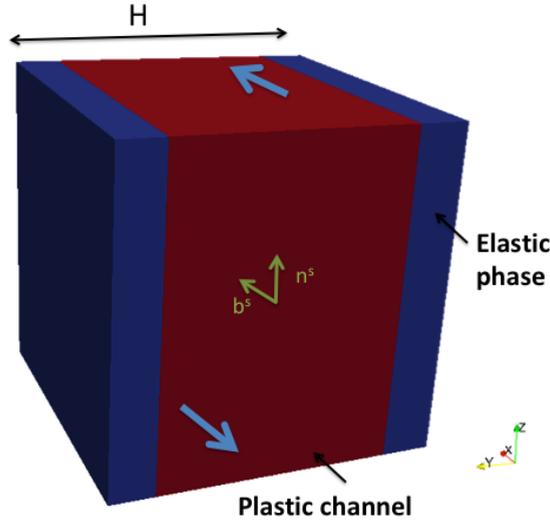

**Figure 1.** Two-phase periodic laminate composite with period  $H$  along the  $y$ -direction. The red region is the plastic channel and the blue regions represent elastic second phase. The blue arrows describe the shear loading, and, the green arrows show the unit slip direction and normal vectors of the active slip system.

### 3. Results and discussion

#### 3.1. Two-phase periodic laminate microstructures


We discuss here reversible plasticity predictions using the MFD-VPFFFT formulation. As illustrative example, a two-phase periodic laminate composite with period  $H$  along the  $y$ -direction as the one shown in Figure 1 is subjected to forward and reverse shear loading. The unit vectors along the  $x$ -,  $y$ -,  $z$ -directions are denoted  $\mathbf{e}_1$ ,  $\mathbf{e}_2$  and  $\mathbf{e}_3$ , respectively. The two-phase composite consists of a purely elastic phase (hereafter called *second phase* and denoted  $P$ ) and an elasto-viscoplastic phase (hereafter called *plastic channel* denoted  $C$ ). The volume fraction of the second phase  $P$  is denoted  $f$ . Similar microstructures were already studied in [19] but only for monotonic loadings. Here, three different periods  $H$  are considered:  $H = 0.25\mu\text{m}$ ,  $H = 1\mu\text{m}$ ,  $H = 10\mu\text{m}$ . The unit cell is discretized into  $32^3 = 32768$  voxels, which is sufficient for such simple microstructure [19].

Elasticity is assumed to be isotropic and homogeneous with Young's modulus  $E = 69\text{GPa}$  and Poisson ratio  $\nu = 0.33$  as for aluminium. Therefore, the elastic shear modulus is  $\mu = 25.94\text{GPa}$ . For the plastic channel, the viscoplastic material parameters used for numerical simulations are reported in Table 1. Let us note that the effect of the phenomenological parameter  $k_0$  in Eq. 9 will be studied considering two different values:  $k_0 = 20$  or  $k_0 = 500$ . The numerical parameters used for GND density evolution equation are taken from [20], where these parameters were optimized. Here, we consider  $c = 0.25$ ,  $\varepsilon_M = 0.2$ ,  $p = 1$ . The unit cell undergoes pure shear loadings in the following sequence: forward shear up to  $+0.2\%$  / reverse shear up to  $-0.2\%$  / forward shear up to  $+0.2\%$ . The applied shear strain rates are  $\dot{E}_{13} = \dot{E}_{31} = \pm 0.001\text{s}^{-1}$  with  $\Delta t_\varepsilon = 0.01\text{s}$ . The crystallographic orientation of the plastic single crystal channel is given by the three Bunge-Euler

angles:  $\phi_1 = 300^\circ$ ,  $\phi = 54.7358^\circ$ ,  $\phi_2 = 45^\circ$ , which leads to a predominant single slip mode in the channel due to the slip system  $(111) \langle 10\bar{1} \rangle$ . This active slip system is represented in Figure 1 by two arrows in the plastic channel, representing the unit normal  $\mathbf{n}^s$ , and, the unit vector in the slip direction  $\mathbf{b}^s$ . Both are parallel to  $\mathbf{e}_3$  and  $\mathbf{e}_1$ , respectively. In this configuration, using the MFDM-EVPFFT model, the main GND density created during this forward/ reverse/ forward shear loading is due to the screw component of the Nye tensor  $\alpha_{11}$  with GND density defined by  $\alpha_{11}/b$  (in  $m^{-2}$ ). In contrast with conventional crystal plasticity, the evolution equations in the MFDM theory impose a jump condition on the plastic distortion rate across the material interfaces [3]. This jump condition is specified to describe the interaction of dislocations with impenetrable elastic/ plastic interfaces, which corresponds to fully constrained plastic flow at the interface [54]. Therefore, the condition on the interface is  $\dot{\mathbf{U}}^p \times \mathbf{n} = 0$ , where  $\mathbf{n} = \mathbf{e}_2$  is the unit normal to the interface. Using Cartesian coordinates, the interfacial condition for voxels in the plastic channel adjacent to the interface is:  $\dot{U}_{ij}^p = 0$  except  $\dot{U}_{12}^p \neq 0$  and  $\dot{U}_{32}^p \neq 0$ .

**Table 1.** List of plastic material parameters used for numerical simulations for the channel phase.

$\dot{\gamma}^0 (s^{-1})$	$n$	$\zeta$	$b$ (m)	$\tau_0$ (MPa)	$\tau_s$ (MPa)	$\theta_0$ (MPa)	$k_0$
1	20	0.33	$2.86 \times 10^{-10}$	3	12	150	20 or 500

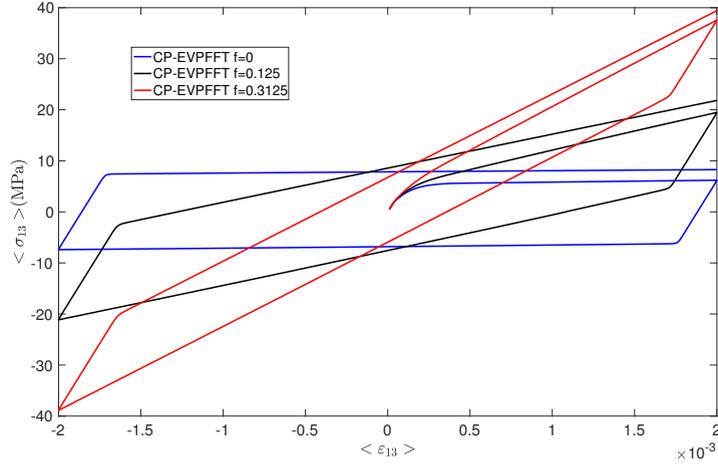


**Figure 2.** Effect of second elastic phase volume fraction  $f$  with CP-EVPFFT on the cyclic shear response of two-phase laminate microstructures.

### 3.2. Cyclic plasticity responses obtained with CP-EVPFFT

Let us first examine the classic composite effect (i.e. associated with the volume fraction  $f$ ) on the reversible behavior of the two-phase laminate composite, obtained with conventional crystal plasticity. It corresponds to  $\boldsymbol{\alpha} = \mathbf{0}$  in Eq. 9 and  $\mathbf{v} = \mathbf{0}$  in Eq. 6, i.e.  $\dot{\mathbf{U}}^p = \mathbf{L}^p$ , and there is no condition on the plastic distortion rate across the material interfaces. The model is then reduced to the classic CP-EVPFFT formulation as described in [38] which is size ( $H$ -) independent, because there is no internal length scale. As reported in Figure 2, the overall shear responses are only dependent on the second phase volume fraction  $f$ . When  $f$  is increased from  $f = 0$  to  $f = 0.125$  and  $f = 0.3125$ , the overall hardening rate during forward and reverse shearing increases. The case  $f = 0$  corresponds to the single crystal's response, which only exhibits a small isotropic hardening contribution due to chosen parameters  $\tau_0$ ,  $\tau_s$  and  $\theta_0$  in Table 1. It is observed on Figure 2 that the Bauschinger effect increases with  $f$ . Following [9, 16], the stress reflecting the Bauschinger effect is defined as  $\Sigma_b = (\Sigma_f - \Sigma_r)/2$ , where  $\Sigma_f$  is here the forward shear stress  $\Sigma_{13}$  at  $E_{13} = 0.2\%$  (in the plastic regime) and  $\Sigma_r$  is the reverse shear stress  $\Sigma_{13}$  at the onset of plasticity during reverse loading. According to Figure 2, a rapid elastic/plastic transition is obtained with CP-EVPFFT when  $\Sigma_r$  is reached. Here,  $\Sigma_b = 0\text{MPa}$  for  $f = 0$  (single crystal),  $\Sigma_b = 12.1\text{MPa}$  for  $f = 0.125$  (with  $\Sigma_f = 19.4\text{MPa}$  and  $\Sigma_r = -4.8\text{MPa}$ ) and  $\Sigma_b = 30.15\text{MPa}$  for  $f = 0.3125$  (with  $\Sigma_f = 37.6\text{MPa}$  and  $\Sigma_r = -22.7\text{MPa}$ ). The negative sign for  $\Sigma_r$  stems from the fact that the onset of plastic yielding during reverse shear loading occurs in the positive stress quadrant in Figure 2 (and not in the negative stress quadrant), which is the signature of a strong Bauschinger effect and a large linear kinematic hardening for such volume fractions of elastic phase. This is also the clear signature of a large *permanent softening*, which was for example reported in [9] for copper crystals reinforced with silica particles.

When  $f = 0.125$  or  $f = 0.3125$ , the observed strong Bauschinger effect is due to backstress (or kinematic hardening) denoted  $X$ . In both phases, the residual stresses  $R^{PC} = \sigma_{13}^{PC} - \Sigma_{13}$  are constant and can be calculated from the stress average rule:  $\Sigma_{13} = \langle \sigma_{13} \rangle = f \sigma_{13}^P + (1-f) \sigma_{13}^C$

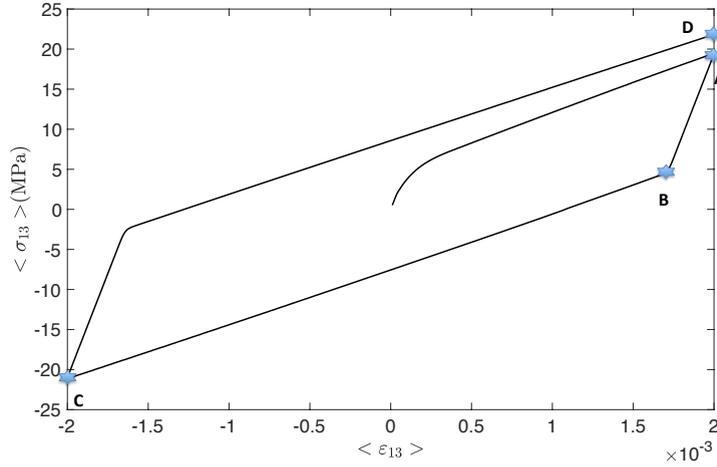


**Figure 3.** Cyclic shear stress response for  $f = 0.125$  obtained with CP-EVPFFT describing the 4 different states: state A (at the end of the first forward shear loading at  $E_{13} = 0.2\%$ ), state B (during the reverse shear loading at  $E_{13} = 0.17\%$ ), state C (at the end of the reverse shear loading at  $E_{13} = -0.2\%$ ), state D (at the end of the second forward shear loading at  $E_{13} = 0.2\%$ ).

using the compatibility condition for an infinite planar grain boundary, as given in [57]:


$$\begin{aligned} R^P &= \sigma_{13}^P - \Sigma_{13} = 2\mu(1-f)\varepsilon_{13}^P \\ R^C &= \sigma_{13}^C - \Sigma_{13} = -2\mu f \varepsilon_{13}^P \end{aligned} \quad (22)$$

where  $\varepsilon_{13}^P$  is the uniform plastic shear strain in the channel. In this configuration,  $\varepsilon_{13}^P = \frac{U_{13}^P}{2}$ , since  $U_{31}^P = 0$ . For this two phase composite under pure shear loading, the kinematic hardening  $X$  is given by the difference between the macroscopic shear stress  $\Sigma_{13}$  and the shear stress in the plastic channel  $\sigma_{13}^C$ , therefore  $X = 2\mu f \varepsilon_{13}^P$ . Since the macroscopic plastic shear strain is  $E_{13}^P = (1-f)\varepsilon_{13}^P$ , the kinematic hardening is given by  $X = 2\mu \frac{f}{(1-f)} E_{13}^P$ . Therefore, a linear kinematic hardening modulus (i.e. hardening slope) of  $2\mu \frac{f}{(1-f)}$  is obtained. This value was verified for both volume fractions  $f = 0.125$  and  $f = 0.3125$  with the classic CP-EVPFFT model using Figure 2. Such hardening slope was also reported by Mughrabi [46]. From Figure 3 in the case of  $f = 0.125$ , the evolution of the plastic distortion  $U_{13}^P$  and shear stress  $\sigma_{13}$  are studied at 4 different loading states (denoted A, B, C, D) during one shear loading cycle, i.e. forward/reverse/forward shear for one cycle. Figures 4 and 5 describe the spatial variations of  $U_{13}^P$  and  $\sigma_{13}$ , respectively, along the  $y$  direction for A, B, C, D. Figure 4 shows that the plastic distortion is uniform in the channel and this result is independent of the spatial period  $H$ . At macroscopic shear strain  $E_{13} = \langle \varepsilon_{13} \rangle = 0.2\%$  (i.e. at the end of forward loading), it is seen from Figure 5 that  $\sigma_{13}^P = 103.7MPa$  and  $\sigma_{13}^C = 7.4MPa$ . The macroscopic shear stress is  $\Sigma_{13} = 19.4MPa$ , therefore the residual stresses in both phases are  $R^P = 84.3MPa$  and  $R^C = -12MPa$ , respectively. From Figure 4,  $U_{13}^P = 0.37\%$  at  $E_{13} = \langle \varepsilon_{13} \rangle = 0.2\%$  (i.e.  $\varepsilon_{13}^P = 0.185\%$  at A), i.e. Eqs. 22 are satisfied.


Using the incompatibility relation  $\boldsymbol{\alpha} = \mathbf{curl} \mathbf{U}^e$  [34, 35] solved in the Fourier space with a centered finite difference scheme (see numerical details in [11, 19]), the profiles of the GND density  $\alpha_{11}/b$  are obtained at the different states. Figure 6 shows a rapid change of sign from

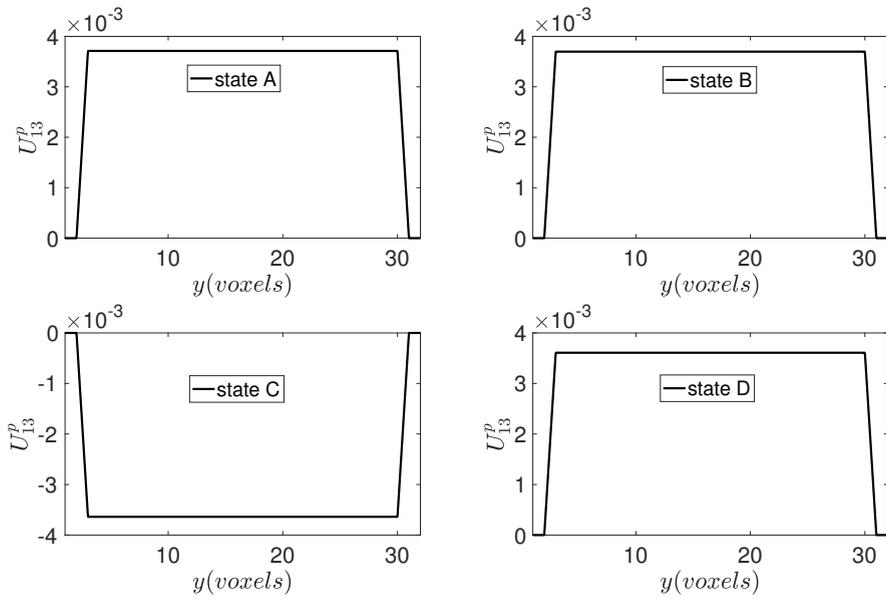

**Figure 4.** Spatial variations along the  $y$ -axis in voxels of the plastic distortion  $U_{13}^p$  at the 4 different states: A, B, C, D.

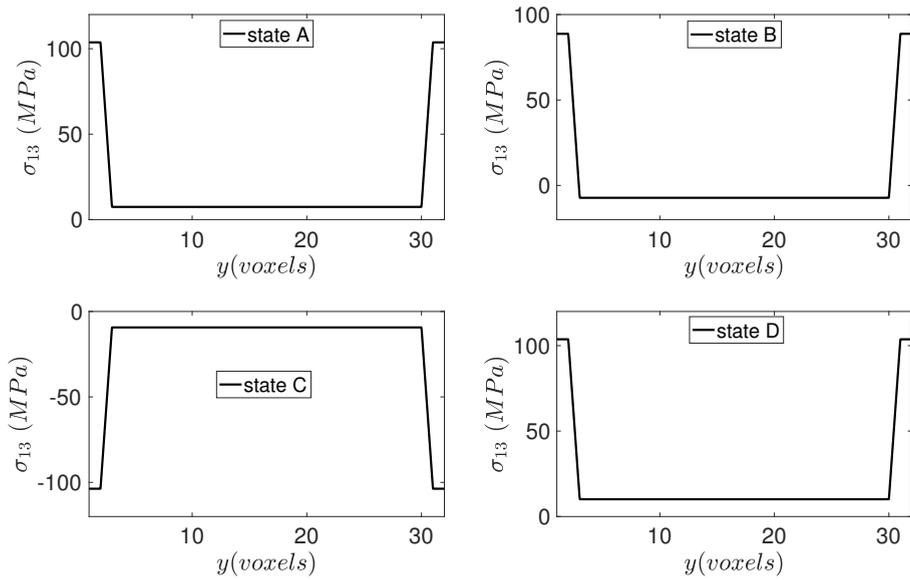

**Figure 5.** Spatial variations along the  $y$ -axis in voxels of the shear stress  $\sigma_{13}$  at the 4 different states: A, B, C, D.

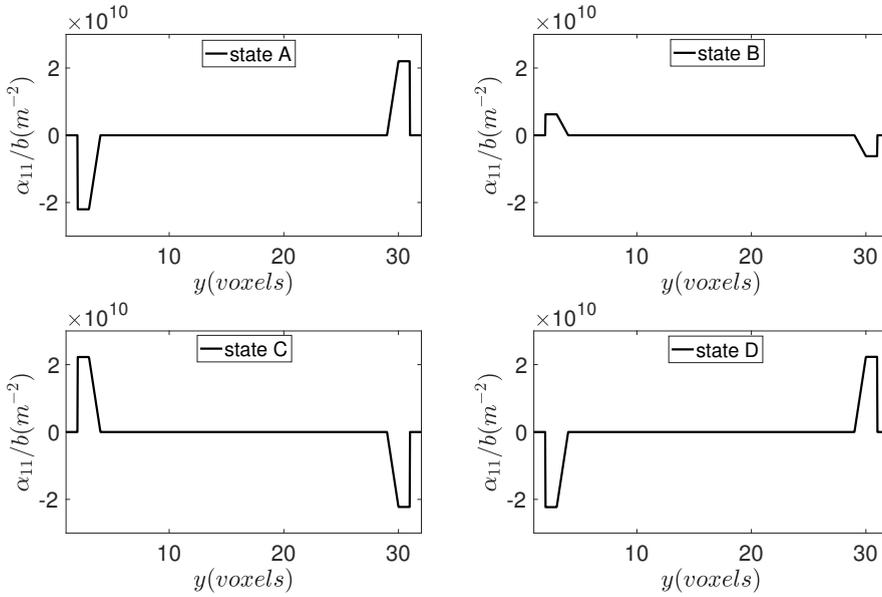


**Figure 6.** Spatial variations along the  $y$ -axis in voxels of the GND density  $\alpha_{11}/b$  at the 4 different states: A, B, C and D.

state B for the GND densities during reverse loading compared to the ones at state A. This leads to an inversion of plastic incompatibilities at the interfaces in the transition between A and C. Such GND densities are low in magnitude with maximal values around  $2 \times 10^{10} m^{-2}$  and they correspond to interfacial GND densities [56]. Therefore, CP-EVPFFT predicts no development of GND pile ups and the relaxation of piecewise constant internal stresses during the transition between forward and reverse strain paths (see Figure 5) explains the rapid transition to a linear *permanent softening* after the onset of plasticity during reverse loading, i.e. after  $\Sigma_r$ .

### 3.3. Cyclic plasticity responses obtained with MFDM-EVPFFT

Let us consider the case where the volume fraction of elastic second phase is set to  $f = 0.125$  with three different periods:  $H = 0.25 \mu m$ ,  $H = 1 \mu m$ ,  $H = 10 \mu m$ . The role of the material parameter  $k_0$  in Eq. 9 is first examined. This parameter is a fitting parameter used in the phenomenological MFDM formulation to modulate the effect of GND densities on the material's isotropic hardening. An increase of  $k_0$  means a decrease of the geometric mean-free path due to forest GND. Figures 7 and 8 report a “*smaller is stronger*” size effect observed on both  $\Sigma_f$  (at  $E_{13} = 0.2\%$ ) and  $\Sigma_b$  for  $k_0 = 20$  and  $k_0 = 500$ , respectively. Comparing the values reported in Tables 2 and 3, this size effect is more pronounced for  $k_0 = 500$ . When  $H$  is large, it is also observed that the *permanent softening* during reverse loading rapidly converges to the CP-EVPFFT result (Figure 3). Conversely, for the smallest size ( $H = 0.25 \mu m$ ), a larger *transient softening* occurs before *permanent softening*, as reported for example in [16] for particulate reinforced Al alloys. It corresponds to a larger rounded stress/strain response, which is observed between states A and B. This transient softening is due to a more gradual onset of plasticity during reverse shear due to plastic strain gradients in plastic channels. This effect is even more pronounced in the case of  $k_0 = 500$  in Figure 9, where the presence of inflection points is also reported during the first reverse loading and during last forward loading to form a hysteresis loop. However, it is noteworthy that the loop is

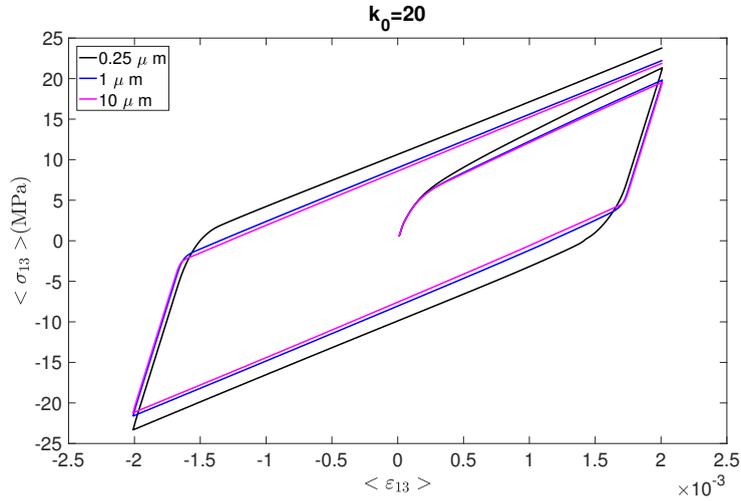

**Figure 7.** Effect of period  $H$  ( $H = 0.25\mu m$ ,  $H = 1\mu m$ ,  $H = 10\mu m$ ) with MFDM-EVPFFT for an elastic phase volume fraction  $f = 0.125$  on the cyclic shear response of two-phase laminate microstructures. The value of  $k_0$  is set to  $k_0 = 20$ .

not completely closed since the hardening is not purely kinematic due to the presence of the isotropic intra-crystalline hardening contribution in the model, see Eq. 9.

In contrast with strain gradient plasticity and Cosserat models, such as the ones described by Forest [23], the present formulation does not provide an *explicit* expression of intra-crystalline backstress involving the *second derivative of slip* in the channel. This explicit dependence stems from the presence of a couple stress tensor in the balance of moment of momentum. In addition, a constitutive relationship between the couple stress tensor and the curvature tensor is applied, where the curvature tensor is related to the Nye tensor [49, 34, 35]. Interestingly, a link was made in [23] with the linear kinematic hardening modulus obtained from the dislocation model of Tanaka and Mura [70], based on the static equilibrium of a double-ended edge dislocation pile-up.


**Table 2.** Values of  $\Sigma_f$  (at  $E_{13} = 0.2\%$ ) and  $\Sigma_b$  for  $k_0 = 20$  obtained with the MFDM-EVPFFT formulation.

$H$	$0.25\mu m$	$1\mu m$	$10\mu m$
$\Sigma_f$ (MPa)	21.3	19.8	19.5
$\Sigma_b$ (MPa)	13.8	12.55	12.3

**Table 3.** Values of  $\Sigma_f$  (at  $E_{13} = 0.2\%$ ) and  $\Sigma_b$  for  $k_0 = 500$  obtained with the MFDM-EVPFFT formulation.

$H$	$0.25\mu m$	$1\mu m$	$10\mu m$
$\Sigma_f$ (MPa)	27.9	22	19.6
$\Sigma_b$ (MPa)	16.6	14.25	12.35


In what follows, the evolution of internal fields at 6 different states are studied for  $H = 0.25\mu m$  and  $k_0 = 500$ . These states are denoted  $A$ ,  $B$ ,  $C$ ,  $D$ ,  $E$  and  $F$  in Figure 9. In order to explain

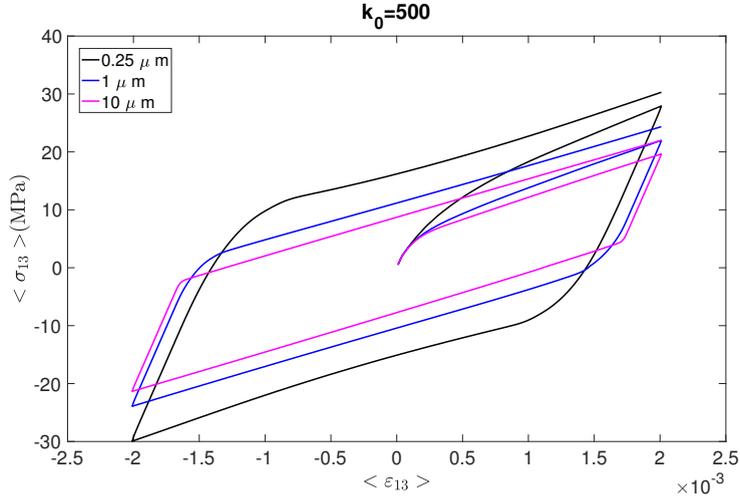

**Figure 8.** Effect of period  $H$  ( $H = 0.25\mu\text{m}$ ,  $H = 1\mu\text{m}$ ,  $H = 10\mu\text{m}$ ) with MFDM-EVPFFT for an elastic phase volume fraction  $f = 0.125$  on the cyclic shear response of two-phase laminate microstructures. The value of  $k_0$  is set to  $k_0 = 500$ .


the transient softening phenomenon with inflection points, obtained with the MFDM-EVPFFT model, let us consider the spatial variation along the  $y$ -direction of the plastic distortion  $U_{13}^p$ , the shear stress  $\sigma_{13}$  and the screw GND density component  $\alpha_{11}/b$ . According to the MFDM-EVPFFT results, the plastic distortion and the stress profiles reported in Figure 10 and Figure 11 respectively exhibit a spatial gradient in the  $y$ -direction of the channel in contrast with the CP-EVPFFT model (see Figure 4). Interestingly, the intra-crystalline slip gradients change sign when the strain is reversed. This can be observed in Figure 10 with a gradual interchange of profile slopes from the middle of the channel to the boundaries, between states  $A$  and  $B/C$ , or, between  $D$  and  $E/F$ . These changes in slopes and the inflexion points observed in the macroscopic response can be explained from the evolution of the GND density component  $\alpha_{11}/b$ , discussed next.

The GND density  $\alpha_{11}/b$  as a function of  $y$  (in voxels) at the 6 different states is shown in Figure 12. At state  $A$ , a continuous screw double-ended GND pile up is first built up at the end of the first forward shear loading, with maximal magnitudes for  $\alpha_{11}/b$  near phase boundaries equal to  $7.8 \times 10^{13} \text{m}^{-2}$ . At state  $B$ , an unpinning-up mechanism operates with the progressive annihilation of the screw GND density built up at stage  $A$ . At stage  $C$ , which corresponds to a state after the inflection point observed on the reverse shear/strain curve, a GND pile up with opposite polarities progressively forms, up to stage  $D$ . At stage  $E$ , which corresponds to the start of the second forward loading in the hysteresis curve, the unpinning-up mechanism operates again with the progressive removal of the GND density built up at stage  $D$ . Finally, at stage  $F$ , a double-ended GND pile up with same polarities as the ones formed at the end of stage  $A$  is restored and is similar to one formed at the end of stage  $A$ . This can be attributed to a plastic memory during cyclic loading and a non linear development of internal stresses due to piling-up / unpinning-up mechanisms as reported by Asaro [7]. Experimental evidence of this specific hardening with concave shape was reported by different authors in Fe-Cr alloys hardened by NiAl intermetallics [69] and in Al-Cu alloys with non-shearable precipitates [67, 53], in which the internal lengths associated with precipitates' interspacing is consistent with the present length-scale used in the MFDM-EVPFFT simulations for  $H = 0.25\mu\text{m}$ . Recently, this effect was simulated and interpreted

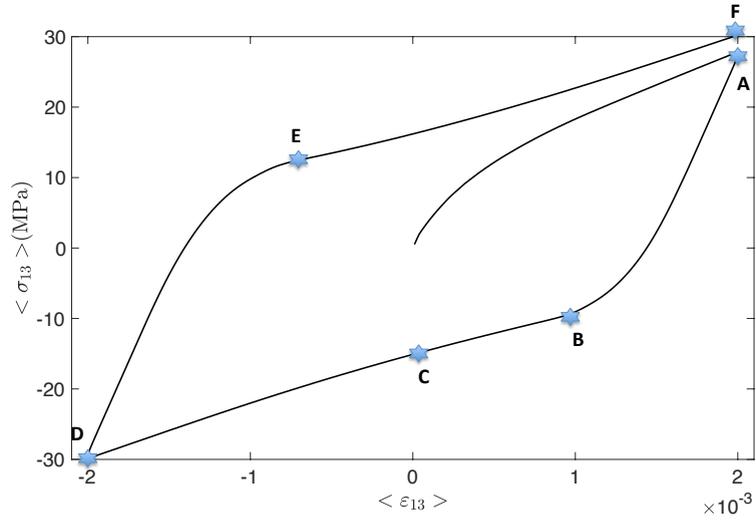


**Figure 9.** Cyclic shear stress response for  $f = 0.125$  obtained with the MFDM-EVPFFT model describing 6 different subsequent states: state *A* (at the end of the first forward shear loading at  $E_{13} = 0.2\%$ ), state *B* (during the reverse shear loading at  $E_{13} = 0.1\%$ ), state *C* (during the reverse shear loading at  $E_{13} = 0\%$ ), state *D* (at the end of the reverse shear loading second forward shear loading at  $E_{13} = -0.2\%$ ), state *E* (during the second forward shear loading at  $E_{13} = -0.07\%$ ), state *F* (at the end of the second forward shear loading at  $E_{13} = 0.2\%$ ).


using higher order strain gradient plasticity theories [51, 75, 22].

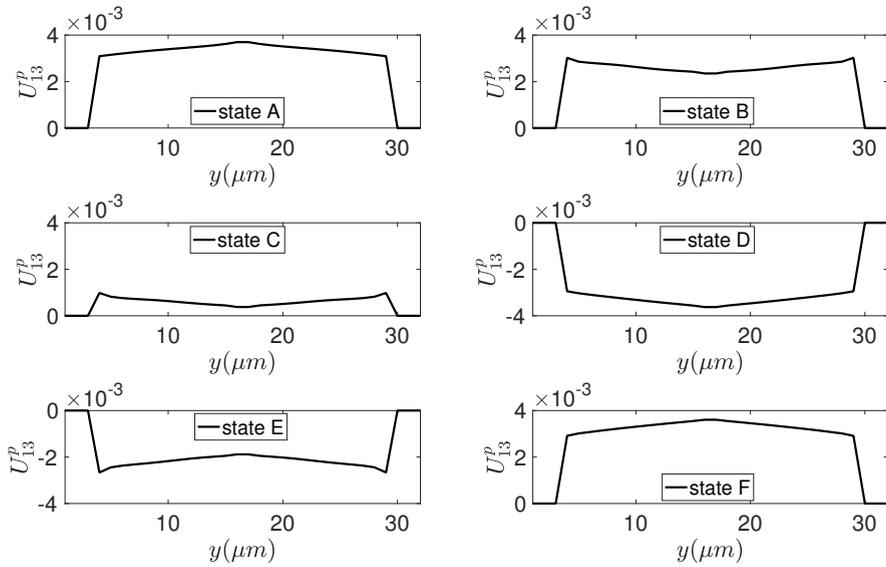

**Figure 10.** Spatial variations along the  $y$ -axis in voxels of the plastic distortion  $U_{13}^p$  at the 6 different states: A, B, C, D, E and F (see Figure 9) for  $H = 0.25\mu\text{m}$  and  $k_0 = 500$ .

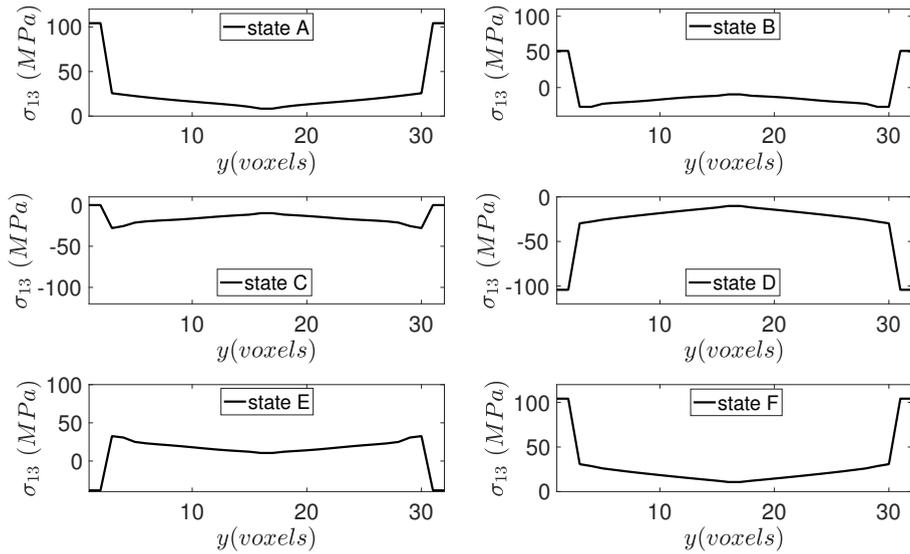

**Figure 11.** Spatial variations along the  $y$ -axis in voxels of the shear stress  $\sigma_{13}$  at the 6 different states: A, B, C, D, E and F (see Figure 9) for  $H = 0.25\mu\text{m}$  and  $k_0 = 500$ .

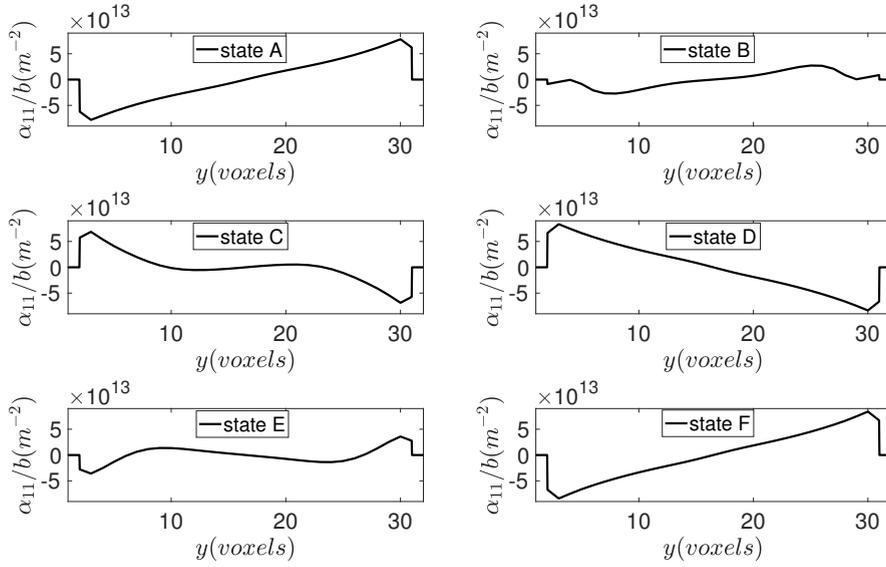

**Figure 12.** Spatial variations along the  $y$ -axis (in voxels) of the GND density  $\alpha_{11}/b$  at the 6 different states:  $A$ ,  $B$ ,  $C$ ,  $D$ ,  $E$  and  $F$  (see Figure 9) for  $H = 0.25\mu m$  and  $k_0 = 500$ .

#### 4. Conclusions

In this study, the MFDM-EVPFFT formulation has been applied to study the reversible plasticity of two-phase laminate microstructures with plastic channels and purely elastic second phase. In contrast with CP-EVPFFT, which only describes for such microstructure a constant permanent softening associated to linear kinematic hardening depending on elastic phase volume fraction, the MFDM-EVPFFT model is able to reproduce size effects on the Bauschinger stress and a non-linear hardening associated with a more complex transient softening with inflection points during reversible plasticity. In particular, hardening mechanisms due to piling up and unpiling up of GND densities at impenetrable interfaces can be reproduced, leading to a gradual relaxation of spatial internal stress gradients during the forward and reversible strain paths.

#### References

- [1] A. Acharya, "A model of crystal plasticity based on the theory of continuously distributed dislocations", *Journal of the Mechanics and Physics of Solids* **49** (2001), p. 761 - 784.
- [2] ———, "Driving forces and boundary conditions in continuum dislocation mechanics", *Proceedings of the Royal Society London A* **459** (2003), p. 1343-1363.
- [3] ———, "Jump condition for GND evolution as a constraint on slip transmission at grain boundaries", *Philosophical Magazine* **87** (2007), p. 1349-1359.
- [4] ———, "Microcanonical entropy and mesoscale dislocation mechanics and plasticity", *Journal of Elasticity* **104** (2011), p. 23-44.
- [5] A. Acharya, A. Roy, "Size effects and idealized dislocation microstructure at small scales : Predictions of a Phenomenological model of Mesoscopic Field Dislocation Mechanics : Part I", *Journal of the Mechanics and Physics of Solids* **54** (2006), p. 1687-1710.
- [6] R. Arora, A. Acharya, "Dislocation pattern formation in finite deformation crystal plasticity.", *International Journal of Solids and Structures* **184** (2020), p. 114-135.
- [7] R. J. Asaro, "Elastic-plastic memory and kinematic-type hardening", *Acta Metallurgica* **23** (1975), p. 1255-1265.

- [8] M. F. Ashby, "Deformation of plastically non-homogeneous materials", *Philosophical Magazine* **21** (1970), p. 399-424.
- [9] J. D. Atkinson, L. M. Brown, W. M. Stobbs, "The work-hardening of copper-silica. IV The Bauschinger effect and plastic relaxation", *Philosophical Magazine* **30** (1974), p. 1247-1280.
- [10] D. S. Balint, V. S. Deshpande, A. Needleman, E. Van der Giessen, "Discrete dislocation plasticity analysis of the grain size dependence of the flow strength of polycrystals", *International Journal of Plasticity* **24** (2010), p. 2149-2172.
- [11] S. Berbenni, V. Taupin, K. S. Djaka, C. Fressengeas, "A numerical spectral approach for solving elasto-static field dislocation and g-disclination mechanics", *International Journal of Solids and Structures* **51** (2014), p. 4157-4175.
- [12] S. Berbenni, V. Taupin, R. A. Lebensohn, "A fast Fourier transform-based mesoscale field dislocation mechanics study of grain size effects and reversible plasticity in polycrystals", *Journal of the Mechanics and Physics of Solids* **135** (2020), p. 103808.
- [13] N. Bertin, L. Capolungo, "A FFT-based formulation for discrete dislocation dynamics in heterogeneous media", *Journal of Computational Physics* **355** (2018), p. 366-384.
- [14] N. Bertin, M. V. Upadhyay, C. Pradalier, L. Capolungo, "A FFT-based formulation for efficient mechanical fields computation in isotropic and anisotropic periodic discrete dislocation dynamics", *Modelling and Simulation in Materials Science and Engineering* **23** (2015), p. 065009.
- [15] R. Brenner, A. J. Beaudoin, P. Suquet, A. Acharya, "Numerical implementation of static Field Dislocation Mechanics theory for periodic media", *Philosophical Magazine* (2014), p. 1-24.
- [16] S. F. Corbin, D. S. Wilkinson, J. D. Embury, "The Bauschinger effect in a particulate reinforced Al alloy", *Materials Science Engineering A* **207** (1996), p. 1-11.
- [17] N. M. Cordero, A. Gaubert, S. Forest, E. P. Busso, F. Galerneau, S. Kruch, "Size effects in generalised continuum crystal plasticity for two-phase laminates", *Journal of the Mechanics and Physics of Solids* **58** (2010), p. 1963-1994.
- [18] K. Danas, V. S. Deshpande, N. A. Fleck, "Compliant interfaces: a mechanism for relaxation of dislocation pile-ups in a sheared single crystal", *International Journal of Plasticity* **26** (2010), p. 1792-1805.
- [19] K. S. Djaka, S. Berbenni, V. Taupin, R. A. Lebensohn, "A FFT-based numerical implementation of mesoscale field dislocation mechanics: application to two-phase laminates", *International Journal of Solids and Structures* **184** (2020), p. 136-152.
- [20] K. S. Djaka, V. Taupin, S. Berbenni, C. Fressengeas, "A numerical spectral approach to solve the dislocation density transport equation", *Modelling and Simulation in Materials Science and Engineering* **23** (2015), p. 065008(27pp).
- [21] K. S. Djaka, A. Villani, V. Taupin, L. Capolungo, S. Berbenni, "Field Dislocation Mechanics for heterogeneous elastic materials: A numerical spectral approach", *Computer Methods in Applied Mechanics and Engineering* **315** (2017), p. 921-942.
- [22] S. A. El-Naaman, K. L. Nielsen, C. F. Niordson, "An investigation of back stress formulations under cyclic loading", *Mechanics of Materials* **130** (2019), p. 76-87.
- [23] S. Forest, "Some links between Cosserat, strain gradient crystal plasticity and the statistical theory of dislocations.", *Philosophical Magazine* **88** (2008), p. 30-32.
- [24] J. Gené, S. Berbenni, N. Gey, R. A. Lebensohn, F. Bonnet, "Particle interspacing effects on the mechanical behavior of a Fe-TiB<sub>2</sub> metal matrix composite using FFT-based mesoscopic field dislocation mechanics", *Advanced Modeling and Simulation in Engineering Sciences* **7** (2020), p. 1-23.
- [25] J. T. Graham, A. D. Rollett, R. LeSar, "Fast Fourier transform discrete dislocation dynamics", *Modelling and Simulation in Materials Science and Engineering* **8** (2016), p. 085005.
- [26] I. Groma, F. F. Csikor, M. Zaiser, "Spatial correlations and higher-order gradient terms in a continuum description of dislocation dynamics", *Acta Materialia* **51** (2003), p. 1271-1281.
- [27] S. Gupta, A. J. Beaudoin, J. Chevy, "Strain rate jump induced negative strain rate sensitivity (NSRS) in aluminium alloy 2024: Experiments and constitutive modeling", *Materials Science Engineering A* **683** (2017), p. 143-152.
- [28] M. E. Gurtin, "A gradient theory of single-crystal viscoplasticity that accounts for the geometrically necessary dislocations", *Journal of the Mechanics and Physics of Solids* **50** (2002), p. 5-32.
- [29] P. J. Guruprasad, W. J. Carter, A. A. Benzerga, "A discrete dislocation analysis of the Bauschinger effect in microcrystals", *Acta Materialia* **56** (2008), p. 5477-5491.
- [30] S. Haouala, S. Lucarini, J. Llorca, J. Segurado, "Simulation of the Hall-Petch effect in FCC polycrystals by means of strain gradient crystal plasticity and FFT homogenization", *Journal of the Mechanics and Physics of Solids* **134** (2020), p. 103755.
- [31] T. Hochrainer, S. Sandfeld, M. Zaiser, P. Gumbsch, "Continuum dislocation dynamics: towards a physically theory of plasticity", *Journal of the Mechanics and Physics of Solids* **63** (2014), p. 167-178.
- [32] M. Jebahi, L. Cai, F. Abed-Meraim, "Strain gradient crystal plasticity model based on generalized non-quadratic defect energy and uncoupled dissipation.", *International Journal of Plasticity* **126** (2020), p. 102617.
- [33] M. Jiang, B. Devincre, G. Monnet, "Effects of the grain size and shape on the flow stress: A dislocation dynamics study", *International Journal of Plasticity* **113** (2019), p. 111-124.
- [34] E. Kröner, *Kontinuumstheorie der Versetzungen und Eigenspannungen*, Collatz L and Loesch F (eds.). Ergebnisse der Angewandte Mathematik 5, Springer Verlag, Berlin, 1958.

- [35] E. Kröner, "Continuum theory of defects", In: *Balian R et al (Eds) Physics of defects Les Houches Session 35 North Holland, New York* (1981), p. 215-315.
- [36] R. A. Lebensohn, "N-site modeling of a 3D viscoplastic polycrystal using Fast Fourier Transform", *Acta Materialia* **49** (2001), p. 2723-2737.
- [37] R. A. Lebensohn, R. Brenner, O. Castelnau, A. Rollett, "Orientation image-based micromechanical modelling of subgrain texture evolution in polycrystalline copper", *Acta Materialia* **56** (2008), p. 3914-3926.
- [38] R. A. Lebensohn, A. K. Kanjarla, P. Eisenlohr, "An elasto-viscoplastic formulation based on Fast Fourier Transforms for the prediction of micromechanical fields in polycrystalline materials", *International Journal of Plasticity* **32-33** (2012), p. 59-69.
- [39] R. A. Lebensohn, A. Needleman, "Numerical implementation of non-local polycrystal plasticity using fast Fourier transforms", *Journal of the Mechanics and Physics of Solids* **97** (2016), p. 333-351.
- [40] B. Liu, D. Raabe, F. Roters, P. Eisenlohr, R. A. Lebensohn, "Comparison of finite element and fast Fourier transform crystal plasticity solvers for texture prediction", *Modelling and Simulation in Materials Science and Engineering* **18** (2009), p. 085005.
- [41] S. Lucarini, J. Segurado, "On the accuracy of spectral solvers for micromechanics based fatigue modeling", *Computational Mechanics* **63** (2019), p. 365-382.
- [42] A. Marano, L. Gélébart, S. Forest, "Intragranular localization induced by softening crystal plasticity analysis of slip and kink bands localization modes from high resolution FFT-simulations results", *Acta Materialia* **175** (2018), p. 262-275.
- [43] J. C. Michel, H. Moulinec, P. Suquet, "A computational scheme for linear and non-linear composites with arbitrary phase contrast", *International Journal of Numerical Methods Engineering* **52** (2001), p. 139-160.
- [44] H. Moulinec, P. Suquet, "A fast numerical method for computing the linear and non linear properties of composites", *Comptes Rendus de l'Académie des Sciences de Paris II* **318** (1994), p. 1417-1423.
- [45] ———, "A numerical method for computing the overall response of nonlinear composites with complex microstructure", *Computer Methods in Applied Mechanics and Engineering* **157** (1998), p. 69-94.
- [46] H. Mughrabi, "Dislocation clustering and long-range internal stresses in monotonically and cyclically deformed metal crystals.", *Revue Physique Appliquée*. **23** (1988), p. 367-379.
- [47] T. Mura, "Continuous distribution of moving dislocations", *Philosophical Magazine* **89** (1963), p. 843-857.
- [48] L. Nicola, Y. Xiang, J. Vlassak, E. VanderGiessen, A. Needleman, "Plastic deformation of freestanding thin films: experiments and modeling", *Journal of the Mechanics and Physics of Solids* **54** (2006), p. 2089-2110.
- [49] J. E. Nye, "Some geometrical relations in dislocated crystals", *Acta Materialia* **1** (1953), p. 153-162.
- [50] N. Ohno, D. Okumura, "Higher-order stress and grain size effects due to self-energy of geometrically dislocations", *Journal of the Mechanics and Physics of Solids* **55** (2007), p. 1879-1898.
- [51] N. Ohno, D. Okumura, T. Shibata, "Grain size dependent yield behavior under loading, unloading and reverse loading", *International Journal of Modern Physics B* **22** (2008), p. 5937-5942.
- [52] A. Panteghini, L. Bardella, C. F. Niordson, "A potential for higher-order phenomenological strain gradient plasticity to predict reliable response under non-proportional loading.", *Proceedings of the Royal Society A* **475** (2019), p. 0258.
- [53] H. Proudhon, W. Poole, X. Wang, Y. Bréchet, "The role of internal stresses on the plastic deformation of the Al-Mg-Si-Cu alloy AA611", *Philosophical Magazine* **88** (2008), p. 621-640.
- [54] S. Puri, A. Das, A. Acharya, "Mechanical response of multicrystalline thin films in mesoscale field dislocation mechanics", *Journal of the Mechanics and Physics of Solids* **59** (2011), p. 2400-2417.
- [55] S. Puri, A. Roy, "Plastic deformation of multicrystalline thin films: Grain size distribution vs. grain orientation", *Computational Materials Science* **52** (2012), p. 20-24.
- [56] C. Rey, G. Saada, "The elastic field of periodic dislocation networks", *Philosophical Magazine* **33** (1976), p. 82541.
- [57] C. Rey, A. Zaoui, "Slip heterogeneities in deformed aluminium bi-crystals", *Acta Metallurgica* **28** (1980), p. 687-697.
- [58] T. Richeton, L. T. Le, T. Chauve, M. Bernacki, S. Berbenni, M. Montagnat, "Modelling the transport of geometrically necessary dislocations on slip systems: application to single and multi-crystals of ice", *Modelling and Simulation in Materials Science and Engineering* **25** (2017), p. 025010(27pp).
- [59] T. Richeton, G. F. Wang, C. Fressengeas, "Continuity constraints at the interfaces and their consequences on the work hardening of metal-matrix composites", *Journal of the Mechanics and Physics of Solids* **59** (2011), p. 2023-2043.
- [60] A. Roy, A. Acharya, "Finite element approximation of field dislocation mechanics", *Journal of the Mechanics and Physics of Solids* **53** (2005), p. 143-170.
- [61] ———, "Size effects and idealized dislocation microstructure at small scales : Predictions of a Phenomenological model of Mesoscopic Field Dislocation Mechanics : Part II", *Journal of the Mechanics and Physics of Solids* **54** (2006), p. 1711-1743.
- [62] A. Roy, S. Puri, A. Acharya, "Phenomenological mesoscopic field dislocation mechanics, lower-order gradient plasticity, and transport of mean excess dislocation density", *Modelling and Simulation in Materials Science and Engineering* **15** (2007), p. 167-180.

- [63] M. Rys, H. Petryk, "Gradient crystal plasticity models with a natural length scale in the hardening law", *International Journal of Plasticity* **111** (2018), p. 168-187.
- [64] S. Sandfeld, T. Hochrainer, P. Gumbsch, M. Zaiser, "Numerical implementation of 3D continuum theory of dislocation dynamics and application to micro-bending", *Philosophical Magazine* **90(27-28)** (2010), p. 3697-3728.
- [65] K. Schulz, D. Dickel, S. Schmitt, S. Sandfeld, D. Weygand, "Analysis of dislocation pile-ups using a dislocation-based continuum theory", *Modelling and Simulation in Materials Science and Engineering* **22** (2010), p. 025008.
- [66] P. Shanthraj, P. Eisenlohr, M. Diehl, F. Roters, "Numerically robust spectral methods for crystal plasticity simulations of heterogeneous materials", *International Journal of Plasticity* **66** (2015), p. 31-45.
- [67] R. Stoltz, R. Pelloux, "The Bauschinger effect in precipitation strengthened aluminum alloys", *Metallurgical Transactions A* **7** (1975), p. 1295-1306.
- [68] P. Suquet, H. Moulinec, O. Castelnau, M. Montagnat, N. Lahellec, F. Grennerat, P. Duval, R. Brenner, "Multi-scale modeling of the mechanical behavior of polycrystalline ice under transient creep", *Procedia IUTAM* **3** (2012), p. 76-90.
- [69] R. Taillard, A. Pineau, "Room temperature tensile properties of Fe-19wt.%Cr alloys precipitation hardened by the intermetallic compound NiAl", *Materials Science Engineering* **56** (1982), p. 219-231.
- [70] K. Tanaka, T. Mura, "A dislocation model for fatigue crack initiation.", *ASME Journal of Applied Mechanics* **48** (1981), p. 97-103.
- [71] V. Taupin, S. Varadhan, J. Chevy, C. Fressengeas, A. J. Beaudoin, M. Montagnat, P. Duval, "Effects of size on the dynamics of dislocations in ice single crystals", *Physical Review Letters* **99** (2007), p. 155507.
- [72] S. Varadhan, A. J. Baudoin, A. Acharya, C. Fressengeas, "Dislocation transport using Galerkin/least squares formulation", *Modelling and Simulation in Materials Science and Engineering* **14** (2006), p. 1245-1270.
- [73] S. Waheed, R. Hao, A. Bhowmik, D. S. Balint, F. Giuliani, "A unifying scaling for the Bauschinger effect in highly confined thin films: a discrete dislocation plasticity study", *Modelling and Simulation in Materials Science and Engineering* **25** (2017), no. 5, p. 054003.
- [74] F. Willot, "Fourier-based schemes for computing the mechanical response of composites with accurate local fields", *Comptes Rendus Mécanique* **343** (2015), p. 232-245.
- [75] S. Wulfinghoff, S. Forest, T. Böhlke, "Strain gradient plasticity modeling of cyclic behavior of laminate structures", *Journal of the Mechanics and Physics of Solids* **79** (2015), p. 1-20.
- [76] M. Zaiser, T. Hochrainer, "Some steps towards a continuum representation of 3D dislocation systems", *Scripta Materialia* **54** (2006), p. 717-721.
- [77] C. Zhou, R. LeSar, "Dislocation dynamics simulations of the Bauschinger effect in metallic thin films", *Computational Materials Science* **54** (2012), p. 350-355.