



HAL
open science

Mn₃O₄@ZnO Hybrid Material: An excellent photocatalyst for the degradation of synthetic dyes including methylene blue, methyl orange and malachite green

Benazir Shaikh, Muhammad Ali Bhatti, Aqeel Ahmed Shah, Aneela Tahira, Abdul Karim Shah, Azam Usto, Umair Aftab, Sarah Bukhari, Sultan Alshehri, Syed Nizam Uddin Shah Bukhari, et al.

► To cite this version:

Benazir Shaikh, Muhammad Ali Bhatti, Aqeel Ahmed Shah, Aneela Tahira, Abdul Karim Shah, et al.. Mn₃O₄@ZnO Hybrid Material: An excellent photocatalyst for the degradation of synthetic dyes including methylene blue, methyl orange and malachite green. *Nanomaterials*, 2022, 12 (21), pp.3754. 10.3390/nano12213754 . hal-04198761

HAL Id: hal-04198761

<https://hal.univ-lorraine.fr/hal-04198761>

Submitted on 7 Sep 2023

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Mn₃O₄@ZnO hybrid material: An excellent photocatalyst for the degradation of synthetic dyes including methylene blue, methyl orange and malachite green

Benazir Shaikh^a, Muhammad Ali Bhatti^a, Aqeel Ahmed Shah^b, Aneela Tahira^{c*}, Abdul Karim Shah^d, Azam Usto^d, Umair Aftab^e, Sarah I Bukhari^f, Sultan Alshehri^f, Syed Nizam Uddin Shah Bukhari^{g,h}, Matteo Tonezzerⁱ, Brigitte Vigolo^j, Zafar Hussain Ibupoto^{c*}

^aInstitute of Environmental Sciences, University of Sindh Jamshoro, 76080, Sindh Pakistan

^bWet Chemistry Laboratory, Department of Metallurgical Engineering, NED University of Engineering and Technology, Karachi, Sindh Pakistan

^cDr. M.A Kazi Institute of Chemistry University of Sindh Jamshoro, 76080, Sindh Pakistan

^dDepartment of Chemical Engineering, Dawood University of Engineering and Technology, Karachi, Pakistan

^eDepartment of Metallurgy and Materials Engineering, Mehran University of Engineering and Technology, 7680 Jamshoro, Sindh Pakistan

^fDepartment of Pharmaceutics, College of Pharmacy, King Saud University, Riyadh 11451, Saudi Arabia

^gState Key Laboratory of Organic-Inorganic Composites, Beijing Key Laboratory of Electrochemical Process and Technology for Materials, school of Material Science, Beijing University of Chemical Technology, Beijing, 100029 China

^hDepartment of Basic Science and Humanities, Dawood University of Engineering and Technology, Karachi, Sindh, 74800 Pakistan

ⁱMEM-CNR, Sede di Trento-FBK, Via alla Cascata 56/C, 38123 Trento, Italy

^jUniversité de Lorraine, CNRS, IJL, F-54000 Nancy, France

* Correspondence: **authors:** Zafar Hussain Ibupoto & Aneela Tahira

Email: zaffar.ibupoto@usindh.edu.pk; aneelatahira80@gmail.com

Abstract: Environmental pollution caused by organic dyes threatens life on land and in water. Therefore, immediate planning and action is needed to eliminate environmental pollution using new technologies, but sadly to this date it has remained a challenging task. In this study, we synthesized hybrid systems based on zinc oxide/manganese oxide (Mn₃O₄@ZnO) using sol gel and hydrothermal methods. The hybrid materials exhibited hierarchical morphologies and structures characterized by the hexagonal phase of ZnO and the tetragonal phase of Mn₃O₄. The hybrid materials were tested for degradation of methylene blue (MB), methyl orange (MO), and malachite green (MG) under ultraviolet (UV) light illumination. In the aim of this work was to observe the effect that various amounts of Mn₃O₄ in the hybrid material have on the degradation of MB, MO and MG. The ZnO photocatalyst showed better performance with an increasing amount of Mn₃O₄ and the degradation efficiency for the hybrid material containing the maximum amount of Mn₃O₄ was found to be 94.59 %, 89.99 % and 97.40 % for MB, MO and MG, respectively. The improvement in the performance of hybrid materials can be attributed to high charge separation rate of electron-hole pairs, co-catalytic role, large amount of catalytic sites and the synergy for the production of high quantities of oxidizing radicals. The performance obtained from the various Mn₃O₄@ZnO hybrid materials suggest that Mn₃O₄ can be considered an effective co-catalyst for a wide range of photocatalytic materials such as titanium dioxide, tin oxide and carbon-based materials in developing practical hybrid photocatalysts for the degradation of dyes and wastewater treatment.

Keywords: ZnO; Mn₃O₄; Mn₃O₄@ZnO; hybrid material; photocatalytic applications

1. Introduction

Environmental pollution caused by the extensive use of synthetic dyes, pigments and other coloring products in various industries such as food, beverages, cosmetics, pharmaceuticals, clothes and paper [1]. These chemical compounds are characterized by a complicated structure, high stability and are highly toxic to living things. In addition, the presence of dyes in wastewater prevents the transmission of sunlight deep into the water, damaging aquatic life. At the same time, these dyes are harmful to humans by causing breathing problems, vomiting, cancer, allergies, and skin problems [2]. Approximately 700000 tons of dyes are produced worldwide each year, and many end up in the wastewater of the textile industries, contaminating water resources and aquatic life as they are very toxic to our environment [3, 4]. Among them, malachite green (MG) and methylene blue (MB) are cationic, while methyl orange (MO) is anionic in nature [5,6].

Currently, the removal and degradation of dyes from wastewater before discharging it from reservoirs is seriously considered, but it still seems like a very difficult challenge. There are numerous methods for wastewater treatment

including coagulation, electro precipitation, adsorption, evaporation, reverse osmosis, flocculation, oxidation and photodegradation under the illumination of ultraviolet and solar light [7, 8]. Many of these methods are complicated, expensive, and have poor dye removal performance, while photodegradation is a simple, low cost and efficient method of removing organic dyes from wastewater [9, 10]. The challenge in photocatalytic degradation is the unavailability of highly efficient yet inexpensive photocatalysts. For this purpose, several photocatalytic materials have been prepared and tested for the degradation of dyes, such as ZnO [11], BiFeO₃ [12], TiO₂ [10], Cu₂O/LDH [13], Chitosan ZnO composite [14], CuCl₂ + STS, chitosan-g-Poly (acrylamide)/ZnS [15], Chitosan/LaFe_{0.8}Cu_{0.2}O₃ and xylan/LaFe_{0.8}Cu_{0.2}O₃ [16].

Among these well-known semiconducting materials, ZnO is highly studied for various applications including photocatalysis, chemical sensing and photovoltaics due to its tunable band gap (3.37 eV) and high exciton binding energy (60 meV) [17,18,19,20]. The role of the nanostructured morphology of ZnO is intensively investigated, therefore different morphologies of ZnO are reported such as 3D hollow spheres, 1D nanorods and nanowires and 2D nanobelts and nanosheets [21,22,23,24]. The advantageous features of these morphologies such as swift mass transfer, hierarchical structures and high surface area have been utilized for different applications such as chemical sensors, lithium-ion batteries and photocatalysis [25,26]. However, for the growing concern for the environment requires the development of nanostructured materials without or with minimum use of harmful chemicals [27,28,29]. Therefore, it is essential of synthesize ZnO-based nanostructures with maximum photocatalytic efficacy in an eco-friendly manner. Manganic oxide (Mn₃O₄) is an emerging p-type semiconductor with significant photocatalytic properties [30, 31]. Previously, Mn₃O₄ has demonstrated very good in photocatalytic applications, especially in combination with other metal oxides [32,33,34,35,36,37,38,39,40]. ZnO has many positive aspects such as high quantum efficiency, rich defect chemistry and cost effectiveness, and is therefore widely used for photocatalysis [39, 40]. The synthesis of hierarchical nanostructures of hybrid material based on Mn₃O₄@ZnO with improved electron-hole pairs separation and high density of electrons in the conduction band of ZnO could lead to more efficient photodegradation of MB, MO and MG under ultraviolet light illumination. A hybrid system based on Mn₃O₄@ZnO for efficient degradation of MB, MO and MG has not yet been reported in the exiting scientific literature.

In this study, we prepared the Mn₃O₄@ZnO hybrid material using the sol gel method followed by the hydrothermal method. Morphology, crystalline structure and chemical composition were studied with different analytical techniques such as SEM, XRD and EDS. The optimized Mn₃O₄@ZnO hybrid system revealed excellent photoactivity in the degradation of MB, MO and MG under UV light illumination.


2. Materials and methods

2.1. Materials used

Potassium permanganate (KMnO₄), glycerol, zinc acetate dihydrate, 33% aqueous ammonia, ethanol, sodium hydroxide, hydrochloric acid, methyl orange, methylene blue, and malachite green were purchased from Sigma Aldrich, Karachi Pakistan. The chemicals used were of a high analytical grade and were used without pretreatment. All desired concentrations of each reagent were prepared in deionized water.

2.2. Synthesis of Z Mn₃O₄@ZnO hybrid materials using sol gel and hydrothermal methods

The synthesis of the nanostructured hybrid material was carried out in two steps. The Mn₃O₄ nanostructures were prepared using the sol gel method and the typical synthesis process is described below. The Mn₃O₄ material was reproduced according to the work reported in [41]. Precursor solutions of 0.4 M glycerol and 0.3M potassium permanganate were prepared. Then the glycerol and potassium permanganate solutions were mixed in a ratio of 1:2 by volume, stirred for 2 h and finally kept for 24 h without disturbance to obtain the desired gel at room temperature. Afterwards, the gel was heated at 80 °C for 30 min and the product precipitates were obtained, and centrifugation was used to collect the fine brown colored Mn₃O₄ powder. Meanwhile the precursor ZnO was prepared by mixing 0.1 M of zinc acetate dihydrate and 5 mL of 33% aqueous ammonia solution in 100 mL of deionized water. Different amounts of Mn₃O₄ were deposited on the ZnO by the hydrothermal method: 0.3, 0.5, 0.75 and 1.0 grams of precipitated Mn₃O₄ were dissolved in four beakers containing 200 mL of a precursor solution of ZnO, in in order to develop hybrid Mn₃O₄@ZnO systems. The materials were labeled as sample 1, sample 2, sample 3, and sample 4, respectively. A fifth beaker was only containing the ZnO precursor solution and the pristine ZnO sample was used as a comparison. After being mixed, the solutions were covered very tightly with aluminum foil and left for hydrothermal reaction in a pre-heated electric oven for 5 h at 95 °C. After completion of the reaction, the beakers were cooled down to room temperature and the product was collected on filter paper and washed several times with ethanol followed by deionized water. In the end, the product was dried at 60 °C overnight.

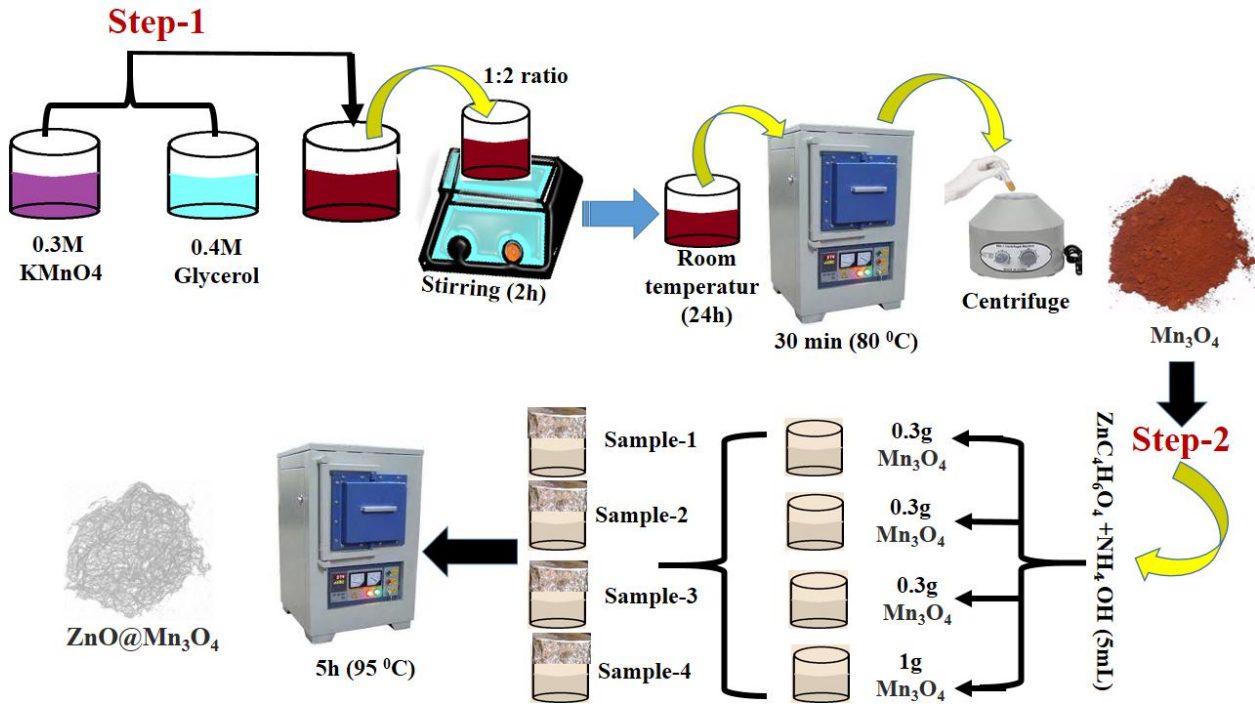

Scheme 1. Stepwise synthesis of $\text{Mn}_3\text{O}_4@\text{ZnO}$ hybrid materials using sol gel and hydrothermal methods.

2.3. Characterization of morphology, crystalline structure, and chemical composition of the materials

Scanning electron microscopy was used at 10 kV to evaluate the morphology of the prepared nanostructured materials. Powder X-ray diffraction was employed at 45 mA and 45 kV to identify the crystal structure and phase of the nanostructured materials. Energy dispersive spectroscopy was used to quantify the elemental composition of each synthesized material. UV-visible spectrophotometry was employed to record absorption spectra during dye degradation under UV light illumination. The UV light source consisted of six UV tubes with a wavelength of 365 nm.

In this study, we studied the performance of hybrid materials for the degradation of various dyes (methylene blue, methyl orange, and malachite green) using 5 mg of each catalyst nanomaterial and a fixed concentration for each dye (1.87×10^{-5} M MB, 2.44×10^{-5} M MO, and 5.48×10^{-5} M MG). Before irradiation with UV light, the dye solution was stirred for 30 min in order to optimize its homogeneity.

The % degradation efficiency of each dye was estimated from the following equation:

$$\text{dye removal \%} = \frac{C_0 - C_t}{C_0} \times 100 \quad (1)$$

where C_0 and C_t are the concentrations of each dye before and after degradation, respectively.

3. Results and discussion

3.1. Characterization of morphology, crystalline structure, and chemical composition of the $\text{Mn}_3\text{O}_4@\text{ZnO}$ hybrid materials

Fig. 1 shows the XRD patterns of the different samples with increasing amounts of Mn_3O_4 . The pattern obtained from the pure ZnO sample shows all the characteristic peaks of the material, as can be seen from the comparison with the black reference at the bottom of the figure (JCPDS sheet: 01-079-0207). In detail, the peaks present at 31.66° , 34.29° , 36.23° , 47.48° , 56.60° , 62.77° and 67.85° can be attributed to the planes (100), (002), (101), (102), (110), (103) and (200) of the hexagonal structure of the ZnO wurtzite. The patterns obtained from the hybrid samples also show the peaks from ZnO, but their relative intensity decreases, while that of the peaks from the tetragonal phase of Mn_3O_4 increases (JCPDS sheet: 00-003-1041, in blue at the bottom of the figure). The XRD patterns shown in Fig. 1 demonstrate that the $\text{Mn}_3\text{O}_4@\text{ZnO}$ hybrid was successfully prepared. The nanomaterial is composed of ZnO and Mn_3O_4 , while no amorphous phases or impurities were observed. As seen in Fig. 1b, the addition of Mn_3O_4 has the effect of slightly shifting the position of peak 220 to higher angles, suggesting an imperfection in the structure of the nanocrystals.

The SEM images in Fig. 2 show the morphology of pure ZnO and of the $\text{Mn}_3\text{O}_4@\text{ZnO}$ hybrids. Pure ZnO appears to be made up of flower-like structures composed of nanorods with a diameter of 200-500 nm (Fig. 2a). Conversely, the morphology of hybrid nanomaterials appears to change towards very thin sheets as the Mn_3O_4 content increases (Fig. 2b-e). The morphology of all the samples is very homogeneous to indicate a good mixing of ZnO and Mn_3O_4 during the

hydrothermal process. The elemental composition of the materials was studied by energy dispersion X-ray spectroscopy, and the spectra are shown in Figure 3. The spectrum of pure ZnO (Fig. 3a) shows only peaks relative to Zn and O, while the other samples show the presence of Zn, O and Mn (Fig. 3b-e). The atomic percentage of manganese increases from Sample 1 to Sample 4, as expected.

3.2. Photocatalytic degradation of MB, MO and MG onto different $Mn_3O_4@ZnO$ hybrid systems

The photodegradation of MB, MO and MG in aqueous solution using pure ZnO and the different hybrid systems $ZnO @ Mn_3O_4$ was studied under UV light illumination.

a. Methylene blue

Figure 4 shows the absorption spectra of pure ZnO during MB degradation over time under UV light illumination. A solution of MB with a concentration of 1.87×10^{-5} M was used to which 5 mg of catalyst was added. The spectra show a typical absorption peak around 663 nm which slowly decreases over time, indicating that the degradation rate is limited and therefore takes a long time. This suggests that pure ZnO exhibits a low density of catalytic sites and a high rate of recombination of the electron-hole pair, and therefore the release of oxidizing agents under illumination is limited, thus leading to poor MB degradation performance. The degradation kinetics was also studied as shown in Figure 4b,c. The reaction rate of MB degradation was evaluated by monitoring the change in concentration C_t over time from the initial concentration C_0 , as shown in Figure 4b. Clearly the photoactivity of pure ZnO is highly correlated to the illumination time. The rate constant (K) of the photodegradation process was also calculated using the first order reaction equation [43]:

$$K_t = \ln(C_0/C_t)$$

The reaction kinetics was also studied as $\ln(C_0/C_t)$ over the illumination time, and is shown in Figure 4c. The rate constant for MB degradation using pure ZnO was found to be 1.14×10^{-3} min, confirming that the reaction follows first order kinetics. The degradation efficiency of pure ZnO photocatalyst was found to be 69.60 % as shown in Figure 4d, indicating that the performance of pure ZnO is not sufficient and the photocatalytic properties must be improved in order to exploit the true potential of this material for practical applications.

The degradation of MB was also performed using the various samples in order to verify how the degradation rate is affected by the composition of the hybrid material, and the spectra are shown in Figure 5a-d. The four panels show that all samples work better as photocatalysts than pure ZnO. Furthermore, comparing the decrease of the absorption spectrum over time in the four panels it is clear that a higher amount of Mn_3O_4 in the hybrid material greatly improves the degradation of MB. This trend could be attributed to the role of Mn_3O_4 in separating the charges of the electron-hole pairs, resulting in the production of a high amount of oxidizing radicals that play an important role in driving the degradation of MB in aqueous solution. The reaction kinetics was investigated for the hybrid samples of $Mn_3O_4@ZnO$ and the ratio between the concentration of MB at a certain time C_t to the initial concentration C_0 is shown in Figure 6a. The degradation of MB on hybrid materials clearly depends on the illumination time. The reaction kinetics in terms of order of reaction was studied by calculating $\ln(C_0/C_t)$ over time (Fig. 6b) and it was found that the rate constant was characterized by first order kinetics. The rate constant (K) values for samples 1, 2, 3 and 4 were estimated to be 3.33×10^{-3} min, 4.19×10^{-3} min, 7.33×10^{-3} min, and 8.51×10^{-3} min, respectively. These values of rate constant suggest that a higher amount of Mn_3O_4 in the hybrid material significantly improves the degradation kinetics of MB in aqueous solution under UV light illumination. The degradation efficiency was calculated from the absorbance spectra and plotted over time for each hybrid system in Figure 6d. The hybrid $Mn_3O_4@ZnO$ system with the highest amount of Mn_3O_4 (sample 4) was the most efficient with a degradation efficiency of 94.59 % for MB. The degradation efficiency of the other hybrid samples 1, 2, and 3 was 82.07 %, 85.28 %, and 92.91 %, respectively.

b. Methyl orange

The photodegradation of methyl orange was investigated with a solution with a concentration of 2.44×10^{-5} M and 5 mg of photocatalyst under UV light illumination. In the case of pure ZnO (Fig. 7), the degradation was found to be very poor due to the stable nature of the material, limited number of active sites and the rapid rate of charge recombination. The absorption trend is very slow, which means that the reaction rate is associated with a high activation energy using pure ZnO as photocatalyst. Poor performance in the degradation of MO by pure ZnO indicates that it is not a suitable material for this application. The reaction kinetics was studied by evaluating the concentration of MO over time C_t with respect to the initial concentration C_0 , and the plot in Fig. 7b shows that the degradation is linear with respect to the irradiation time with UV light. The reaction kinetics with respect to UV light irradiation time turned out to be of the first order and the rate constant was calculated to be 6.44×10^{-4} min⁻¹, as shown in Figure 7c. The degradation efficiency

181 for MO was calculated from the absorption spectra of MO over a time of 320 minutes, and the calculated value was
182 73.56 %, as shown in Figure 7d. The four different hybrid samples were tested for the degradation of MO using a so-
183 lution with a concentration of $2.44 \times 10^{-5} \text{M}$ and 5 mg of each hybrid catalyst. The degradation experiments lasted 240
184 min and an adsorption spectrum was acquired every 30 minutes, as shown in Figure 8. Comparing the plots in Fig. 8
185 with that in Fig. 7a, it is clear, albeit qualitatively, that the degradation is in all cases better than that of pure ZnO. This
186 indicates that the presence of Mn_3O_4 in the $\text{ZnO}@\text{Mn}_3\text{O}_4$ hybrid material increases the density of active sites and de-
187 creases the charge recombination rate of electron-hole pairs. In fact, the degradation of MO increases as the quantity of
188 Mn_3O_4 present in the hybrid photocatalyst increases, i.e. from sample 1 to sample 4. The degradation kinetics of MO
189 was also studied by evaluating how the MO concentration over time C_t varies with respect to the initial concentration
190 C_0 (Fig. 9a). The \ln of as the ratio is instead shown in Figure 9b. As can be seen in both panels, the degradation rate
191 strongly depends on the irradiation time with UV light. The reaction kinetics of the four hybrid photocatalysts are of
192 the first order and the rate constant values obtained for samples 1, 2, 3 and 4 are respectively $2.32 \times 10^{-3} \text{min}^{-1}$,
193 $2.50 \times 10^{-3} \text{min}^{-1}$, $2.74 \times 10^{-3} \text{min}^{-1}$ and $4.58 \times 10^{-3} \text{min}^{-1}$. The percent degradation efficiency of samples 1, 2, 3 and 4 was calculated
194 and found to be 82.78 %, 83.38 %, 85.12 %, and 89.99 %, respectively, as shown in Figure 9c. It is therefore clear that the
195 degradation efficiency for MO increases as the quantity of Mn_3O_4 in the hybrid material increases.

196 c. Malachite green

197 Considering the high toxicity of MG to aquatic life and human health, pure ZnO and $\text{Mn}_3\text{O}_4@\text{ZnO}$ hybrid materi-
198 als were tested for the degradation of MG under UV light illumination. In the experiments, a solution of MG with a
199 concentration of $5.48 \times 10^{-5} \text{M}$ and 5 mg of catalyst were used. Figure 10 shows the maximum absorption peak of MG at
200 617 nm and its evolution over time in the presence of pure ZnO. The adsorption peak decreases confirming the cata-
201 lytic activity, however the degradation process is relatively slow and the efficiency is not very high due to the wide
202 band gap of pure ZnO, its fast charge recombination rate and its low density of catalytic sites. The reaction rate of MG
203 with pure ZnO was studied quantitatively by plotting the ratio between the concentration over time C_t and the initial
204 concentration C_0 , and it is clear that the degradation of MG strongly depends on the time of irradiation with UV light
205 (Figure 10b). Furthermore, plotting $\ln C_0/C_t$ as in Figure 10c, it can be seen that the reaction kinetics are of the first
206 order. The percent degradation efficiency was calculated obtaining a value of 85.37 %, as shown in Figure 10d. The
207 performance of pure ZnO was therefore unsatisfactory, demonstrating that the material must be functionalized to
208 efficiently degrade MG under UV light illumination.

209 In this sense, the hybrid materials $\text{Mn}_3\text{O}_4@\text{ZnO}$ were also tested, whose absorption spectra over time are shown in
210 Figure 11. All materials functionalized with Mn_3O_4 proved to be highly efficient for the degradation of MG, as can be
211 seen from the strong decrease of the absorption peak at 617 nm. Note that the degradation experiment in this case only
212 lasted 70 minutes. Comparing the four panels (a-d) it can be seen that a greater quantity of Mn_3O_4 increases the deg-
213 radation efficiency. The excellent performance of the hybrid materials can therefore be reasonably attributed to of the
214 functionalization with Mn_3O_4 which acts as a co-catalyst and lowers the charge recombination rate of the electron-hole
215 pairs. The synergy of the two materials allows a faster production of oxidizing radicals which increases the degrada-
216 tion rate of MG in aqueous solution. The reaction rate was quantitatively assessed in terms of the change in MG con-
217 centration over time C_t with respect to its initial concentration C_0 , as shown in Figure 12a. The curves show that the
218 degradation of MG in aqueous solution depends on the time of illumination with UV light. The kinetics of the degrada-
219 tion of MG is first order for all hybrid photocatalysts $\text{Mn}_3\text{O}_4@\text{ZnO}$ and the rate constants for samples 1, 2, 3 and 4 are
220 calculated in $1.72 \times 10^{-2} \text{min}^{-1}$, $2.38 \times 10^{-2} \text{min}^{-1}$, $2.73 \times 10^{-2} \text{min}^{-1}$, and $3.01 \times 10^{-2} \text{min}^{-1}$, respectively, as shown in Figure 12b. The
221 degradation efficiency for the four hybrid materials (samples 1, 2, 3 and 4) was calculated as 93.22 %, 95.71 %, 96.67 %, and 97.40 %
222 respectively, as shown in Figure 12c.

223 Overall, the degradation measurements of MB, MO and MG dyes demonstrated that $\text{Mn}_3\text{O}_4@\text{ZnO}$ hybrid
224 nanomaterials are excellent photocatalysts. The photocatalytic activity of the hybrid material with the maximum
225 amount of Mn_3O_4 was the best for all three dyes, reaching almost 100%. For MG The performance of the various
226 $\text{Mn}_3\text{O}_4@\text{ZnO}$ hybrid materials for the degradation of MB, MO and MG is summarized in Table 1.

227 4. Conclusions

228 In this research work, we used sol gel and hydrothermal methods to synthesize different nanostructured materials
229 based on pristine ZnO and functionalized with different amounts of Mn_3O_4 . The morphology turned out to be hierar-
230 chical composed of thin nanosheets, the composition containing only Zn, O and Mn and the structure composed of the
231 hexagonal phases of ZnO and tetragonal of Mn_3O_4 . The degradation performance of all tested dyes (MB, MO and MG)
232 increased as the amount of Mn_3O_4 in the $\text{Mn}_3\text{O}_4@\text{ZnO}$ hybrid photocatalyst increased. The material with the highest

233 amount of Mn_3O_4 (1 g) showed excellent degradation properties for all dyes: 94.59%, 89.99% and 97.40% for MB, MO
234 and MG respectively. The degradation for all dyes followed first order kinetics. The rate constant values for the best
235 catalyst were $8.51 \times 10^{-3} \text{min}^{-1}$ for MB, $4.58 \times 10^{-3} \text{min}^{-1}$ for MO and $3.01 \times 10^{-2} \text{min}^{-1}$ for MG. The improved performance of hy-
236 brid materials can be attributed to the synergy between ZnO and Mn_3O_4 which leads to a high charge separation rate, a
237 high density of catalytic sites and the generation of a large amount of oxidizing reactive species. These improvements
238 suggest that Mn_3O_4 can be used as a dopant to increase the photocatalytic properties of other metal oxides such as TiO_2 ,
239 SnO_2 and carbon-based materials.

240 **Conflict of Interest**

241 Authors declare no conflict of interest in this research study


242 **4. References**

- 243 [1]. K.A. Gusmao, L.V. Gurgel, T.M. Melo, L.F. Gil, *J Environ Manag* 2013, **118**, 135–143.
- 244 [2]. K. Bhattacharya and A. Sharma, Kinetics and thermodynamics of methylene blue adsorption on neem
245 (*Azadirachta indica*) leaf powder. *Dyes Pigments* 2005, **65**(1), 51–59.
- 246 [3]. M. Anbia and S. Salehi, Removal of acid dyes from aqueous media by adsorption onto ami-
247 no-functionalized nanoporous silica SBA-3. *Dyes Pigments* 2012, **94** (1), 1–9.
- 248 [4]. S. Nethaji, A. Sivasamy, G. Thennarasu and S. Saravanan, Adsorption of Malachite Green dye onto
249 activated carbon derived from *Borassus aethiopicum* flower biomass. *J Hazard Mater* 2010, **181** (1–3),
250 271–280.
- 251 [5]. A. M. Saad, M.R. Abukhadra, S.A.K. Ahmed, A.M. Elzanaty, A.H. Mady, M.A. Betiha, J.J. Shim and
252 A.M. Rabie, Photocatalytic degradation of malachite green dye using chitosan supported ZnO and Ce–ZnO
253 nano-flowers under visible light. *J Environ Manage.* 2020, **258**, 110043.
- 254 [6]. A. Mohammadi, H. Daemi and M. Barikani, Fast removal of malachite green dye using novel
255 superparamagnetic sodium alginate-coated Fe_3O_4 nanoparticles *Int J Biol Macromol* 2014, **69**, 447–455
- 256 [7]. M. Jamshidi, M. Ghaedi, K. Dashtian, S. Hajati and A.A. Bazrafshan, Sonochemical assisted hydro-
257 thermal synthesis of ZnO: Cr nanoparticles loaded activated carbon for simultaneous ultrasound-assisted
258 adsorption of ternary toxic organic dye: derivative spectrophotometric, optimization, kinetic and isotherm
259 study. *Ultrason Sonochem* 2016, **32**, 119–131
- 260 [8]. F.N. Azad, M. Ghaedi, K. Dashtian, S. Hajati and V. Pezeshkpour, Ultrasonically assisted hydrothermal
261 synthesis of activated carbon–HKUST-1-MOF hybrid for efficient simultaneous ultrasound-assisted removal
262 of ternary organic dyes and antibacterial investigation: Taguchi optimization. *Ultrason Sonochem* 2016,
263 **31**, 383–393
- 264 [9]. M.S. Chiou and G.S. Chuang, Competitive adsorption of dye metanil yellow and RB15 in acid solutions
265 on chemically cross-linked chitosan beads. *Chemosphere*, 2006, **62**, 731–740
-

-
- 266 [10]. S. Sakthivel, B. Neppolian, M.V. Shankar, B. Arabindoo, M. Palanichamy and V. Murugesan, Solar
267 photocatalytic degradation of azo dye: comparison of photocatalytic efficiency of ZnO and TiO₂. *Sol En-*
268 *ergy Mater Sol Cells*, 2003, **77**(1),65–82.
- 269 [11]. J.H. Sun, S.Y. Dong, J.L. Feng, X.J. Yin and X.C. Zhao, Enhanced sunlight photocatalytic perfor-
270 mance of Sn-doped ZnO for Methylene Blue degradation. *J Mol Catal A Chem*, 2011, **335**,145–150.
- 271 [12]. L. Di, H. Yanga, T. Xian and X. Chen, Facile synthesis and enhanced visible-light photocatalytic ac-
272 tivity of novel p-Ag₃PO₄/n-BiFeO₃ heterojunction composites for dye degradation. *Nanoscale Res Lett*,
273 2018, **21**(5), 1–13.
- 274 [13]. Y. Zhou, H. Wenjihao, Yu. Jingang and F. Jiao, Effective photocatalytic degradation of methylene blue
275 by Cu₂O/MgAl layered double hydroxides. *React Kinet Mech Catal* 2015, **115**, 581–596.
- 276 [14]. Y. Haldorai and J.J. Shim, hitosan-zinc oxide hybrid composite for enhanced dye degradation and an-
277 tibacterial activity. *Composite Interfaces*.2013 **20** (5), 365–377.
- 278 [15]. D. Pathania, D. Gupta, A.H. Al-Muhtaseb, G. Sharma, A. Kumar, M. Naushad, T. Ahamad and S.M.
279 Alshehri, Photocatalytic degradation of highly toxic dyes using chitosan-g-poly (acrylamide)/ZnS in pre-
280 sence of solar irradiation. *J Photochem Photobiol A Chem* 2016, **329**, 61–68
- 281 [16]. A. Deng, J. Chen, H. Li, J. Ren, R. Sun, L. Zhao, *Biol Res* 2014, **9**(2), 2717–2726.
-
- 282 [17]. X. Liu, J. Zhang, L. Wang, T. Yang, X. Guo, S. Wu and S. Wang, 3D hierarchically porous ZnO
283 structures and their functionalization by Au nanoparticles for gas sensors. *J. Mater. Chem.*, 2011, **21**, 49-356.
- 284 [18]. Z.H. Jing and J.H. Zhan, Fabrication and gas-sensing properties of porous ZnO nanoplates. *Adv.*
285 *Mater.*, 2008, **20**, 4547-4551.
- 286 [19]. Y.C. Qiu, W. Chen and S.H. Yang, Facile hydrothermal preparation of hierarchically assembled, porous
287 single-crystalline ZnO nanoplates and their application in dye-sensitized solar cells. *J. Mater. Chem.*,
288 2010, **20**, 1001-1006.
- 289 [20]. D.C. Look, Recent advances in ZnO materials and devices *Mater. Sci. Eng., B*, 2001, **80**, 383-387.
- 290 [21]. X.J. Feng, L. Feng, M.H. Jin, J. Zhai, L. Jiang and D.B. Zhu, Reversible super-hydrophobicity to
291 super-hydrophilicity transition of aligned ZnO nanorod films. *J. Am. Chem. Soc.*, 2004, **126**, 62-63
- 292 [22]. L. Vayssieres, Growth of arrayed nanorods and nanowires of ZnO from aqueous solutions *Adv. Mater.*,
293 2003, **15**, 464-466.
- 294 [23]. M.S. Arnold, P. Avouris, Z.W. Pan and Z.L. Wang, Field-effect transistors based on single semicon-
295 ducting oxide nanobelts. *J. Phys. Chem. B*, 2003, **107**, 659-663

-
- 296 [24]. C.L. Kuo, T.J. Kuo and M.H. Huang, Hydrothermal synthesis of ZnO microspheres and hexagonal
297 microrods with sheetlike and platelike nanostructures. *J. Phys. Chem. B*, 2005, **109**, 20115-20121.
- 298 [25]. X.W. Lou, Y. Wang, C. Yuan, J.Y. Lee and L.A. Archer, Template-free synthesis of SnO₂ hollow
299 nanostructures with high lithium storage capacity. *Adv. Mater.*, 2006, **18**, 2325-2329.
- 300 [26]. X.W. Lou, C. Yuan and L.A. Archer, Shell-by-shell synthesis of tin oxide hollow colloids with
301 nanoarchitected walls: cavity size tuning and functionalization. *Small*, 2007, **3**, 261-265.
- 302 [27]. L. Robben, A.A. Ismail, S.J. Lohmeier, A. Feldhoff, D.W. Bahnemann and J.C. Buhl, Facile synthesis of
303 highly ordered mesoporous and well crystalline TiO₂: Impact of different gas atmosphere and calcina-
304 tion temperatures on structural properties. *Chem. Mater.*, 2012, **24**, 1268-1275.
- 305 [28]. R.Q. Song, A.W. Xu, B. Deng, Q. Li and G.Y. Chen, From layered basic zinc acetate nanobelts to hi-
306 erarchical zinc oxide nanostructures and porous zinc oxide nanobelts. *Adv. Funct. Mater.*, 2007, **17**,
307 296-306.
- 308 [29]. B. Li and Y. Wang, Facile synthesis and enhanced photocatalytic performance of flower-like ZnO hi-
309 erarchical microstructures. *J. Phys. Chem. C*, 2010, **114**, 890-896.
- 310 [30]. M. Osgouei, M. Saket, H. Khatamian and H. Kakili, Improved visible-light photocatalytic activity of
311 Mn₃O₄-based nanocomposites in removal of methyl orange. *Mater. Chem. Phys.*, 2020, **239**, 122108.
- 312 [31]. T. Shen, S. Xueke, G. Jiaxiu, L. Jing and Y. Shandong, Photocatalytic removal of NO by light-driven
313 Mn₃O₄/BiOCl heterojunction photocatalyst: Optimization and mechanism. *Chem. Eng. J.*, 2021, **408**,
314 128014.
- 315 [32]. Y. Ma, J. Jiang, A. Zhu, P. Tan, Y. Bian, W. Zeng, H. Cui and J. Pan, Enhanced visible-light
316 photocatalytic degradation by Mn₃O₄/CeO₂ heterojunction: a Z-scheme system photocatalyst.
317 *Inorg. Chem. Front.*, 2018, **5**, 2579-2586.
- 318 [33]. R. Rahimi, A. Mehrehjedy and S. Zargari, BiVO₄/Mn₃O₄ a novel p-n heterojunction photocatalyst
319 functionalized with metalloporphyrins: Synthesis, charge transfer mechanism, and enhanced visi-
320 ble-light photocatalysis for degradation of dye pollutant *Environ. Prog. Sustain. Energy*, 2017, **36** ,
321 1439-1448.
- 322 [34]. Q. Ma, X. Zhang, R. Guo, H. Zhang, Q. Cheng, M. Xie and X. Cheng, Persulfate activation by magnetic
323 γ -Fe₂O₃/Mn₃O₄ nanocomposites for degradation of organic pollutants. *Separ. Purif. Technol.*, 2019,
324 **210**, 335-342.
- 325 [35]. N. Li, Y. Tian, J. Zhao, J. Zhang, J. Zhang, W. Zuo and Y. Ding, Efficient removal of chromium from
326 water by Mn₃O₄@ ZnO/Mn₃O₄ composite under simulated sunlight irradiation: synergy of
327 photocatalytic reduction and adsorption. *Appl. Catal., B*, 2017, **214**, 126-136.

-
- 328 [36]. M.T. Qamar, M. Aslam, Z. Rehan, M.T. Soomro, J.M. Basahi, I.M. Ismail, T. Almeelbi and A. Hameed,
329 The influence of p-type Mn₃O₄ nanostructures on the photocatalytic activity of ZnO for the removal of
330 bromo and chlorophenol in natural sunlight exposure. *Appl. Catal., B*, 2017, **201**, 105-118
- 331 [37]. R. Saravanan, V.K. Gupta, V. Narayanan and A. Stephen, Visible light degradation of textile effluent
332 using novel catalyst ZnO/ γ -Mn₂O₃. *J. Taiwan Inst. Chem. Eng.*, 2014, **45**, 1910-1917.
- 333 [38]. P.J. Shubha, H.S. Savitha, S.F. Adil, M. Khan, M.R. Hatshan, K. Kavalli and B. Shaik, Employing
334 manufactured Mn₃O₄-ZnO nanocomposite for ameliorated photocatalytic performance under visible
335 light. *dyes Molecules*, 2012, **26** (15), 4661.
- 336 [39]. S. Khan, A. Hussain, K. He, B. Liu, Z. Imran, J. Ambreen, S. Hassan, M. Ahmad, S. Sitwat Batool and C.
337 Li, Tailoring the bandgap of Mn₃O₄ for visible light driven photocatalysis. *J. Environ. Manag.*, 2021,
338 **293**,112854.
- 339 [40]. M.T. Qamar, M. Aslam, Z. Rehan, M.T. Soomro, J.M. Basahi, I.M. Ismail, T. Almeelbi and A. Hameed,
340 The influence of p-type Mn₃O₄ nanostructures on the photocatalytic activity of ZnO for the removal of
341 bromo and chlorophenol in natural sunlight exposure. *Appl. Catal., B*, 2017, **201**, 105-118.
- 342 [41]. A.A. Ullah, A.F. Kibria, M. Akter, M.M.I. Khan, A.R.M. Tareq and S.H. Firoz, Oxidative degrada-
343 tion of methylene blue using Mn₃O₄ nanoparticles. *Water Conservation Science and Engineering*,
344 2017, **1**(4), 249-256.
- 345 [42]. N. Kumar, H. Mittal, L. Reddy, P. Nair, J.C. Ngila and V. Parashar, Morphogenesis of ZnO
346 nanostructures: role of acetate (COOH⁻) and nitrate (NO₃⁻) ligand donors from zinc salt precursors in
347 synthesis and morphology dependent photocatalytic properties. *RSC Adv.*, 2015, **5**, 38801-38809

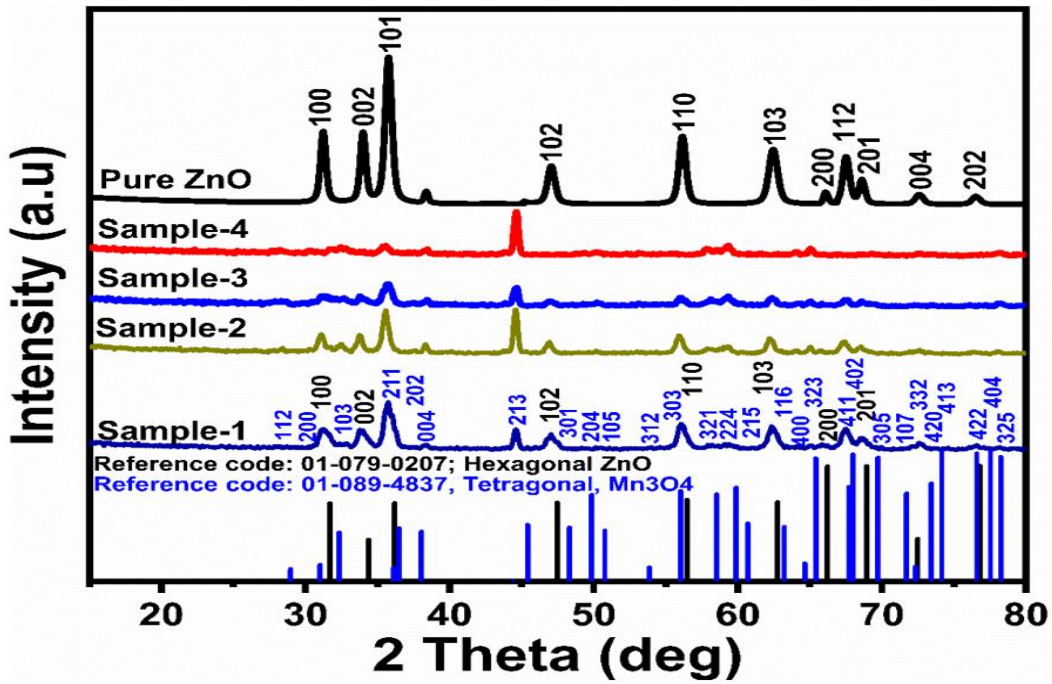

362 **Figure1:** (a) XRD patterns of pristine ZnO and ZnO doped with different amounts of Mn₃O₄ (b) shift
 363 comparison of the (220) peak for pristine ZnO and Mn₃O₄-doped samples.


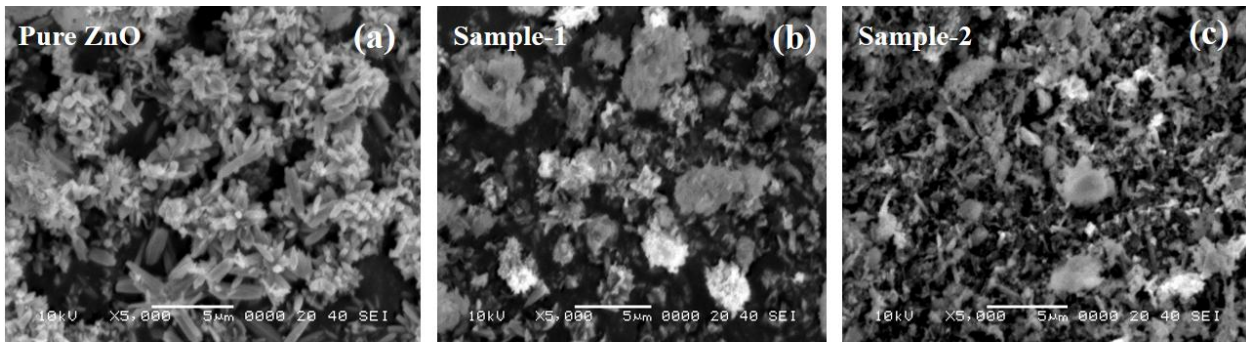


Figure 2:
SEM

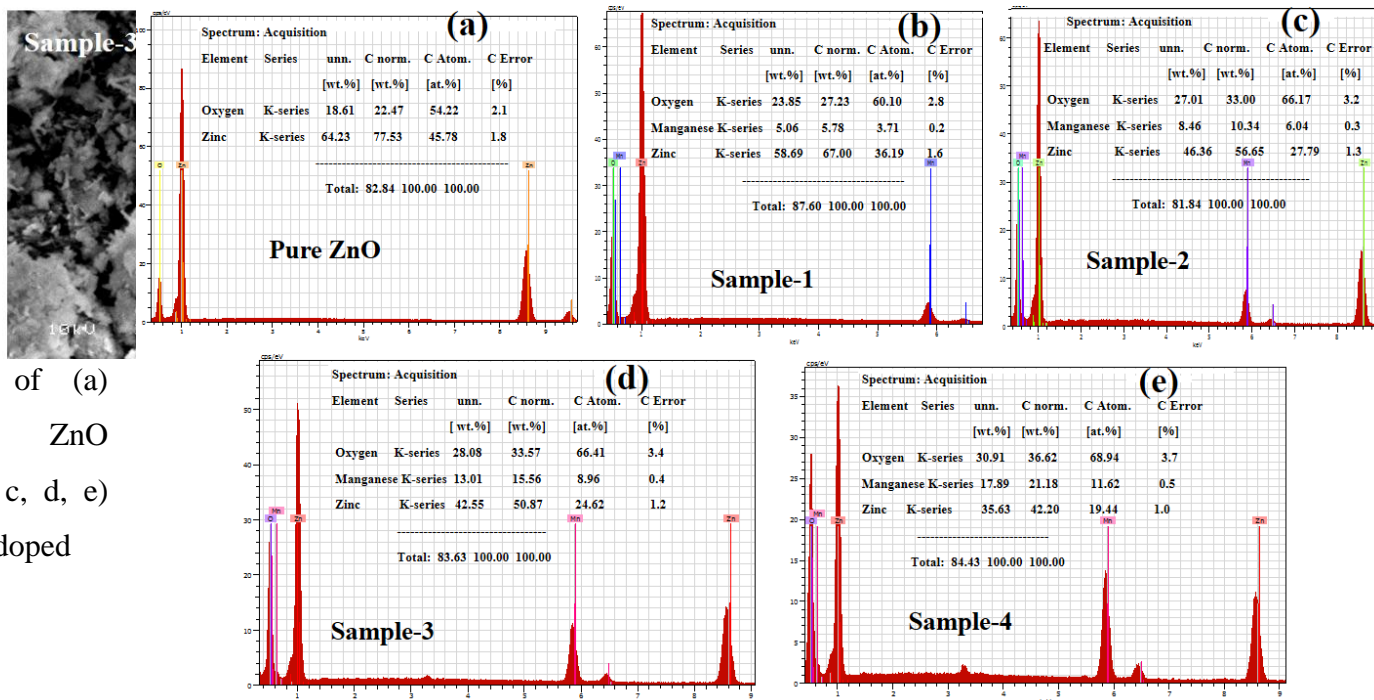

371 images of (a)
 372 pristine ZnO
 373 and (b, c, d, e)
 374 Mn₃O₄-doped

375 ZnO materials synthesized

376 by sol-gel method

377

378 **Figure 3:** (a) EDX analysis of (a) pristine ZnO and (b, c, d, e) Mn₃O₄-doped ZnO material synthesized

379 by Sol-gel method

380

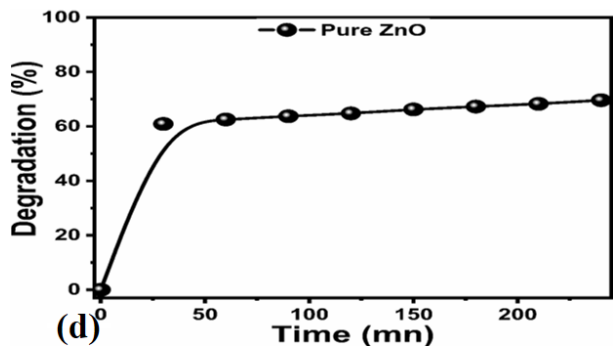
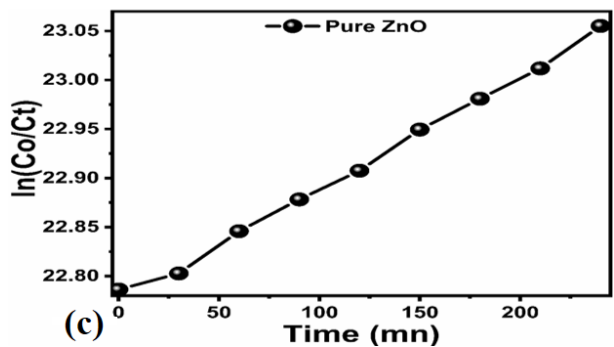
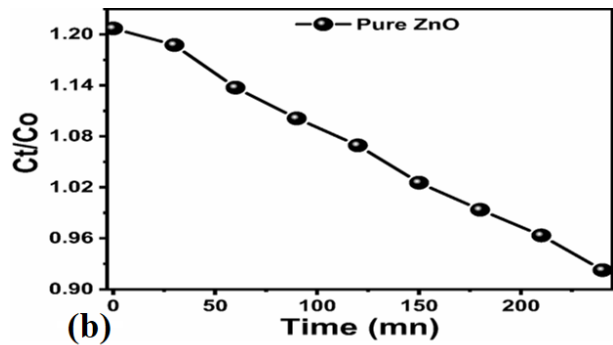
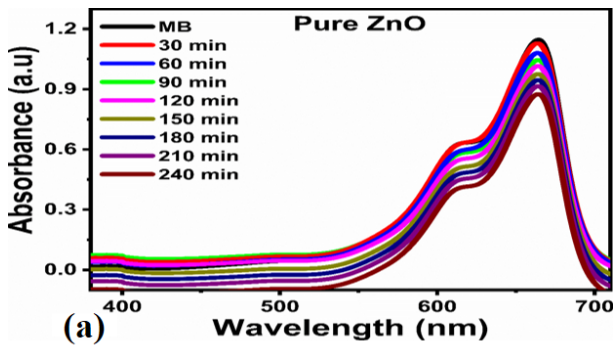


Figure 4:

Degrada-
tion over
time

(240 min)
of a so-
lution of

MB of
concen-
tration

$1.87 \times$
 10^{-5} M
under

394

irradia-

395 tion with UV light in the presence of 5 mg of pristine ZnO. (a) UV-vis absorption spectra during dye degra-

396 dation, (b) kinetics Ct/Co irradiation time, (c) LnCt/Co plot, (d) percent degradation of MB

397

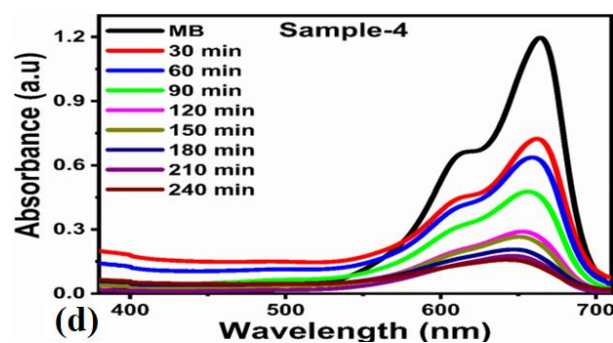
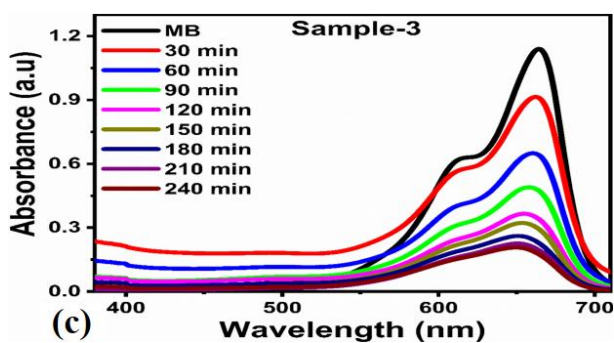
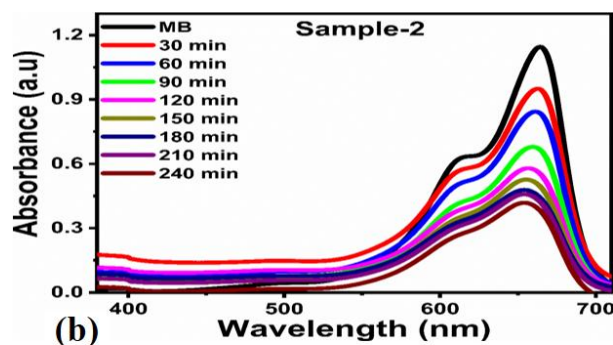
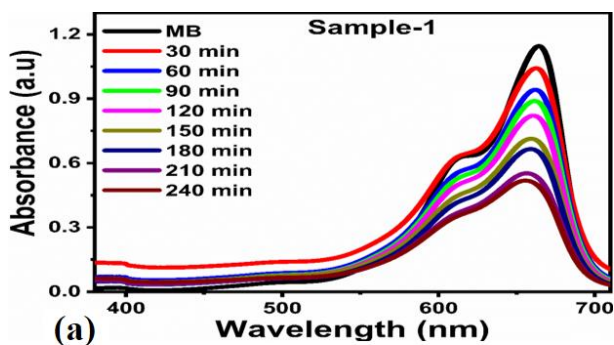


Figure 5:

(a-d)

UV-Vis
absorp-
tion

spectra

of the

MB so-
lution at

concen-

409 tration of $1.87 \times 10^{-5} \text{M}$ using 5 mg photocatalyst dose of hybrid materials during photodegradation under UV
 410 light illumination using samples 1-4 as photocatalysts

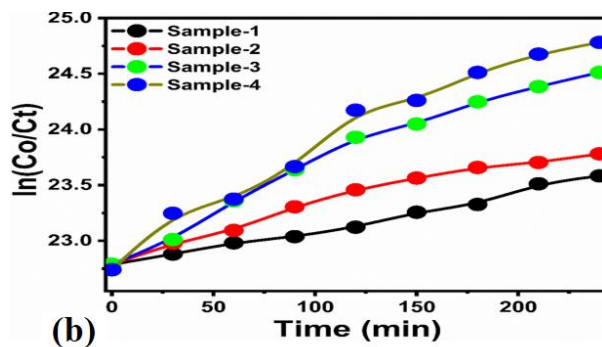
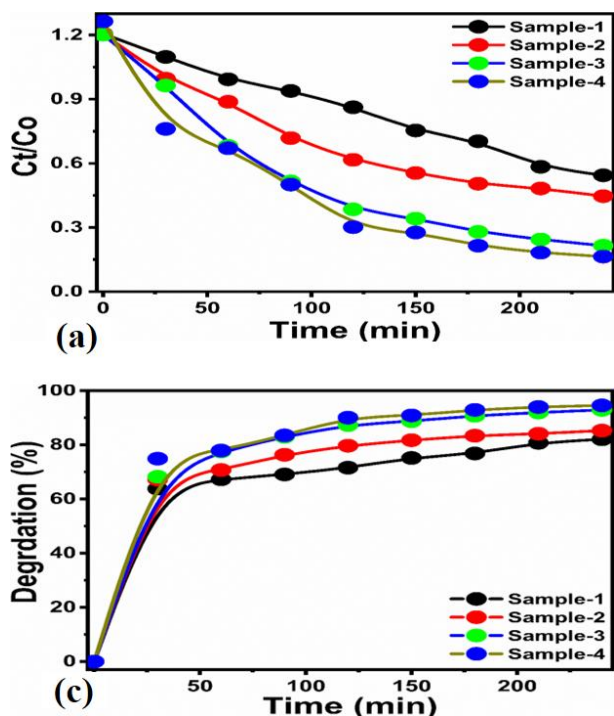


Figure 6: Degradation kinetics (a) C_t/C_0 versus irradiation time, (b) $\ln(C_0/C_t)$ plot, (c) percent

424 degradation of MB

425
426
427

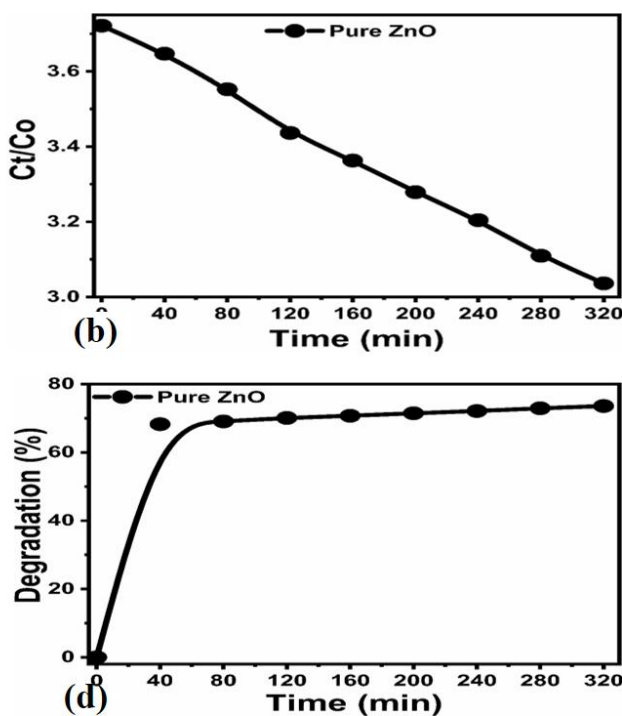
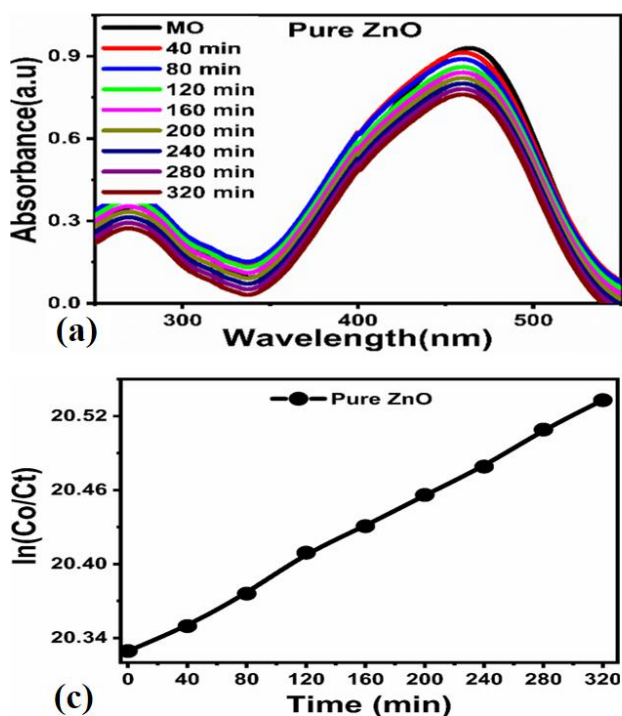


Figure 7: Degradation over time (320 min) of a solution of MO of concentration

442 tration $2.44 \times 10^{-5} \text{M}$ under irradiation with UV light in the presence of 5 mg of pristine ZnO. (a) Time

443 change of the UV-vis spectrum, (b) kinetics Ct/Co irradiation time, (c) LnCt/Co plot, (d) percent degradation
444 of MO

445
446
447
448

449


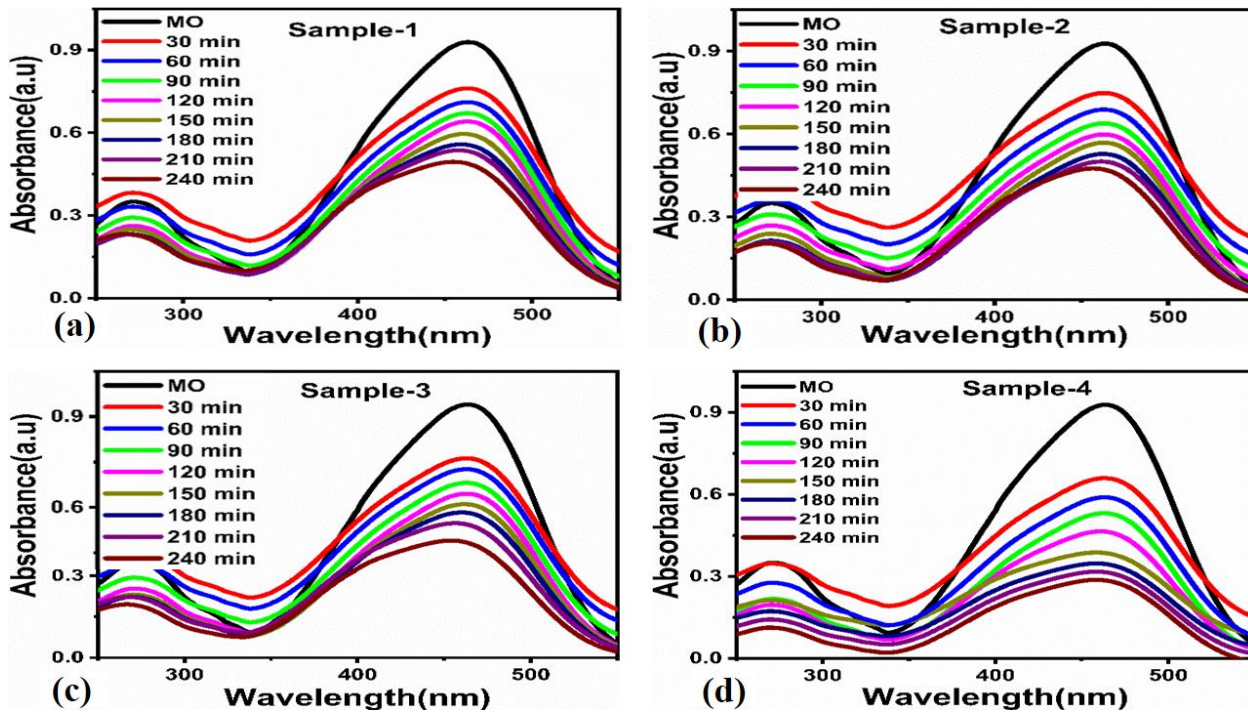


Figure 8:
(a-d)
UV-Vis
absorp-
tion
spectra
MO so-
lution at
concen-
tration of
 2.44×10^{-5}

463 ^5M during photodegradation under UV light illumination using 5 mg dose of samples 1-4 as hybrid
464 photocatalysts.

465

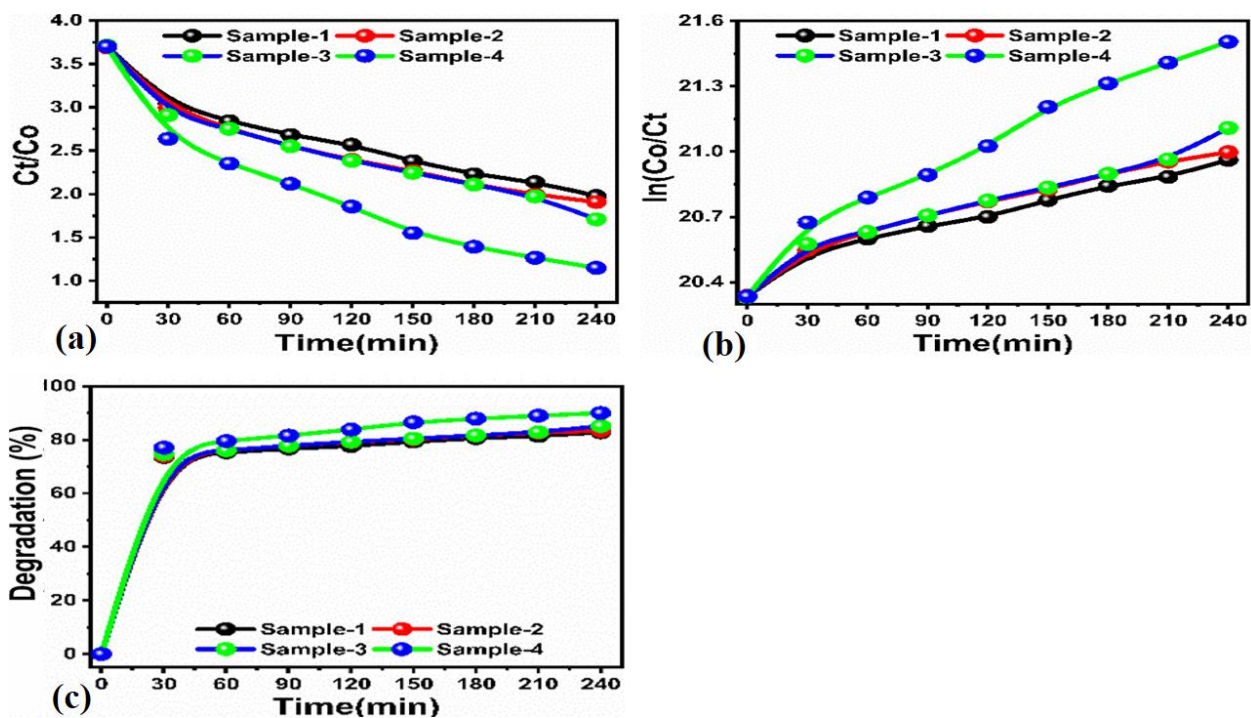

466
467 **Figure 9:** Degradation kinetics (a) kinetics Ct/Co irradiation time, (b) LnCt/Co plot, (c) percent degradation
468 of MO

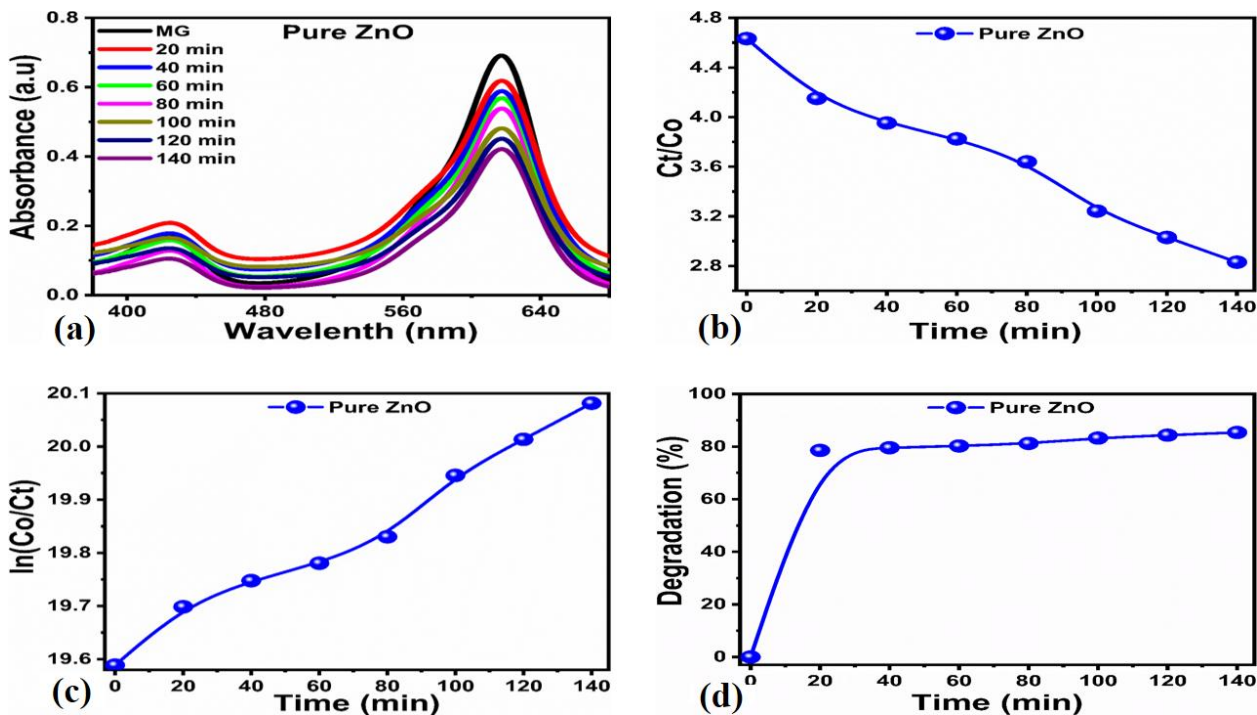


Figure 10: Degradation over time (140 min) of a solution of MG of concentration $5.48 \times$

484 10^{-5} M under irradiation with UV light in the presence of 5 mg of pristine ZnO. (a) Time change of the
485 UV-vis spectrum, (b) Ct/Co over irradiation time, (b) kinetics Ct/Co irradiation time, (c) LnCt/Co plot, (d)
486 percent degradation of MG

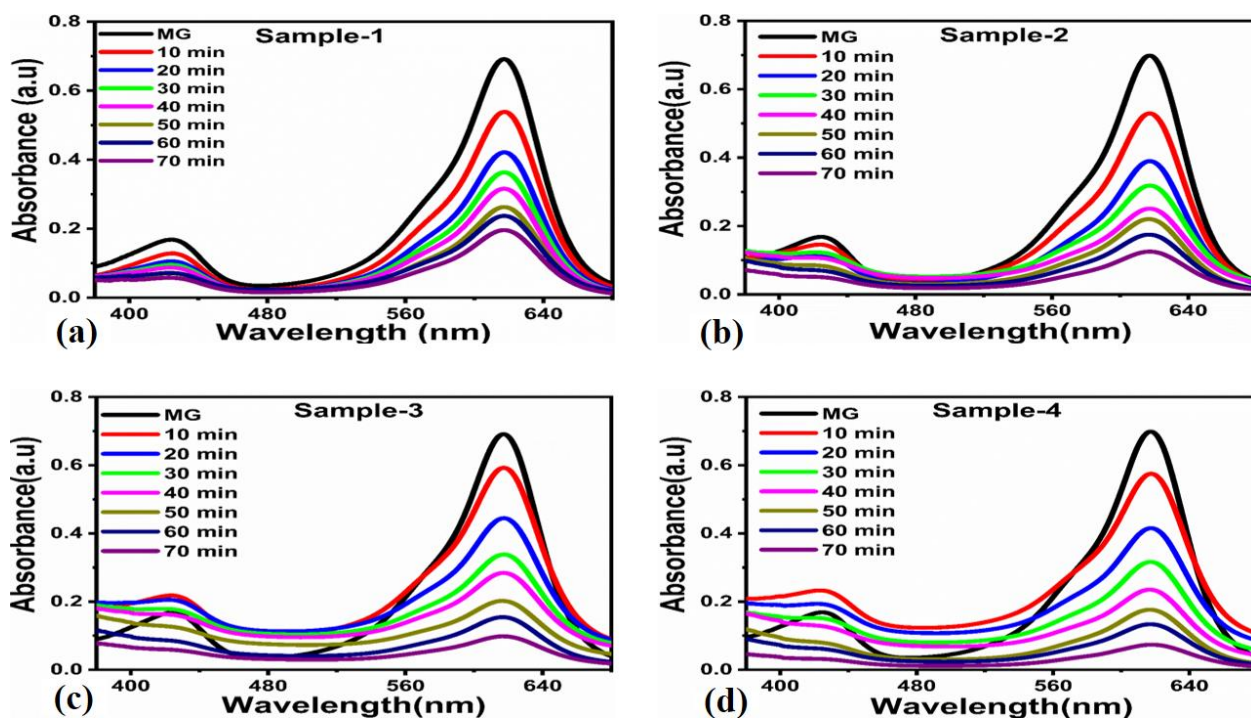


Figure 11: (a-d) change in the UV-Vis spectrum of the MG solution at

502 concentration of $5.48 \times 10^{-5} \text{ M}$ during photodegradation under UV light irradiation using 5mg dose of samples
 503 1-4 as photocatalysts.

504
 505
 506
 507
 508
 509
 510

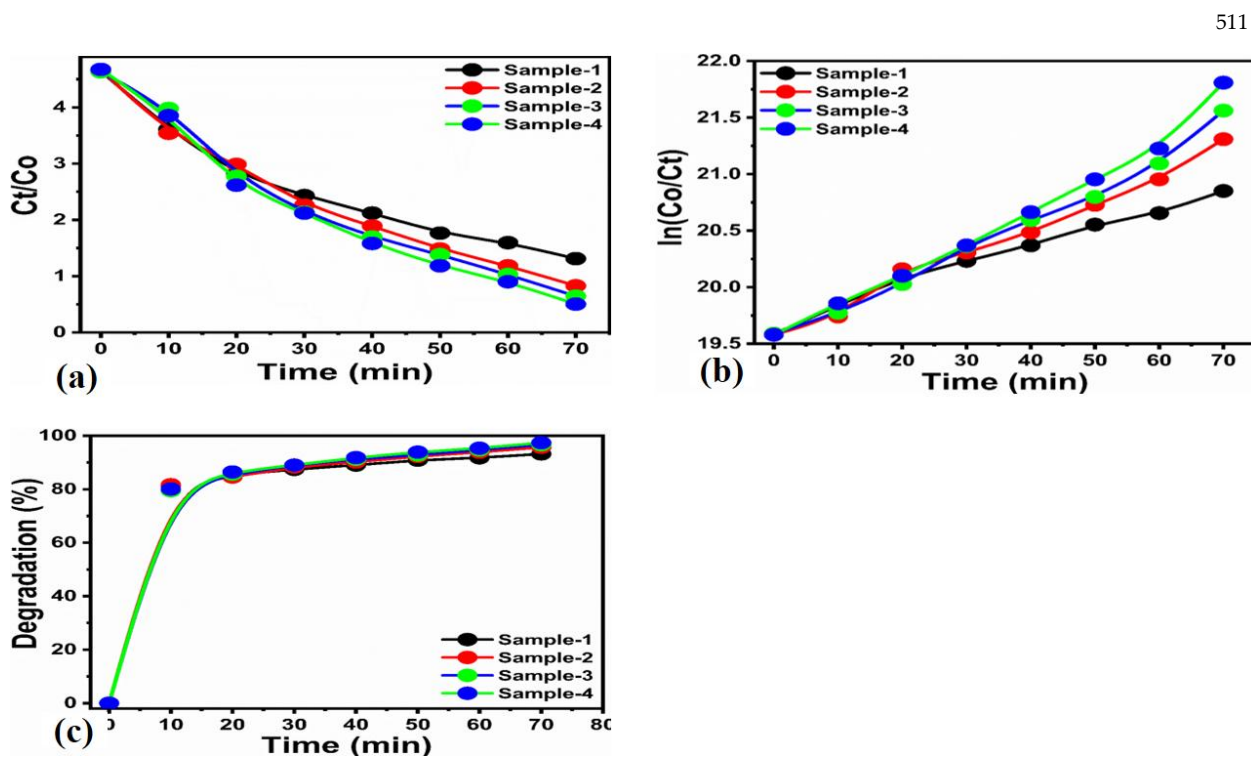


Figure 12: Degradation kinetics (a) kinetics Ct/Co

522 irradiation time, (b) LnCt/Co plot, (c) percent degradation of MG

523

524

525 **Table 1:** Summary of obtained results for the Photodegradation of various dyes using different
526 Mn₃O₄@ZnO hybrid materials in comparison to pure ZnO.

Sample Name	Dye	Degradation %	Time (min)	Rate constant (K)
Pure ZnO	MB	69.60 %	240 min	1.14×10^{-3} min
	MO	73.56 %	320 min	6.43951E-4
	MG	85.37 %	140 min	3.37×10^{-3} min
Sample-1	MB	82.07 %	240 min	3.33×10^{-3} min
	MO	82.78 %	240 min	2.32×10^{-3} min
	MG	93.22 %	70 min	1.72×10^{-2} min
Sample-2	MB	85.28 %	240 min	4.19×10^{-3} min
	MO	83.38 %	240 min	2.50×10^{-3} min
	MG	95.71 %	70 min	2.38×10^{-2} min
Sample-3	MB	92.91 %	240 min	7.33×10^{-3} min
	MO	85.12 %	240 min	2.74×10^{-3} min
	MG	96.67 %	70 min	2.73×10^{-2} min
Sample-4	MB	94.59 %	240 min	8.51×10^{-3} min
	MO	89.99 %	240 min	4.58×10^{-3} min
	MG	97.40 %	70 min	3.01×10^{-2} min

527

528